

A NEW SYNTHETIC HYDRATE OF ALUMINUM ARSENATE*

GERALD KATZ AND HORST KEDESZY, *Signal Corps Engineering Laboratories, Fort Monmouth, New Jersey.*

ABSTRACT

In an attempt to grow large crystals of aluminum orthoarsenate (AlAsO_4) by the hydrothermal method, a dense polycrystalline product resulted. The aggregate was in the form of fibrous crystallites in parallel arrangement which readily parted into fine, clear needles. Thermal decomposition analyses, chemical analysis, and powder and single crystal *x*-ray diffraction studies indicate this material to be a new hydrate of aluminum arsenate. The oxide formulation as determined by chemical analysis is:



An orthorhombic unit cell was established from rotation and Weissenberg studies as follows:

$$a = 12.30\text{\AA} \quad b = 4.64\text{\AA} \quad c = 8.61\text{\AA}.$$

The systematically absent reflections indicate a body-centered unit cell; the possible space groups are:

$$D_{2h}^{26} - I_{mmm}, \quad C_{2v}^{20} - I_{mm2}, \quad D_2^8 - I_{222}.$$

Two molecules per unit cell gives a calculated density $\rho = 3.27$. The pycnometric density is 3.21.

INTRODUCTION

One part of the research program of the Signal Corps Engineering Laboratories has been directed toward the synthesis of substitutes for piezoelectric quartz. In this connection, the growth and properties of aluminum orthoarsenate (AlAsO_4) have been studied because of its marked isomorphism with the natural piezoelectric quartz.¹ This compound has been shown to be isostructural with α -quartz with the three silicon atoms of the elementary cell of quartz statistically substituted in a 1:1 ratio by Al^{+3} and As^{+5} cations. The *c*-axis is doubled in order to distribute properly the Al^{+3} and the As^{+5} ions. In the course of an attempt to increase the size of aluminum orthoarsenate crystals grown by the hydrothermal method, changes were made in the normally used temperature gradient and ratio of Al_2O_3 , As_2O_5 , and H_2O of the feed materials. Instead of obtaining a single crystal with the usual well developed morphology, a dense polycrystalline product resulted. This aggregate was in the form of fibrous crystallites, in parallel arrangement, which readily parted into exceedingly fine, clear needles of a fibrous nature.

Figure 1 shows the gross character of the polycrystalline product. The overall height of this cross-sectional view is approximately 1.5 cm. The

* Presented at June 1953 meeting of American Crystallographic Association, Ann Arbor, Michigan.

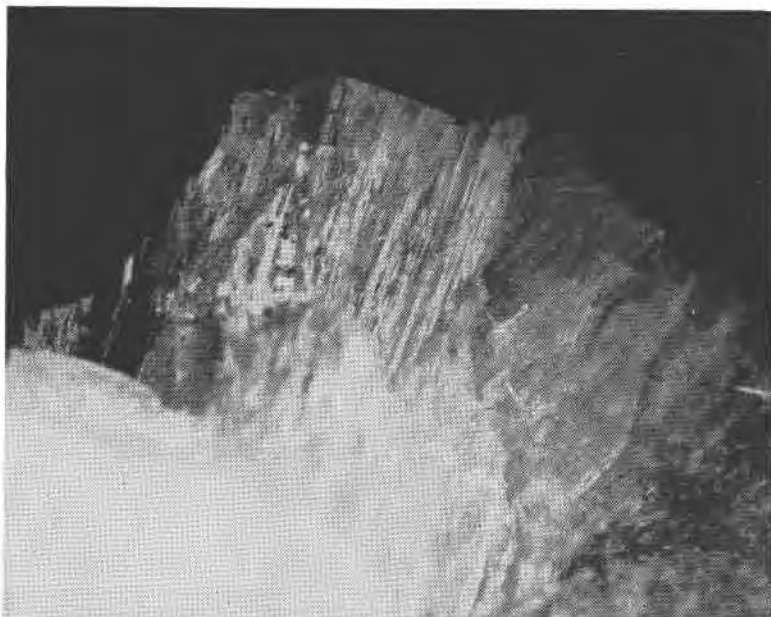


Fig. 1. Cross-sectional view of polycrystalline aggregate. Mag. 5 \times

electron micrograph (Fig. 2) shows the needle-like nature of the crystallites. The crystallites are generally triangular in cross-section and frequently have a characteristic cleavage at their tip, making an angle of approximately 110° with the needle axis.

THERMAL ANALYSES

As an initial step, the *x*-ray diffraction powder pattern made from selected clear crystals was compared with a reference pattern of aluminum orthoarsenate. The comparison disclosed at once that the material under study was not of the α -quartz structure (see Fig. 5). Since spectrochemical analysis showed aluminum and arsenic to be the only cations present in structurally significant amount, the possibility was considered that the material might be a hydrate of aluminum arsenate. In order to check this, a decomposition study was made of this compound using the differential thermal analysis method. The sample was heated from room temperature to $1,000^\circ\text{C}$. at a rate of 13°C./min . (Fig. 3). The *DTA* curve showed several endothermic peaks and a very small exothermic one. Such a *DTA* curve is not uncommon for hydrous compounds such as the hydrous aluminum phosphates.² The endothermic reactions at low temperature indicate the loss of water of crystallization; those at higher temperatures are correlated with the loss of water due to hydroxyl

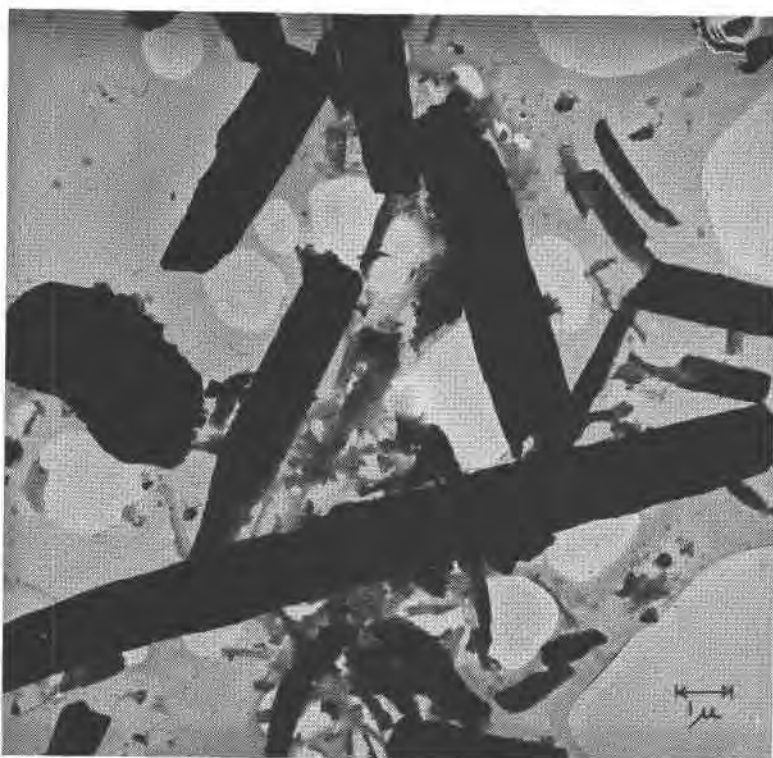


FIG. 2. Electron micrograph of crystallites showing their acicular nature and characteristic cleavage at the end of needles. Mag. 7,500 \times

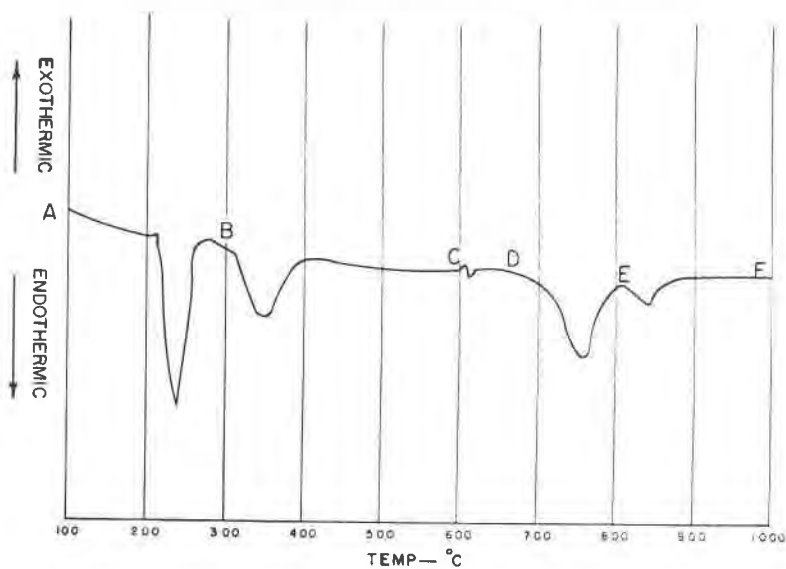


FIG. 3. Differential thermal analysis curve, heating rate—13° C./min.

groups in the structure. Recrystallization is indicated by exothermic reaction peaks.

As will be shown from the chemical analysis, this structure is believed to have a total of 10 waters per unit cell. A rough comparison was made of the area under each of the major endothermic peaks in order to explain the various steps of the conversion to the anhydrate. The first sharp peak at 240°C . appears to be the loss of all the water of crystallization. This water is bonded by van der Waals' forces and may be expected to

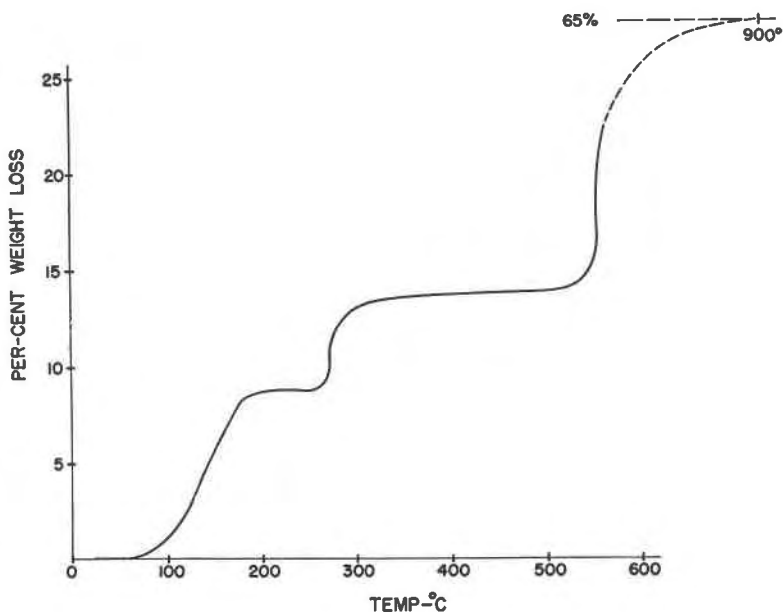


FIG. 4. Static loss-in-weight curve.

be the first to leave the structure. This would mean that all the waters of crystallization would leave at 240°C . and the remaining 6 waters, due to hydroxyl groups, would be distributed among the other three endothermic peaks according to their relative areas; namely, 3 waters at 355°C ., 2 waters at 765°C ., and 1 water at 835°C .

In order to check the *DTA* results concerning the water loss, a loss-in-weight study of a heated sample of this aluminum arsenic compound was made (Fig. 4). A powdered sample was heated at progressively higher temperatures; the specimen being held at each temperature for a three-hour period. The two steps in the curve below 300°C ., which correspond to the first two endothermic peaks of the *DTA* curve, indicate

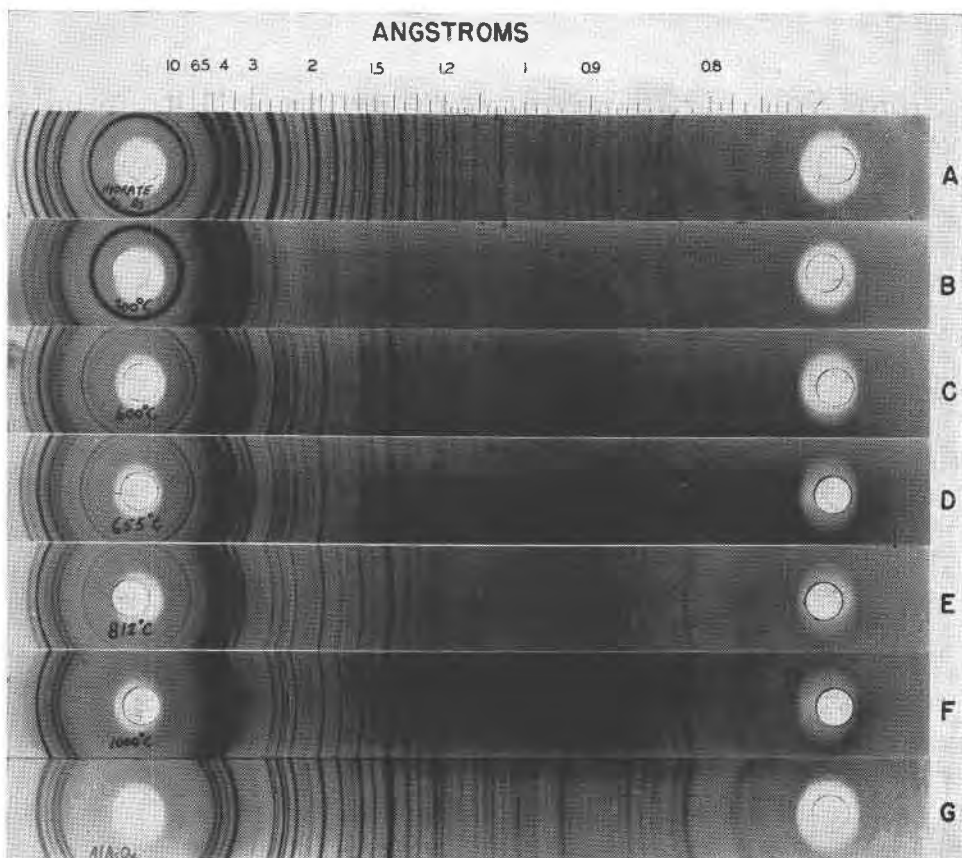


FIG. 5. X-ray powder patterns taken using CuK radiation $\lambda = 1.5418 \text{ \AA}$; camera radius 57.3 mm. All patterns taken at room temperature. *A*—Hydrate of aluminum arsenate—unheated. *B*—Hydrate after air-quenching from 300° C . *C*—Hydrate after air-quenching from 600° C . *D*—Hydrate after air-quenching from 655° C . *E*—Hydrate after air-quenching from 812° C . *F*—Hydrate after air-quenching from 1000° C . *G*—Aluminum orthoarsenate—pattern made from ground single crystal.

a loss-in-weight of about 14%. This compares very well with the calculated losses of $4\text{H}_2\text{O}$ between $100^\circ\text{--}170^\circ \text{ C}$. and $3\text{H}_2\text{O}$ in the vicinity of 270° C . which give a theoretical cumulative loss of 13%, 1% difference is attributed to adsorbed water. Above 600° C . there was a marked increase in the weight-loss accompanied by the evolution of As_2O_3 and O_2 from the sample. Since no differentiation could be made between the water loss and the loss due to As_2O_3 and O_2 , the loss-in-weight measurements were discontinued.

X-RAY DIFFRACTION POWDER ANALYSIS

To further monitor the decomposition study, Debye-Scherrer powder patterns were made of samples after being heated in the *DTA* unit to temperatures bracketing each reaction peak as indicated by the lettered points in Fig. 3. Each of the samples was heated at the same rate of 13°C./min. , as in the *DTA* run, to the desired temperature and then immediately air-quenched. The powder patterns in Fig. 5 were obtained from air quenched specimens corresponding to the lettered points in the *DTA* curve (Fig. 3). While the patterns of each of the quenched specimens have not been completely identified, the patterns which bracket the *DTA* peaks indicate phase transitions, some probably representing mixtures of two or more phases. It is interesting to note from the diffraction patterns that a marked change occurs in the heating interval between room temperature and 300°C. ; after the evolution of the water of crystallization, the sample exhibits broader diffraction lines. Between 300°C. – 600°C. there is another noticeable change reflected in the diffraction patterns. The characteristic 6 \AA and 7 \AA lines of the original material re-appear with a reversal in their relative intensity. At the same time, the first appearance of the strongest characteristic lines of AlAsO_4 are detected, at 3.45 \AA , 2.18 \AA , 1.88 \AA , 1.42 \AA , 1.41 \AA . It is surprising to note that before reaching the last decomposition step the final phase has already appeared. Its intensity shows that only a small amount has been converted. However, an attempt to complete the formation of AlAsO_4 by heating this compound for four days at 500°C. was unsuccessful. At 655°C. there is a more noticeable appearance of the final AlAsO_4 phase with a gradual diminution in the intensity of the intermediate phase represented by the 6 \AA and 7 \AA lines. A slight shift is noted in the 5 \AA line changing to 5.2 \AA . At 812°C. only the 6.5 \AA , 5.5 \AA , and 2.79 \AA lines are detectable in addition to those of the AlAsO_4 pattern. At 1000°C. the material is completely converted to AlAsO_4 ; its pattern can be seen to be identical to that made from a pure AlAsO_4 single crystal (see Fig. 5, pattern G).

These results led us tentatively to designate this material as a hydrate of aluminum arsenate. A literature study of the arsenates and phosphates has indicated the existence of a number of mineral hydrates of the phosphates and arsenates. Table 1 summarizes various reported hydrates found in nature. Among these is a di-hydrate of aluminum orthoarsenate called mansfieldite, $(\text{AlAsO}_4 \cdot 2\text{H}_2\text{O})$ reported by V. T. Allen, J. J. Fahey, and J. M. Axelrod.³ However, no crystallographic data were given other than that the powder pattern of the material, which was intimately intergrown with kaolinite and quartz, was similar to that of scorodite

($\text{FeAsO}_4 \cdot 2\text{H}_2\text{O}$). A comparison of the powder pattern made from a sample of mansfieldite supplied by the authors with the powder pattern of this material under investigation established them to be different compounds; yet mansfieldite may well be $\text{AlAsO}_4 \cdot 2\text{H}_2\text{O}$. In all the hydrates reported in Table 1, there is a 1:1 atomic ratio of the metal cations.

TABLE 1. ISOSTRUCTURAL α -QUARTZ COMPOUNDS AND MINERAL DI-HYDRATES OF PHOSPHATES AND ARSENATES

Formula	Name	a_0	b_0	c_0	β	ρ_x	$\rho_s \sigma$
SiO_2	Quartz	4.90 Å	—	5.39 Å	—	2.65	—
AlAsO_4	Aluminum ortho-arsenate ¹	5.03 Å	—	2x 5.61 Å	—	3.34	3.30
AlPO_4	Aluminum ortho-phosphate	4.93 Å	—	2x 5.47 Å	—	2.56	—
$\text{FePO}_4 \cdot 2 \text{H}_2\text{O}$	Phosphosiderite ⁴	5.30 Å	9.79 Å	8.67 Å	90°36'	2.74	2.76
$\text{FePO}_4 \cdot 2 \text{H}_2\text{O}$	Phosphosiderite ⁵	5.28 Å	9.75 Å	8.71 Å	90°36'	—	2.76
$\text{FePO}_4 \cdot 2 \text{H}_2\text{O}$	Strengite ⁵	10.06 Å	9.85 Å	8.65 Å	—	2.89	2.86
$\text{FeAsO}_4 \cdot 2 \text{H}_2\text{O}$	Scorodite ⁶	8.88 Å	10.26 Å	9.98 Å	—	3.35	3.41
$\text{FeAsO}_4 \cdot 2 \text{H}_2\text{O}$	Scorodite ⁷	10.42 Å	8.96 Å	10.15 Å	—	3.24	3.27
$\text{AlPO}_4 \cdot 2 \text{H}_2\text{O}$	Variscite ⁴	9.85 Å	9.55 Å	8.50 Å	—	2.61	2.5
$\text{AlPO}_4 \cdot 2 \text{H}_2\text{O}$	Metavariscite ⁴	5.15 Å	9.45 Å	8.45 Å	~90°	2.53	2.54
$\text{AlAsO}_4 \cdot 2 \text{H}_2\text{O}$	Mansfieldite ³	—	—	—	—	—	3.03

CHEMICAL ANALYSIS

A chemical analysis was made in order to compare the composition of the hydrate under investigation with those shown in the table. The following result was obtained:


	<i>Analysis</i>	<i>Postulated</i>	<i>Calculated</i>
	<i>Wt. %</i>	<i>Formula</i>	<i>Wt. %</i>
Al_2O_3	11.7	$1 \cdot \text{Al}_2\text{O}_3$	10.5
As_2O_5	69.8	$3 \cdot \text{As}_2\text{O}_5$	71.0
H_2O	18.0	$10 \cdot \text{H}_2\text{O}$	18.5
	99.5%		100.0%

This indicates a 1:3 ratio of Al:As. The total loss-in-weight of the sample, including the loss of water and of other volatile decomposition products, when ignited at 900° C., was found to be 64.6%. From this it can be assumed that a decomposition has taken place with the liberation of As_2O_3 and O_2 as well as water. Taking 18% from the loss as the amount of liberated water the remainder of the loss would correspond to two moles of As_2O_5 .

From these results the following formula for this hydrate of aluminum arsenate was proposed:



Using this formula, it can be assumed that the following decomposition takes place:



SINGLE CRYSTAL ANALYSIS

As described earlier, no difficulty was encountered in obtaining a fine, clear needle of the material suitable for single-crystal x -ray studies.

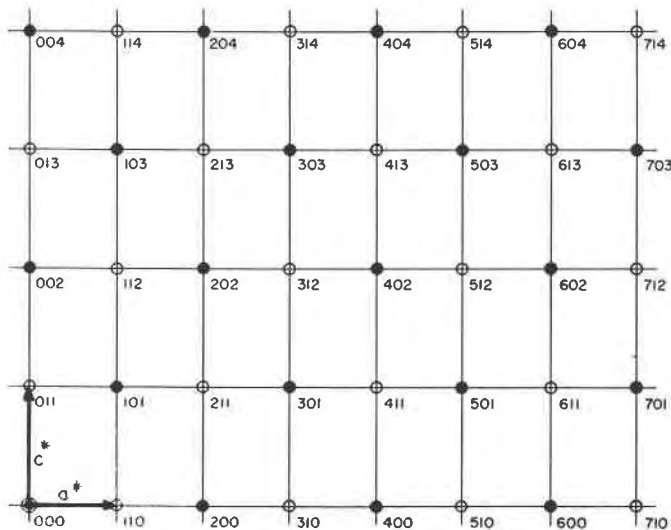


FIG. 6. Zero and 1st level of the reciprocal lattice from b -axis rotation.

●—zero level. ○—1st level.

Uniformly parallel optical extinction between crossed Nicols along the needle or fiber axis indicated this direction to be a crystallographic axis. Rotation photographs were taken of this crystal; the crystal being rotated about the fiber axis. The identity period, as determined from the rotation photograph, is 4.64 \AA . In addition, Weissenberg photographs were taken for the zero, first, and second layer lines. Figure 6 represents the reciprocal lattice drawn to scale as found from the evaluation of the Weissenberg photographs. The dots represent the zero level, the circles the first layer line. The two reciprocal axes chosen lie 90° apart giving an

TABLE 2. X-RAY POWDER DATA—HYDRATE OF ALUMINUM ARSENATE—



Orthorhombic: $a=12.30 \text{ \AA}$, $b=4.64 \text{ \AA}$, $c=8.61 \text{ \AA}$; $Z=2$

Possible Space Groups: $D_{2h}^{25}-I_{mmm}$, $C_{2v}^{20}-I_{mm2}$, $D_2^8-I_{222}$

Radiation: Cu-Ni filter $\lambda=1.5418 \text{ \AA}$

<i>I</i>	<i>d</i> (meas.)	<i>hkl</i>	<i>d</i> (calc)*	<i>I</i>	<i>d</i> (meas.)	<i>hkl</i>	<i>d</i> (calc.)*
VS	7.09	101	7.04			600	2.05
M-	6.10	200	6.15	M	2.04	022	2.04
						204	2.03
VS	4.33	110	4.34	M, B	1.963	321	1.966
		002	4.31				
M	4.08	011	4.08	M+	1.944	512	1.940
						222	1.938
VS	3.69	301	3.70	M-	1.925	114	1.929
						413	1.918
M	3.54	202	3.53	W	1.860	503	1.868
VS	3.39	211	3.40				
				W	1.845	420	1.852
		400	3.08			602	1.851
VS	3.06	310	3.07	W, B	1.833	611	1.832
		112	3.06				
M	2.81	103	2.80	M	1.785	123	1.785
S	2.51	312	2.50				
		402	2.49	S	1.766	404	1.763 ₄
						314	1.762 ₉
M+	2.44	411	2.46	M	1.708	105	1.705
		013	2.44			422	1.701
		501	2.37	VW, B	1.652	521	1.656
VW	2.31	303	2.35			323	1.651
		020	2.32				
M	2.27	213	2.27	M-	1.640	710	1.643
VW	2.20	121	2.20	M-	1.622	015	1.614
				M-	1.593	305	1.588
		510	2.17 ₃				
M-	2.17	220	2.17 ₁	M	1.570	024	1.578
		004	2.15			613	1.570

* Calculated *d* spacings taken from indices of zero, 1st, and 2nd level Weissenberg photographs, *b*-axis rotation CuK radiation.

TABLE 2—continued

<i>I</i>	<i>d</i> (meas.)	<i>hkl</i>	<i>d</i> (calc.)*	<i>I</i>	<i>d</i> (meas.)	<i>hkl</i>	<i>d</i> (calc.)*
M	1.560	424	1.567	M, B	1.229	903	1.234
		215	1.561			1000	1.230
		800	1.537			705	1.229
		620	1.536			822	1.228
M+	1.534	712	1.535	M, B	1.203	107	1.224
		514	1.529			525	1.205
		224	1.528			516	1.198
						226	1.197
M	1.519	604	1.515	VVW	1.187	017	1.189
M	1.493	703	1.499			1002	1.183
VW, B	1.470	523	1.455	M, B	1.176	1011	1.178
						307	1.177
M	1.446	802	1.448	M, B	1.153	606	1.176
		622	1.447			035†	1.151
W	1.437	811	1.437	W+	1.139	426	1.134
		006	1.435	W	1.122	914	1.120
		413	1.429				
M, B	1.410	505	1.411	W, B	1.115	815	1.113
						417	1.109
M	1.370	125	1.374	W, B	1.098	1101	1.109
		901	1.367			824	1.101
M	1.360	116	1.363	W, B	1.084	507	1.100
						1013	1.098
						1110	1.087
						1020	1.086 ₇
						725	1.084
						127	1.083
						716	1.081
VW	1.275	820	1.282	W, B	1.069	905	1.071
						1004	1.068
M, B	1.268	615	1.268	M, B	1.053	208	1.060
						1112	1.054
M, B	1.248	912	1.254	M, B	1.053	327	1.050
		804	1.251			806	1.049
		624	1.250			626	1.048 ₈

† Reflection outside sphere of reflection for *b*-axis rotation. B broad diffraction line.

orthorhombic real unit cell. The unit cell dimensions were determined to be:

$$a = 12.30\text{\AA}$$

$$b = 4.64\text{\AA}$$

$$c = 8.61\text{\AA}$$

Table 2 is an evaluation of the powder pattern using the lattice parameters obtained from the rotation and Weissenberg data. The indices for the calculated d spacings were obtained from the zero, 1st, and 2nd level Weissenberg photographs. The d spacings for indices outside the sphere of reflection for b -axis rotation using Cu/Ni filtered radiation were not calculated.

Using the previously postulated chemical formula of $\text{Al}(\text{H}_2\text{AsO}_4)_3 \cdot 2\text{H}_2\text{O}$ together with the unit cell dimensions, the density can be calculated

$$\rho_x = \frac{M \cdot Z \cdot 1.65}{V}$$

M = Mol. weight

Z = Moles per unit cell

V = Unit cell volume in \AA^3

assuming $Z=2$, we get:

$$\rho_x = \frac{485.70 \times 2 \times 1.65}{12.30 \times 4.64 \times 8.61} = 3.27.$$

Due to the characteristic fibrous nature of the crystals, it was necessary to powder the material in order to obtain accurate density measurements. The pycnometric density determined using toluene was 3.21.

Figure 7 shows the indexing of the reciprocal lattice of the zero and 1st level directly on the Weissenberg photographs. The 2nd level was a repetition of the zero level.

The following reflections were found to be systematically absent:

$$\begin{array}{ll} hkl & \text{with } h + k + l = 2n + 1 \\ 00l & \text{with } l = 2n + 1 \\ h00 & \text{with } h = 2n + 1 \\ h0l & \text{with } h + l = 2n + 1 \\ 0kl & \text{with } k + l = 2n + 1 \end{array}$$

This indicates a body-centered unit cell. Considering the assumed chemical formula of the compound and the extinction rules found, the possible space groups are: $D_{2h}^{25} - I_{mmm}$, $C_{2v}^{20} - I_{mn2}$, $D_2^8 - I_{222}$.⁸

⁸ R. Pepinsky, private communication April 20, 1954, Penn. State University, hydrate of aluminum arsenate found to be clearly piezoelectric. This data, which is in agreement with the detection of optical activity and triboluminescence, eliminates the centrosymmetric space group $D_{2h}^{25} - I_{mmm}$.

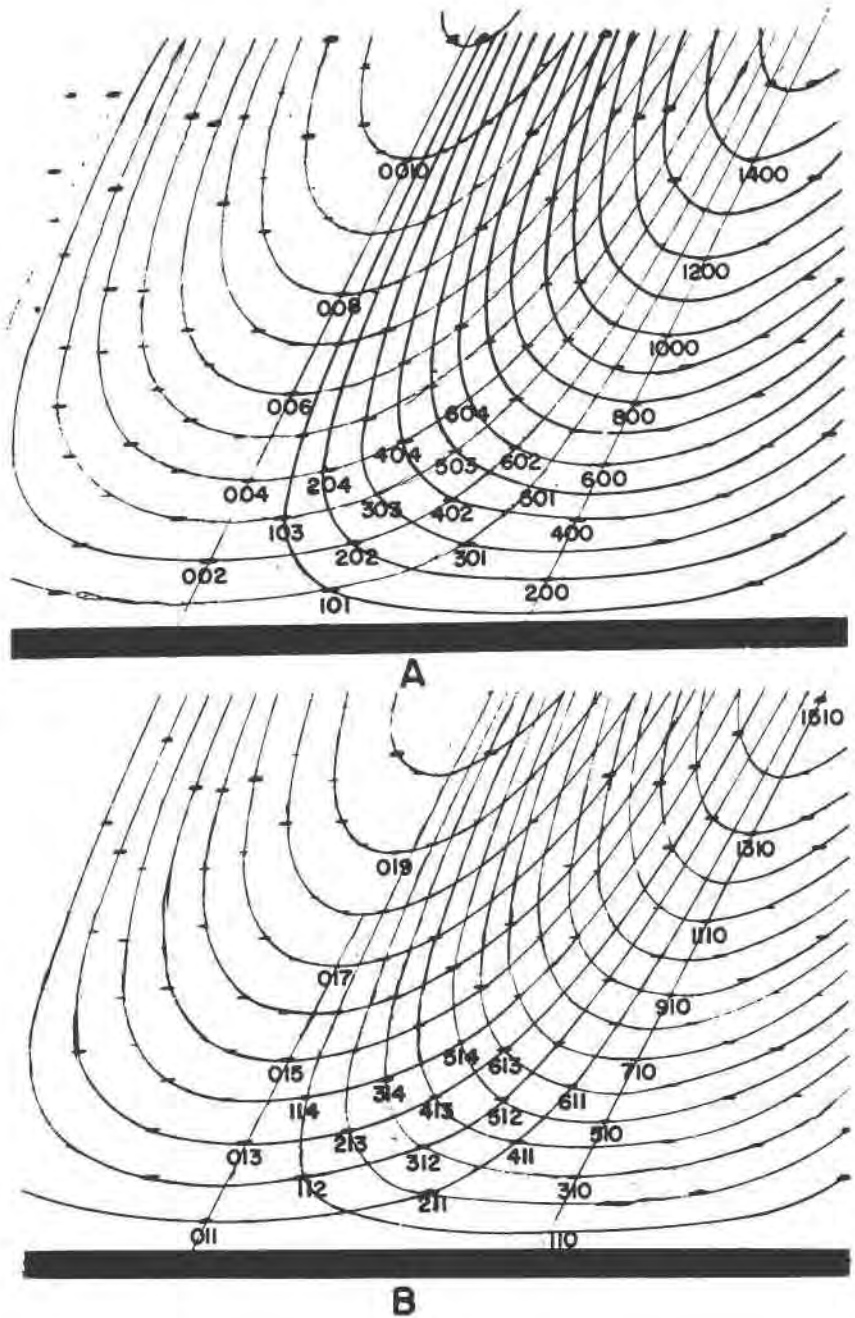


FIG. 7. Indexed Weissberg photographs. A—zero level. B—1st level.

This paper has described the identification and characterization and preliminary structure postulation of a new synthetic hydrate of aluminum arsenate. A complete structure determination has been started.

ACKNOWLEDGMENTS

The authors wish to express their indebtedness to the following: Mr. J. M. Stanley for growing the sample; Mr. S. delVecchio for performing the chemical analysis; Mr. L. Toman for obtaining the *DTA* data; Mr. R. Clarke for the density measurement.

REFERENCES

1. MACHATSCHKI, F., The crystal structure of aluminum arsenate AlAsO_4 : *Zeit. Krist.*, **90**, 314-321 (1935).
2. MANLY, R. L., JR., The differential thermal analysis of certain phosphates: *Am. Mineral.*, **35**, 108-115 (1950).
3. ALLEN, V. T., FAHEY, J. J. , AND AXELROD, J. M., Mansfieldite, a new arsenate, the aluminum analogue of scorodite, and the mansfieldite-scorodite series: *Am. Mineral.*, **33**, 122-134 (1948).
4. McCONNELL, D., Clinobarrandite and isodimorphous series, variscite-metavariscite: *Am. Mineral.*, **25**, 719-725 (1940).
5. STRUNZ, H., AND SZTRÓKAY, K. V., Isomorphism between metavariscite, variscite, phosphosiderite, and strengite: *Zentral. Mineralogie, Geol., Palaont.*, **A**, 272-278 (1939).
6. KOKKOROS, P., *Extr. Prakt. Acad. Athenes*, **13**, 337 (1938).
7. KIRIYAMA, R., AND SAKURAI, K., The crystal structure of scorodite: *X-Sen (Rays)*, **5**, 85-88 (1949).

Manuscript received Aug. 31, 1953