

OLIVINE X-RAY DETERMINATIVE CURVE

H. S. YODER, JR., *Geophysical Laboratory, Carnegie Institution of Washington, Washington, D. C.*

AND

TH. G. SAHAMA, *Institute of Geology, Helsinki, Finland.*

ABSTRACT

The (130) spacing of 31 chemically analyzed natural olivines and seven synthetic olivines has been measured. A determinative curve has been calculated from 26 of the chemically analyzed natural olivines:

$$Fo \text{ (mol \%)} = 4233.91 - 1494.59 d_{130}.$$

The fictive end points are $d_{130} \text{ (Fo=100)} = 2.7659$ and $d_{130} \text{ (Fo=0)} = 2.8328$. The error attached to an individual measurement ranges from 3 to 4 mol per cent, depending on the composition.

Portions of the powder x-ray diffraction patterns for synthetic forsterite and synthetic fayalite have been indexed. The cell constants, density, and molar volumes are given.

INTRODUCTION

The composition of members of the forsterite-fayalite series may be estimated by measuring the indices of refraction, $2V$, or density in lieu of a chemical analysis. The index of refraction and $2V$ determinative curves of Poldervaart (1950, p. 1073) or Winchell and Winchell (1951, p. 500) are usually used for this purpose. Some prefer to use the index of refraction determinative curve of Bowen and Schairer (1935, p. 197) based on six synthetic olivines, and still others use the $2V$ tables of Tomkeieff (1939, p. 235), based on Winchell's (1933, p. 191) earlier compilation. Bloss (1952, p. 974-975) gives a determinative curve based on density, using 30 measurements from the literature. It is the purpose of this paper to present a curve for estimating the composition of members of the forsterite-fayalite series using powder x-ray diffraction data.

METHOD OF INVESTIGATION

Certain parameters in the structure of olivine vary with composition. These variations may be studied by measuring in a powder x-ray diffraction pattern either the absolute position of reflections or the separation of two reflections from olivines of known composition. The absolute position of a reflection may be determined by measuring the angular separation between the reflection of the olivine and the reflection of an admixed substance whose parameters are known. A plot of either of these data against composition provides a possible means of estimating the composition of unknown olivines.

The measurement of the absolute position of a single reflection was chosen on the basis of the following requirements. (1) A reflection of

TABLE 1. POWDER X-RAY DIFFRACTION DATA FOR SYNTHETIC FORSTERITE (P-2)

$2\theta_{obs}$	$Q_{obs} \times 10^5$	$\Delta Q \times 10^5$	hkl	I	d
17.410	3,854	-6	020	26	5.094
20.605	5,382	1	110	3	4.310
22.915	6,640	6	021	95	3.881
23.900	7,214	5	101	39	3.723
25.475	8,180	1	111	13	3.496
25.620	8,272	-3	120	12	3.477
29.865 (α_1)	11,191	-3	002	41	2.989
32.365	13,070	9	130	51	2.766
35.775	15,875	2	131	>100	2.510
36.560 (α_1)	16,583	-8	112	>100	2.456
38.345 (α_1)	18,180	10	041	18	2.345
38.870 (α_1)	18,661	-15	210	8	2.315
39.755	19,453	8	122	50	2.267
40.095 (α_1)	19,808	5	140	48	2.247
41.825 (α_1)	21,475	-31	211	33	2.158
44.560 (α_1)	24,232	39	132	20	2.032
46.800 (α_1)	26,585	-1	042	8	1.940
48.535 (α_1)	28,471	0	150	10	1.874

$2\theta_{obs}$ in degrees: CuK α $\lambda=1.5418$

CuK α_1 $\lambda=1.54050$

d =interplanar spacing in Å

$Q=1/d^2$

$\Delta Q=Q_{calc}-Q_{obs}$

I =relative intensity based on arbitrary scale

high intensity throughout the compositional range was sought for two reasons: (a) the intensity diminishes for certain wave lengths of x -radiation (e.g., Cu) with increasing iron content; (b) the amount of olivine in an unknown sample may be small and the intensity will be proportionally reduced. For a high intensity reflection, therefore, olivines need not be carefully separated. In fact it has been found possible to obtain a suitable x -ray pattern from a thin slab or a thin section (with cover glass removed) of some olivine-bearing rocks. (2) The reflection must be resolved clearly from neighboring reflections throughout the range of composition and should be readily distinguishable from those of commonly associated minerals such as plagioclase and pyroxene. (3) The reflection should vary continuously throughout the composition range, preferably uniformly, at a rate suitable for a precise estimate of the composition.

The indices of the observed reflections in the low-angle region for a synthetic forsterite and a synthetic fayalite are given in Tables 1 and 2, respectively. The space group is $Pbnm$ (Bragg and Brown, 1926), and the cell dimensions obtained from the powder x -ray diffraction data in Tables 1 and 2 are:

	<i>Synthetic forsterite</i>	<i>Synthetic fayalite</i>
<i>a</i>	4.756 ± 0.005 Å	4.817 ± 0.005 Å
<i>b</i>	10.195 ± 0.005 Å	10.477 ± 0.005 Å
<i>c</i>	5.981 ± 0.010 Å	6.105 ± 0.010 Å

These values are in accord with those published by Rinne (1923, p. 236) and Winchell (1950, p. 14) for samples close to the end members. The density obtained from the cell volumes is 3.222 for forsterite and 4.392 for fayalite. Bloss (1952) gives 3.217 and 4.36 for pure natural forsterite and pure natural fayalite, respectively.

The above requirements appear to be satisfied for the most part by the (130) reflection. It may be noted that none of the adjoining pairs of intense reflections (e.g., 131 and 112) satisfies the conditions desired.

The measurement of the spacing of the (130) reflection was performed in the following way. The sample was ground in an agate mortar under acetone, and about 10 mg. of the olivine powder was mixed with 1–2 mg. of pure silicon powder on a glass slide. A few drops of a very weak solution of lacquer in acetone were added, and then the powder was stirred into a thin film on the slide. The slide was mounted on the Norelco Geiger-counter focusing diffractometer, and records were made on a scale of 1 inch per degree 2θ . The divergent and scatter slits were 1° , receiving slit 0.006 inch, and the scan speed was $\frac{1}{4}^\circ$ per minute. The positions of

TABLE 2. POWDER X-RAY DIFFRACTION DATA FOR SYNTHETIC FAYALITE

$2\theta_{obs}$	$Q_{obs} \times 10^5$	$\Delta Q \times 10^5$	<i>hkl</i>	<i>I</i>	<i>d</i>
16.920	3,642	2	020	16	5.240
20.245	5,197	24	110	8	4.386
22.365	6,328	-1	021	14	3.975
23.515	6,987	6	101	7	3.783
25.050	7,914	-10	111	75	3.555
29.260	10,735	-4	002	11	3.052
31.620	12,491	18	130	100	2.829
34.225	14,568	8	040	22	2.620
34.975	15,195	-3	131	60	2.565
35.915	15,995	-42	112	80	2.500
37.340	17,244	{ 15 -4	{ 041 200	35	2.408
38.300	18,108	43	210	18	2.350
39.080	18,824	62	140	35	2.305
41.205	20,837	-3	211	12	2.191
43.650	23,259	-18	132	6	2.074

$2\theta_{obs}$ in degrees CuK α $\lambda = 1.5418$

d = interplanar spacing in Å

$$Q = 1/d^2$$

$$\Delta Q = Q_{calc} - Q_{obs}$$

I = relative intensity based on arbitrary scale

the olivine (130) reflection and the silicon (111) reflection were then measured to $0.005^\circ 2\theta$ by a vernier rule. The following standard values of 2θ in degrees for the (111) reflection of silicon were used (Philips Laboratories):

	$K\alpha$	$K\alpha_1$
Cu	28.465	28.440
Co	33.175	33.150

The position of the olivine reflection was corrected by means of the silicon reflection and the absolute value obtained. The d_{130} values were calculated using 7-place sine tables (Peters, 1918) and the wave lengths for Cu and Co radiation given by Bragg (1947, p. 27).

Four to 12 records of natural and synthetic samples were made by Yoder, using Cu radiation in the region $33-28^\circ 2\theta$. Five or six records of 17 of the natural samples were made using identical apparatus with Co radiation in the region $38-33^\circ$ and measured independently by Sahama. These independent data permitted an estimate of operator error since the same sample of silicon powder was used and the same procedures were employed by both authors.

DESCRIPTION OF SAMPLES

Thirty-one analyzed natural and seven synthetic olivines were *x*-rayed with the Si internal standard. The locality and source of the natural samples are given in Table 3. Chemical analyses of the natural olivines are listed in order of increasing Fo (mol %) content in Table 4. The source and reference to the synthetic samples may be found in Table 5.

The Mg_2SiO_4 content, Fo, of the natural samples was calculated in the following way. The H_2O , F, and alkalis were neglected and the remaining oxides divided by their equivalent weights as given by Stevens (1946, p. 109). These equivalents are adjusted to equal the total of eight anion equivalents of the olivine structure. The resulting numbers are then divided by their respective valence to give the atoms per formula. The Fo content is obtained from the ratio Mg/X of atoms per formula X_2SiO_4 . In the past the composition of an olivine has been given on the basis of its iron content, Fa, or if the manganese content, expressed as tephroite, is known and appreciable the composition is recorded as Fo_x - Fa_y - Te_z . In view of the problems involving the oxidation of iron and manganese, it was considered more appropriate to give the composition in terms of the single-valued component, Fo.

The natural olivines are usually of relatively simple composition ($Fo + Fa > 95\%$) and are, therefore, amenable to the measurement of a single parameter as an estimate of their composition. However, Ca, Al, Fe^{+3} , and Mn may enter the olivines in measurable amounts. Although

TABLE 3. X-RAY MEASUREMENTS OF NATURAL OLIVINES

For- mol %	Original sample No.	Reference No.	Source	Locality	Occurrences	Measurements of 2θ(130)	Average in parentheses.	d ₁₃₀	nr. d ₁₃₀
						Calc'l (Index)	Calc'l (Strens)	Index	Strens
0	USMPO458	18	G. Switzer	Rockport, Mass.	perovskite in hornblende-biotite gneiss	31.695 31.610 31.690 31.690 31.595 31.595 31.595 (31.600)	36.800 36.840 36.890 36.895 36.855 36.890 (36.840)	2.8313	2.8907
2.6	EQ4139	10,34	I. D. Muir, L. R. Weger	Skarvegard Intrusion, East Greenland (2500 meters)	olivine-quartz gabbro of layered intrusion	31.615 31.620 31.620 31.690 31.695 31.625 31.610 31.695	36.870 36.880 36.880 36.875 36.885 36.870 (36.875)	2.8291	2.8286
5.5	F	24	Th. G. Schum	St. Ulvervik Hage, Tumsherg, Söderman- land, Sweden	enLysite	31.615 31.615 31.610 31.615 31.615 31.620 31.610 31.615 31.620	36.895 36.840 36.845 36.840 36.885 36.860 (36.850)	2.8300	2.8320
19.2	MS174	17	I. D. Muir	Seaver Bay, Minn.	iron-rich diabase of sill-like intrusion	31.740 31.750 31.745 31.740 31.745 31.750 31.740 31.750	—	2.8187	—
20.2	EQ4146	10,34	I. D. Muir, L. R. Weger	Skarvegard Intrusion, East Greenland (2100 meters)	olivine-quartz gabbro of layered intrusion	31.730 31.720 31.705 31.725 31.705 31.720 31.715 (31.715)	—	2.8213	—
26.3	—	N.P.*	I. D. Muir	Garth Island, Shiant Islands (350 feet above sea level)	olivine-tin holserite, part of sill	31.765 31.765 31.755 31.760 31.750 31.765 31.770	—	2.8174	—
32.3	USMOL913	18	G. Switzer	Mouros, Uganda	with magnetite and calcite	31.935 31.955 31.990 31.935 31.980 31.920 31.935 31.930 31.930 (31.930)	37.205 37.220 37.205 37.205 37.205 37.225 (37.210)	2.8028	2.8035
39.7	FEA821	N.P.	K. Höpff	Noroto, Uganda	olivine diabase	31.890 31.870 31.870 31.870 31.885	37.135 37.150 37.145 37.150 37.150 37.150 (37.150)	2.8075	2.8079
40.0	EQ4907	10,34	I. D. Muir, L. R. Weger	Skarvegard Intrusion, East Greenland (1800 meters)	olivine-quartz gabbro in layered intrusion	31.815 31.815 31.810 31.815 31.815 31.815 (31.815)	—	2.8126	—
44.6	—	30	I. D. Muir	Umas Mbr., Hutu	olivine gabbro	31.920 31.920 31.910 31.935 31.915 31.915 (31.920)	—	2.8036	—
55.9	E	24	Th. G. Schum	Sudakul, Vanuatu, Flakoo	magnetite-ilmenite olivine	32.010 32.005 32.010 32.015 32.005 32.005 (32.010)	37.310 37.310 37.335 37.315 37.315 37.315 (37.315)	2.7959	2.7959
55.6	D	24	Th. G. Schum	drainage channel of Lake Malilang, Mt. Makila, Palau	diabase	32.025 32.000 32.000 31.985 32.015 31.990 31.990 32.025	37.305 37.310 37.310 37.305 37.315 37.325 (37.310)	2.7964	2.7963
61.3	FEA852	N.P.	Th. G. Schum	between Mt. Bihavara and Mt. Bihavara, Q. 8000 Ft., Sumatra, Uganda	phonocrysts in kirtite	32.070 32.070 32.060 32.070 32.060	37.315 37.315 37.340 37.370 37.375 37.355 (37.360)	2.7913	2.7927
62.2	FEA856	N.P.	Th. G. Schum	Nyarusu, Bulumbira, Uganda	phonocrysts in diabase	32.040 32.040 32.035 32.030 32.045	37.385 37.385 37.385 37.390 37.400 37.370 (37.385)	2.7934	2.7908
63.1	EQ4077	10,34	I. D. Muir, L. R. Weger	Skarvegard Intrusion, East Greenland (500 meters)	olivine-biotite gabbro of layered intrusion	32.025 32.025 32.030 32.025 32.025 32.025 (32.025)	—	2.7951	—

TABLE 3. X-RAY MEASUREMENTS OF NATURAL OLIVINES—(Continued)

Co mol %	Original sample No.	Reference No.	Source	Locality	Occurrence	Measurements of 2θ(130)		Average in parentheses.		d _{hkl}	S _{hklm}	av. d _{hkl}
						Unit ¹ (Yoder)	Unit ² (Sahama)	Unit ¹ (Yoder)	Unit ² (Sahama)			
68.1	FEA574	N.P.	Th. G. Sahama	Googo Frontier on the east of Murchison, Uganda	phenocrysts in diabase	32.080 32.090 32.105 32.110	32.080 (32.095)	37.445 37.430 37.445 37.430	(37.430)	2.7687	2.7687	2.7682
73.9	—	15	S. R. Nockolds	Elasroogis, Farm Roadment District, Orange Province, South Africa	phenocrysts in millite basalt	32.155 32.145 32.150 32.120 32.160	32.145 (32.145)	—	—	2.7845	—	2.7845
76.4	II	N.P. (see 13)	R. Johnston	Gubb Eilias Sill, Shiant Islands (38 ft. above sea level)	pleochroite part of sill	32.170 32.185 32.180 32.215 32.180	32.185 (32.180)	—	—	2.7816	—	2.7816
78.0	I	N.P. (see 13)	R. Johnston	Gubb Eilias Sill, Shiant Islands (see level)	perlite, base of sill	32.185 32.205 32.210 32.210	32.205 (32.200)	—	—	2.7799	—	2.7799
80.6	FEA539	N.P.	K. Hytönen	Mankings, Karamoja, Uganda	phenocrysts in volcanic basaltic rock	32.200 32.210 32.210	32.210 (32.210)	37.555 37.545 37.545	(37.550)	2.7782	2.7791	2.7786
80.8	BEK932.9	28	M. H. Hay	Alite Springs, Australia	meteorite	32.270 32.260 32.290 32.285	32.270 (32.275)	37.630 37.625 37.630 37.620	(37.620)	2.7779	—	2.7799
85.6	—	15	S. R. Nockolds	Spiegel River, Ruvum- bais District, Orange Province, South Africa	phenocrysts in millite basalt	32.260 32.265 32.275 32.285	32.275 (32.285)	—	—	2.7731	—	2.7731
87.4	FEA556	N.P.	Th. G. Sahama	Moko Flow, Rubanda Area, Uganda	phenocrysts in ugandite	32.280 32.275 32.275	32.270 (32.270)	37.615 37.600 37.600	(37.605)	2.7740	2.7751	2.7746
87.8	C	24	Th. G. Sahama	Marjanihti, Finland	meteorite	32.270 32.270 32.270 32.285 32.270	32.280 (32.275)	37.635 37.635 37.635 37.630 37.630	(37.635)	2.7736	2.7737	2.7736
88.4	7	22	C. S. Ross	Ishinomaga, Akita Prefecture, Japan	nodule in basalt	32.290 32.275 32.275	32.280 (32.275)	37.645 37.640 37.640	(37.650)	2.7736	2.7720	2.7728
88.6	III	11	R. Johnston	Unakont Island, West Greenland	intrusive perlitic sheet	32.300 32.280 32.275	32.275 (32.290)	—	—	2.7723	—	2.7723
89.9	B	24	Th. G. Sahama	Ultschhal, Tyrol, Austria	dunite	32.275 32.285 32.280 32.310	32.285 (32.285)	37.635 37.630 37.630 37.615	(37.635)	2.7727	2.7732	2.7730
90.1	A	24	Th. G. Sahama	Dreis, Elfeld, Germany	volcanic bomb	32.295 32.280 32.300 32.295 32.280	32.295 (32.295)	37.645 37.640 37.640 37.640 37.640	(37.650)	2.7719	2.7720	2.7720
90.4	SJSM9394.8	22	C. S. Ross	Salt Lake Crater, Oahu, Hawaii	nodule in basalt	32.295 32.290 32.300 32.285	32.295 (32.290)	37.655 37.650 37.650 37.650	(37.655)	2.7722	2.7712	2.7718
93.1	14	22	C. S. Ross	Houmas, New Caledonia	serpentinized peridotite	32.310 32.280 32.295	32.310 (32.295)	37.645 37.650 37.655	(37.645)	2.7719	2.7718	2.7718
94.7	150	23	Th. G. Sahama	Ojama, Iohja, Finland	limestones, with clinohumite	32.330 32.320 32.325 32.325	32.325 (32.320)	37.710 37.690 37.720 37.700	(37.705)	2.7698	2.7680	2.7689

*N.P. = chemical analysis not published.

there appear to be narrow limits within which the first three atoms may substitute, Mn is known to form a complete series of solutions, fayalite-tephroite. For these reasons certain restrictions had to be placed on the composition of olivines used to construct the determinative curve. Only specimens whose analyses satisfied the following specifications of atoms per formula were considered suitable for a determinative curve:

Si: 0.97-1.03
 X: 1.93-2.04
 Mn: 0-0.03

TABLE 4. CHEMICAL ANALYSES OF NATURAL OLIVINES

Formula	Theoretical O.O	0.0	2.6	5.5 ^a	19.2	20.2 ^b	26.3 ^c	32.3	39.7	40.0	44.6
SiO ₂	29.48	30.08	30.15	29.96	30.42	31.85	31.56	33.77	34.08	33.72	34.04
TiO ₂		n.d.	0.20	0.00	1.20	0.01	0.41	n.d.	0.04	tr.	0.43
Al ₂ O ₃		n.d.	0.07	0.00	0.50	tr.	0.79	n.d.	0.00	nil	0.91
Fe ₂ O ₃		n.d.	0.43	0.00	nil	0.11	n.d.	n.d.	0.27	0.05	1.46
FeO	70.52	68.12	65.02	63.31	57.62	58.64	53.64	47.26	47.30	47.91	40.37
MnO		0.72	1.01	4.40	n.d.	0.85	0.56	4.54	0.65	0.41	0.68
MgO		n.d.	1.05	2.23	8.17	8.49	11.39	13.88	17.83	18.07	20.32
CaO		n.d.	2.18	0.10	1.32	0.18	0.85	n.d.	0.00	nil	0.81
H ₂ O ⁺		0.88	n.d.	0.00	0.18	n.d.	0.16	0.48	0.05	n.d.	0.09
H ₂ O ⁻	n.d.		0.00	0.21	n.d.	0.06	0.00		n.d.		
Total	100.00	99.80	100.11	100.00	99.62	100.13	99.42	99.93	100.22	100.16	99.11

Formula	53.9 ^d	55.6 ^e	61.3	62.2	63.1	68.1	73.9	76.4	78.0	80.6 ^f	80.8
SiO ₂	35.31	35.84	36.25	36.28	38.11	37.76	37.33	37.93	38.07	38.53	37.24
TiO ₂	0.00	0.00	0.00	0.00	tr.	0.00	0.09	tr.	0.07	0.04	nil
Al ₂ O ₃	0.00	0.00	0.14	0.10	nil	0.04	0.18	0.11	0.03	0.74	n.d.
Fe ₂ O ₃	1.70	1.99	0.64	0.00	0.15	0.40	1.60	0.02	0.01	0.67	n.d.
FeO	36.91	35.18	32.60	32.90	31.48	27.66	21.58	21.70	19.95	16.60	16.92
MnO	0.53	0.60	0.26	0.22	0.22	0.11	0.27	0.16	0.25	0.27	n.d.
MgO	25.55	26.39	30.04	30.75	30.50	34.05	38.13	40.40	41.20	43.15	43.88
CaO	0.00	0.00	0.12	0.05	0.02	0.16	0.38	0.17	0.27	0.00	1.26
H ₂ O ⁺	0.00	0.00	0.00	0.00	n.d.	0.00	0.17	n.d.	0.03	0.00	n.d.
H ₂ O ⁻	0.00	0.00	0.00	0.00	n.d.	0.00	0.04	n.d.		0.00	n.d.
Cr ₂ O ₃	0.00	0.00	n.d.	n.d.	n.d.	n.d.	n.d.	n.d.	n.d.	n.d.	n.d.
P ₂ O ₅	n.d.	n.d.	n.d.	n.d.	n.d.	n.d.	0.09	n.d.	n.d.	n.d.	n.d.
Na ₂ O	0.00	0.00	n.d.	n.d.	n.d.	n.d.	0.03	n.d.	n.d.	n.d.	n.d.
K ₂ O			n.d.	n.d.	n.d.	n.d.	0.05	n.d.	n.d.	n.d.	n.d.
Total	100.00	100.00	100.05	100.30	100.48	100.18	99.94	100.49	99.88	100.00	99.30

TABLE 4. CHEMICAL ANALYSES OF NATURAL OLIVINES—(Continued)

Fo mol %	85.6	87.4	87.8	88.4	88.6 ^e	89.9 ^h	90.1	90.4	91.1	94.7	Theoretical 100.0
SiO ₂	39.12	40.90	40.24	40.30	39.81	40.72	40.60	40.87	41.32	41.07	42.69
TiO ₂	0.09	0.00	0.00	0.15	tr.	0.12	0.00	0.02	0.01	0.05	
Al ₂ O ₃	0.58	0.25	0.01	0.25	nil	0.09	0.20	0.07	0.00	0.56	
Fe ₂ O ₃	1.69	0.66	0.68	0.00	nil	0.10	0.96	0.00	0.30	0.65	
FeO	10.76	10.73	10.92	10.26	10.20	9.48	8.35	8.72	7.49	3.78	
MnO	0.16	0.20	0.28	0.09	0.13	0.13	0.16	0.15	0.15	0.23	
MgO	46.51	46.96	48.08	48.60	49.03	49.52	49.60	49.78	49.56	54.06	57.31
CaO	0.48	0.14	0.00	0.07	0.75	0.00	0.00	0.07	0.29	0.00	
H ₂ O ⁺	0.21	0.06	0.00	0.33	n.d.	0.00	0.00	0.05	0.60	0.05	
H ₂ O ⁻	0.07	0.00	0.04		0.04	0.02	0.04			0.00	0.00
F	n.d.	n.d.	n.d.	n.d.	n.d.	n.d.	n.d.	n.d.	n.d.	0.00	
Cr ₂ O ₃	n.d.	n.d.	0.07	0.03	n.d.	0.03	0.03	0.02	0.04	n.d.	
F ₂ O ₅	0.07	n.d.	n.d.	n.d.	n.d.	n.d.	n.d.	n.d.	n.d.	n.d.	
Na ₂ O	0.15	n.d.	0.00	0.04	n.d.	0.00	0.00	0.01	0.01	n.d.	
K ₂ O	0.06	n.d.		0.03	n.d.			0.00	0.00	0.00	n.d.
NiO	n.d.	n.d.	n.d.	0.41	n.d.	n.d.	n.d.	0.34	0.31	n.d.	
CoO	n.d.	n.d.	n.d.	n.d.	n.d.	n.d.	n.d.	0.013	0.011	n.d.	
Total	99.95	99.90	100.32	100.56	99.96	100.21	99.94	100.11	100.09	100.45	100.0

a. Corrected for an estimated 1% magnetite.

b. Analyzed specimen was incorrectly referred to as EG4145 (Wager and Deer, 1939, p. 73). See Wager and Deer (1939, p. 71) and Deer and Wager (1939, p. 23).

c. Partial analysis.

d. Corrected for estimated 0.75% ilmenite and magnetite.

e. Corrected for estimated 2% analyzed titanomagnetite.

f. Corrected for 1.6% analyzed clinopyroxene.

g. Spectrographic determinations in p.p.m. given by S. R. Nockolds: Cr, 1000; V, 5; Ni, 1750; Co, 120.

h. Value for Al₂O₃ misprinted as 0.90.

The following specimens were rejected on the basis of their chemical analyses:

Mol % Fo	Locality	Basis for rejection
80.8	Alice Springs, Australia	low Si, high X
32.3	Monroe, Orange County, N. Y.	high Mn
5.5	St. Utterviks Hage, Tunaberg, Sweden	high Mn

The rejected specimens will be reconsidered in the light of their (130) spacing below.¹

¹ It would be desirable to construct a determinative grid for the series forsterite-fayalite-tephroite based on d_{130} and some other parameter (e.g., index of refraction, $2V_{\alpha}$, density); however, a sufficient number of suitable analyzed specimens were not available. It is noteworthy that the variation of d_{130} is unique relative to the nearly parallel variations of indices of refraction, $2V_{\alpha}$, and density.

TABLE 5. X-RAY MEASUREMENTS FOR SYNTHETIC OLIVINES

Name	No.	Reference	Source	Preparation	Measurements of $2\theta(130)$				d
Forsterite	T2-36C	5	O. F. Tuttle	hydrothermal	32.375	32.380	32.360	32.380	32.355
					32.345	32.370	32.370	32.380	(32.370)
Forsterite	P-2	38	H. S. Yoder	hydrothermal	32.365	32.350	32.350	32.360	32.355
Forsterite	—	—	J. F. Schairer	dry fusion	32.355	32.360	32.360	32.355	(32.355)
Fayalite	—	2	L. H. Adams	blast furnace	32.370	32.375	32.375	32.370	(32.370)
					32.375	32.365	32.375		
Fayalite	—	14	Th. G. Sahama	dry fusion	31.620	31.630	31.610	31.615	31.610
					31.625	31.625	31.610	31.635	(31.620)
Fayalite	FAS112-2	26	K. Yagi	dry fusion	31.620	31.625	31.630	31.625	31.625
					31.635	31.620	31.620	31.630	(31.625)
Tephroite	—	27	R. B. Snow	dry fusion	31.625	31.610	31.635	31.630	31.610
					31.625	31.615	31.615	31.610	(31.620)
Fayalite	—	14	Th. G. Sahama	dry fusion	31.165	31.170	31.150	31.160	31.165
					31.160	31.180	CoK α_1	36.850	(36.860)
					36.870	36.875	36.850	36.850	(36.860)
					36.860	36.860			

RESULTS FROM NATURAL SPECIMENS

The x -ray data for the natural samples are given in Table 3 and the average values (the mean of the average for those x -rayed by each writer) are plotted in Fig. 1.

Two points in the figure, in addition to two of those rejected on the basis of chemical analysis, are almost certainly subject to large error:

<i>Mol % Fo</i>	<i>Locality</i>
40.0	East Greenland 1907 (1800 meters)
63.1	East Greenland 4077 (500 meters)

The first of these has been reexamined optically by Dr. I. Muir and he gives $Fo=25-27$ on the basis of indices of refraction ($\gamma=1.829$) and $2V_a(60^\circ)$. The value obtained from the x -ray measurement is $Fo=30$. Since there appears to be agreement between the new optical and x -ray determinations, the chemical analysis is believed to be in error and is re-

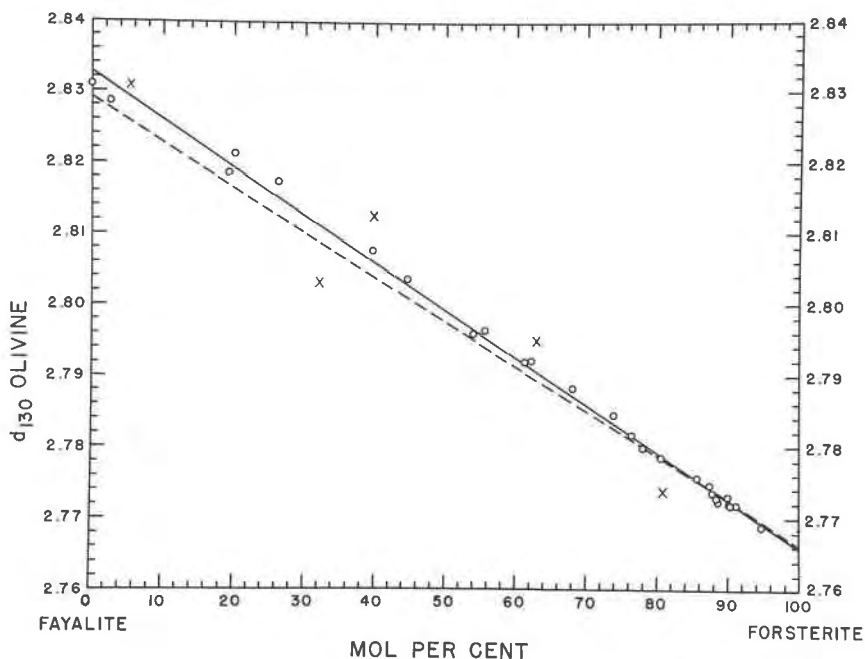


FIG. 1. Olivine x -ray determinative curve (solid line). Circles represent average d_{130} for analyzed specimens used in calculation of determinative curve. Crosses represent those points rejected for reasons given in text. Dashed line is assumed linear variation of d_{130} for synthetic olivines, using experimentally determined end points.

jected. There are no obvious reasons for rejecting the chemical analysis of the second specimen. The writers have taken the liberty of excluding this measurement from the calculation of the determinative curve for the sole reason that it appears to be anomalous.

Other problems arose in fitting a curve to the data on the natural specimens, and the writers are indebted to Dr. Felix Chayes for suggesting the following statistical analysis and making many of the computations.

The first problem to arise involved the use of the data obtained by each writer on the same specimen. It was necessary to learn whether either group of averaged measurements was biased before they could be combined. The spacing data for those compositions *x*-rayed by both writers were plotted against each other. If there were no bias the best fitting straight line would be characterized by a slope not differing significantly from unity and an intercept not significantly different from zero (see Youden, 1951, p. 40-49). The following equations were obtained using first the spacings of Yoder (d_y) and then those of Sahama (d_s) as the independent variable:

$$\begin{aligned}d_s &= 1.0105 d_y - 0.00117 \\d_y &= 0.9868 d_s + 0.00142.\end{aligned}$$

For the first equation the error of slope is 0.0140 and that of the intercept 0.00130. The errors for the constants of the second equation are 0.0136 and 0.00127, respectively. Departures of slopes and intercepts from the expected values are thus insignificant in relation to error, and it is permissible to use the mean of the average *d* value of each writer. In a broader sense, the small differences between the two equations also indicate that analogous measurements by other investigators may be compared with those presented here in estimating the composition of unanalyzed olivines.

Next, it was necessary to choose the independent variable, d_{130} or composition. The spacing was chosen as the independent variable for two reasons: (1) in the opinion of the writers the d_{130} is known better than the chemical composition, which is based on only a single analysis of each specimen, and (2) the spacing is to serve as the estimator of the chemical composition in the application of the determinative curve.

The equation of the determinative curve for the data assembled in the above-mentioned fashion is

$$Fo \text{ (mol \%)} = 4233.91 - 1494.59 d_{130}.$$

The residual variance amounts to 0.34%, and, as there seems to be no systematic distribution of deviations, higher order terms are not justified.

The fictive end points are d_{130} ($Fo=100$) = 2.7659 and d_{130} ($Fo=0$) = 2.8328.¹

The upper and lower 95 per cent confidence limits are as follows:

d	True value, mol % Fo	$\pm 95\%$ confidence limits
2.8328	0	1.65
2.8194	20	1.23
2.8061	40	0.88
2.7994	50	0.74
2.7927	60	0.69
2.7793	80	0.76
2.7659	100	1.08

The confidence limits plot as gentle curves, which are closest to the determinative curve at its mean and furthest from it at the limits of the range. The strict interpretation of the confidence limits presupposes that d is subject to negligibly small random errors. As seen in the data tables the estimate of d is subject to measurable error. The standard deviation is 0.00084 Å, and since the total range is only 0.0669 Å this amounts to ± 2.45 mol per cent Fo. If the errors involved in the estimate of d_{130} and the estimate of the true composition are added, the error attached to an individual estimate of composition, using the above determinative curve, is approximately ± 4 mol per cent near pure Fo or Fa and about ± 3 mol per cent in the vicinity of the mean, which lies near 64 mol per cent Fo.

RESULTS FROM SYNTHETIC SPECIMENS

The average d_{130} for the three synthetic forsterite specimens and three synthetic fayalite specimens is 2.7661 and 2.8293, respectively. On the assumption that the variation of d_{130} is linear throughout the composition range, the following determinative curve may be calculated:

$$Fo \text{ (mol \%)} = 4476.739 - 1582.278 d_{130}.$$

The validity of the assumption will be examined below. The curve is plotted as a dashed line in Fig. 1.²

The d_{130} for synthetic tephroite is 2.8697. The value is included for use in determining the correction for olivines high in Mn.

¹ In the Annual Report of the Director of the Geophysical Laboratory (Abelson, 1954, p. 120) the fictive end points of the preliminary curve based on fewer data were given as d_{130} ($Fo=100$) = 2.7660 and d_{130} ($Fo=0$) = 2.8326.

² The synthetic intermediate olivines prepared by Bowen and Schairer (1935, p. 195-197), on which the optical determinative curves are based, could not be located. Only the unanalyzed, partially oxidized starting materials prepared in the gas furnace were found, and these gave broad multiple reflections.

DISCUSSION OF RESULTS

Those samples rejected on the basis of their chemical analysis may now be reexamined in the light of their (130) spacings. The Alice Springs, Australia, specimen ($F_o = 80.8$) appears to have too small a spacing. The discrepancy cannot be attributed to the Ca or Mn (not determined) content since the correction would have the wrong sign. The analysis is still regarded as incorrect. The Monroe, Orange County, N. Y., specimen ($F_o = 32.3$) was considered to have too high an MnO content (4.54%); however, the correction for Mn would be in the wrong direction. The olivine occurs with magnetite, and it is possible that inclusions of that mineral could account for too high an FeO content (Fe_2O_3 was not determined). The St. Utterviks Hage, Tunaberg, Sweden, specimen ($F_o = 5.5$) was also believed to have too high an MnO content (4.40%) to be suitable for a determinative curve of the forsterite-fayalite series. When corrected for Mn, however, the spacing still gives a reasonable estimate of the F_o content.

The two additional specimens rejected, East Greenland 1907 ($F_o = 40.0$) and East Greenland 4077 ($F_o = 63.1$), have (130) spacings which indicate high Mn content. The chemical analyses do not support this suggestion.

The difference (0.0035 Å) between the d_{130} of synthetic fayalite and the fictive d_{130} for pure natural fayalite lies outside the precision of measurement and is of some concern. The fictive point represents a fayalite having 8.7 mol per cent tephroite or 6.0 weight per cent MnO, on the assumption that the (130) spacing of synthetic fayalite is correct. Since the chemical analyses of the natural samples were chosen on the basis of low MnO content, the source of the discrepancy must lie elsewhere. One possible, but improbable, explanation is that two forms of fayalite having slightly different properties exist (see Chudoba and Frechen, 1943). The most likely explanation is that the cell dimensions are a function of the temperature of formation. The synthetic fayalites were produced at temperatures over 1000° C. Olivines having a high iron content are usually associated with lower temperatures. It is to be noted that there is close agreement between the (130) spacing of synthetic forsterite and the fictive (130) spacing for a pure natural forsterite.

THEORETICAL RELATION OF d_{130} TO COMPOSITION

The practical problem of estimating the composition of most natural olivines by means of d_{130} appears to have been met. It is of interest to examine qualitatively why d_{130} varies linearly, within the limits of error, with composition.

The construction of a compositional determinative curve for solid solution series from powder x -ray diffraction data was suggested and applied to certain cubic systems by Vegard (1921) and further applied by Vegard and Dale (1928). Vegard's "law" stated that the cell dimension, a_0 , varied linearly with composition. Deviations from linearity were considered as a measure of the nonideality of the solid solution series. Grimm and Herzfeld (1923, p. 80) as well as Mehl and Mair (1928, footnote p. 65) and Zen (1956) pointed out that it is the atomic volume, a_0^3 which varies linearly in *ideal* substitutional type solid solutions. Further complications arose when the "law" was applied to systems of lower symmetry since two or more parameters had to be considered. For these reasons Vegard's "law" is now used only in special cases as an approximation.

The forsterite-fayalite series has been shown in part to be thermodynamically ideal within the error of measurement by Sahama and Torgeson (1949) on the basis of heats-of-solution data. In addition, the present writers find that the molar volumes of natural olivines calculated from the density data of Bloss (1952, p. 974-975) are essentially additive. (The molar volumes of synthetic forsterite and synthetic fayalite, 43.7 cc. and 46.4 cc., respectively, calculated from the unit cell data of Tables 1 and 2, differ by only a small amount.) These observations suggest that the variation of cell parameters should not deviate greatly from the ideal values.

There is, unfortunately, no unique way of predicting the changes of a specific cell spacing solely from knowledge of the additivity of molar volume. The cell volume, V , is related to the molar volume V_m by a constant:

$$V = \frac{nM}{N_0\delta} = kV_m,$$

where n = molecules per unit cell, N_0 = Avogadro's number, δ = density, M = molecular weight; and is related to the three parameters of the orthorhombic cell by

$$V = abc.$$

On the other hand, the spacing of any (hkl) is related to the orthorhombic cell parameters as follows:

$$d_{hkl} = \left(\frac{h^2}{a^2} + \frac{k^2}{b^2} + \frac{l^2}{c^2} \right)^{-1/2}.$$

The relation of d_{130} to the cell parameters would then be

$$d_{130} = \left(\frac{1}{a^2} + \frac{9}{b^2} \right)^{-1/2}.$$

If one notes that a/b is approximately the same for the olivine end members, then the change of d_{130} with composition is essentially a linear func-

tion of the parameters. It is presumed that the total change of each cell parameter is sufficiently small over the composition range so that their functions are closely approximated by straight lines. An examination of the Bunn chart (Bunn, 1946, p. 133) for indexing tetragonal powder patterns indicates that the variation of d_{hkl} is essentially linear for small changes in the axial ratio. On the basis of these qualitative arguments the linear relation of d_{130} vs. composition appears reasonable.

In conclusion, certain features of the x -ray method should be pointed out. The peak observed on an x -ray chart is a summation of the diffraction of many crystals. If these crystals are variable in composition, as a result of zoning, for example, then a broad peak or even a multiple peak obtains. The x -ray method, therefore, gives an average composition in the same way as a chemical analysis, but in addition indicates in a crude way the range. On the other hand, composition determined by optical methods represents that of a small number of crystals, and some discrepancies between the results of the various methods are to be expected. Although the variations in the three cell parameters of natural olivines may not be sufficiently unique, it should be possible to determine composition of crystals in the three-component system forsterite-fayalite-tephroite by means of powder x -ray diffraction patterns. It is more likely that a combination of methods, optical and x -ray, will provide a more practical estimate of composition of the complex olivines.

ACKNOWLEDGMENTS

The writers are greatly indebted to the analysts and contributors of specimens listed in Tables 3 and 5, particularly to those who kindly granted permission to publish chemical analyses as yet unrecorded. Dr. A. Juurinen made five chemical analyses ($F_o=39.7, 61.3, 62.2, 68.1, 87.4$) especially for this study; Dr. I. Muir analyzed $F_o=26.3$; Mr. R. J. Murray, $F_o=78.0$ and 76.4 ; and Mr. Aulis Heikkinen, $F_o=80.6$. The other analysts are recorded in the references cited in Table 3. The samples of the fayalite-tephroite series, not used in the present study, from Drs. W. T. Schaller and K. Omori and the late Mr. L. H. Bauer were appreciated. Dr. I. Muir contributed many new optical determinations which provided an independent control on the chemical analyses. Dr. Felix Chayes is heartily thanked for his detailed statistical analysis of the natural olivine data and his comments on the manuscript. Helpful criticism was also obtained from Drs. G. Kullerud, D. B. Stewart and J. R. Smith.

REFERENCES

1. ABELSON, P. H. (1954), Annual Report of the Director of the Geophysical Laboratory: *Carnegie Inst. of Wash. Year Book* No. 53, 95-145.

2. ADAMS, L. H. (1931), The compressibility of fayalite, and the velocity of elastic waves in peridotite with different iron-magnesium ratios: *Gerlands Beitr. Geophys.*, **31**, 315-321.
3. BLOSS, F. D. (1952), Relationship between density and composition in mol per cent for some solid solution series: *Am. Mineral.*, **37**, 966-981.
4. BOWEN, N. L., AND SCHAIRER, J. F. (1935), The system, MgO-FeO-SiO₂: *Am. Jour. Sci.*, **29**, 151-217.
5. ——— AND TUTTLE, O. F. (1949), The system MgO-SiO₂-H₂O: *Bull. Geol. Soc. Am.*, **60**, 439-460.
6. BRAGG, W. L. (1947), The conversion factor for kX units to Angstrom units: *Jour. Sci. Instr.*, **24**, 27.
7. ——— AND BROWN, G. B. (1926), Die Struktur des Olivins: *Zeit. Krist.*, **63**, 538-556.
8. BUNN, C. W. (1946), *Chemical Crystallography*: Oxford University Press, Oxford, 422 pp.
9. CHUDOBA, K. F., AND FRECHEN, J. (1943), Der Einfluss der Temperatur auf die Beziehung zwischen Optik und Chemismus der Olivine: *Neues Jahrb. Min., Monatshefte*, **A**, 91-106.
10. DEER, W. A., AND WAGER, L. R. (1939), Olivines from the Skaergaard intrusion, Kangerdlugssuak, East Greenland: *Am. Mineral.*, **24**, 18-25.
11. DREVER, H. I., AND JOHNSTON, R. (1956), Olivines of picritic sills: in press.
12. GRIMM, H. G., AND HERZFELD, K. F. (1923), Über Gitterenergie und Gitterabstand von Mischkristallen: *Zeit. Phys.*, **16**, 77-83.
13. JOHNSTON, R. (1953), The olivines of the Garbh Eilean Sill, Shiant Isles: *Geol. Mag.*, **90**, 161-171.
14. KELLEY, K. K. (1941), The specific heats at low temperatures of ferrous silicate, manganese silicate, and zirconium silicate: *Jour. Am. Chem. Soc.*, **63**, 2750.
15. MATHIAS, M. (1949), Two olivines from South African melilite-basalts: *Min. Mag.*, **28**, 486-491.
16. MEHL, R. F., AND MAIR, B. J. (1928), Chemical affinity in metallic alloys, especially solid solutions: A study in compressibility: *Jour. Am. Chem. Soc.*, **50**, 55-73.
17. MUIR, I. D. (1954), Crystallization of pyroxenes in an iron-rich diabase from Minnesota: *Min. Mag.*, **30**, 376-388.
18. PENFIELD, S. L., AND FORBES, E. H. (1896), Fayalite from Rockport, Mass., and on the optical properties of the chrysolite-fayalite group and of monticellite: *Am. Jour. Sci.*, **1**, 129-135.
19. PETERS, J. (1918), *Siebenstellige Werte der trigonometrischen Funktionen*: Verlag der Optischen Anstalt C. P. Goerz, Berlin.
20. POLDERVAART, A. (1950), Correlation of physical properties and chemical composition in the plagioclase, olivine, and orthopyroxene series: *Am. Mineral.*, **35**, 1067-1079.
21. RINNE, F. (1923), Bemerkungen und röntgenographische Erfahrungen über die Umgestaltung und den Zerfall von Kristallstrukturen: *Zeit. Krist.*, **59**, 230-248.
22. ROSS, C. S., FOSTER, M. D., AND MYERS, A. T. (1954), Origin of dunites and of olivine-rich inclusions in basaltic rocks: *Am. Mineral.*, **39**, 693-737.
23. SAHAMA, TH. G. (1953), Mineralogy of the humite group: *Ann. Acad. Sci. Fennicae*, Ser. A, III, No. **31**, 1-50.
24. ——— AND TORGESON, D. R. (1949a), Thermochemical study of the olivines and orthopyroxenes: *Bur. Mines Rept. Investigations* **4408**, 1-24.
25. ——— AND ——— (1949b), Some examples of the application of thermochemistry to petrology: *Jour. Geol.*, **57**, 255-262.
26. SCHAIRER, J. F., AND YAGI, K. (1952), The system FeO-Al₂O₃-SiO₂: *Am. Jour. Sci.*, Bowen Vol., 471-512.

27. SNOW, R. B. (1943), Equilibrium relationships on the liquidus surface in part of the $MnO-Al_2O_3-SiO_2$ system: *Jour. Am. Ceram. Soc.*, **26**, 11-20.
28. SPENCER, L. J., AND HEY, M. H. (1932), A new pallasite from Alice Springs, Central Australia: *Min. Mag.*, **23**, 38-42.
29. STEVENS, R. E. (1946), A system for calculating analyses of micas and related minerals to end members: *U. S. Geol. Survey Bull.* **950**, 101-119.
30. TILLEY, C. E. (1952), Some trends of basaltic magma in limestone syntaxis: *Am. Jour. Sci.*, Bowen Vol., 529-545.
31. TOMKEIEFF, S. I. (1939), Zoned olivines and their petrogenetic significance: *Min. Mag.*, **25**, 229-251.
32. VEGARD, L. (1921), Die Konstitution der Mischkristalle und die Raumfüllung der Atome: *Zeit. Phys.*, **5**, 17-26.
33. ——— AND DALE, H. (1928), Untersuchungen über Mischkristalle und Legierungen: *Zeit. Krist.*, **67**, 148-162.
34. WAGER, L. R., AND DEER, W. A. (1939), Geological investigations in East Greenland, Part III: *Meddelelser om Grønland*, **105**, 1-335.
35. WINCHELL, A. N. (1933), Elements of Optical Mineralogy: Part II, John Wiley & Sons, Inc., N. Y., 459 pp.
36. ——— AND WINCHELL, H. (1951), Elements of Optical Mineralogy: Part II, John Wiley & Sons, Inc., N. Y., 551 pp.
37. WINCHELL, H. (1950), Preliminary report on the lattice constants of olivines: *Amer. Crystallogr. Assoc., Abstr. Meeting*, April 10-12, 1950, p. 14 (see Structure Reports, 1950, **13**, 367-368).
38. YODER, H. S. (1952), The $MgO-Al_2O_3-SiO_2-H_2O$ system and the related metamorphic facies: *Am. Jour. Sci.*, Bowen Vol., 569-627.
39. YODEN, W. J. (1951), Statistical Methods for Chemists: John Wiley & Sons, Inc., N. Y.
40. ZEN, E. (1956), Validity of "Vegard's Law": *Am. Mineral.*, **41**, 523-524.

Manuscript received November 24, 1956.