

- NIKOLAIEV, A. V., AND CHELISHCHEVA, A. G. (1940), The 25° isotherm of the systems:  $\text{CaO} + \text{B}_2\text{O}_3 + \text{H}_2\text{O}$  and  $\text{MgO} + \text{B}_2\text{O}_3 + \text{H}_2\text{O}$ : *Compt. Rend. (Doklady) Acad. Sci. U.R.S.S.*, **28**, 127-130.
- SPIRYAGINA, A. I. (1949), Conditions of formation of kurnakovite: *Doklady Akad. Nauk S.S.S.R.*, **68**, 909-911.

THE AMERICAN MINERALOGIST, VOL. 45, MAY-JUNE, 1960

### JACOBSITE FROM THE NEGEV, ISRAEL

GERALD KATZ, *Israel Atomic Energy Commission, Rehovoth, Israel.*

The specimen of jacobsite investigated is the first reported occurrence from Israel and the middle east. The sample was not found in situ but obtained from a large boulder (approximately 1 cubic meter) which was mined from the vicinity of "manganese hill," 26 miles North of Eilat, in the Southern Negev (Sturm 1953 and Bentor 1956). All subsequent analyses were performed on a "fist-sized" sample removed from this boulder.

### PHYSICAL PROPERTIES AND COMPOSITION

In appearance, the specimen was predominantly of a deep black color, exhibiting a brownish-black streak test. It was very magnetic, being able to support a 3 inch alnico horse-shoe magnet with 1 cm<sup>2</sup> pole pieces. The hardness on the Mohs scale was just below 6 of feldspar. It was quite difficult to cut the specimen with a carborundum saw and sections were made using a diamond saw. No regular cleavage was observed and only an irregular fracture was obtainable.

Spectrochemical analysis indicated iron and manganese to be the major elements present plus small amounts of silicon, aluminium, barium and traces of other elements. Wet chemical analysis gave a content of:

29.0% manganese by weight

14.6% iron by weight

### POLISHED SURFACE STUDIES\*

The specimen is of complex mineralogy, very fine grained, considerably oxidized, and in general, a particularly difficult problem for mineralogical study. Fig. 1. is a photomicrograph made under low magnification. The very bright small particles (low left center) are hematite. The smooth fairly bright areas are jacobsite; the brightness varies as it is oxidized and hydrated to limonite, which most of the darker areas represent. In addition to jacobsite and hematite, several other phases are discernible. A

\* Study performed by Dr. C. Milton of the U. S. Geological Survey, Washington 25, D. C.

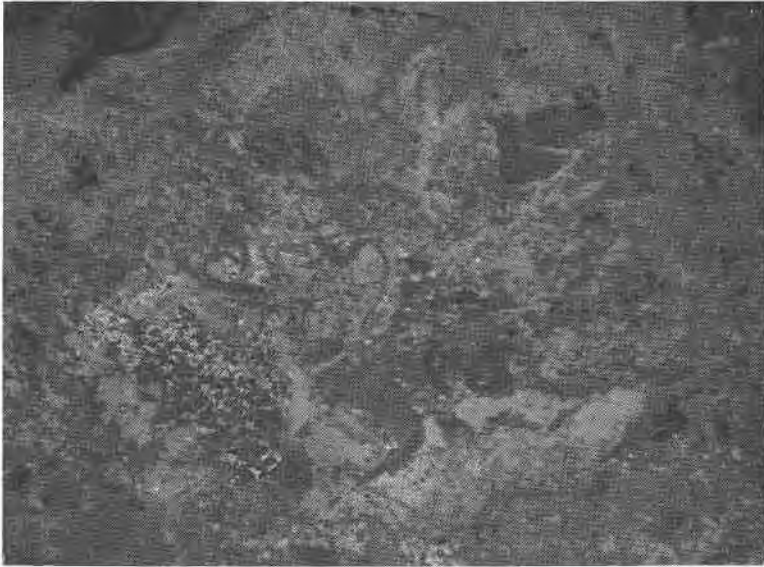


FIG. 1. Photomicrograph (ordinary light). The very bright small particles (lower left center) are hematite. The smooth fairly bright areas are jacobite; the brightness varies as it is oxidized and hydrated to limonite, which most of the darker areas represent.  $\times 45$

large part of the specimen appears to be hydrous iron oxide, goethite, as indicated by red internal reflections, low reflectivity and a considerable water content by closed tube test. There are veinlets cutting the specimen, apparently psilomelane or a similar manganese oxide.

#### X-RAY STUDY

When one considers the variety of oxidation states possible in iron and manganese ores, unambiguous identification of the phases present can best be accomplished by  $x$ -ray diffraction techniques. Debye-Scherrer photographs were taken from a region of the specimen which was found, by probing with a bar magnet, to be most magnetic. The polished surface study was made on a sample adjacent to this region. In Table 1 the powder diffraction data of the sample is presented with the identification of the various phases detected. There are two major phases present;  $\alpha$ - $\text{Fe}_2\text{O}_3$  and jacobite, a cubic phase which readily indexed as the spinel structure type. Trace amounts of goethite,  $\alpha$ - $\text{Fe}_2\text{O}_3 \cdot \text{H}_2\text{O}$  and a calcium manganese oxide hydrate (ASTM 4-0149) were found. After a magnetic separation of the powdered sample was made, the non-magnetic fraction indicated the possible presence of bementite,  $8\text{MnO} \cdot 7\text{SiO}_2 \cdot 5\text{H}_2\text{O}$ . The  $7.17 \text{ \AA}$  line has not been identified.

TABLE 1. X-RAY POWDER DATA FOR NEGEV ORE  
Fe/Mn filter, Fe K=1.9373; Camera diameter 114.59 mm.

$d_{\text{obs}}(\text{\AA})$	I	Spinel phase ( $hkl$ )	$a_0(\text{\AA})$	$d_{\text{obs}}(\text{\AA})$	I	$hkl$	$a_0(\text{\AA})$
* 7.17	M			(H) 1.631	M-	$\begin{Bmatrix} 333 \\ 511 \end{Bmatrix}$	8.475
4.85	W	111	8.402	(H) 1.606	M-		
(G) 4.25	VW			1.503	M+	440	8.502
(H) 3.625	M-			(H) 1.482	M		
2.982	M	220	8.433	(H) 1.450	M		
* 2.782	W			1.345	W+	620	8.507
(H, G) 2.672	S			* 1.322	W+		
2.547	M+	311	8.448	(H) 1.294	VW	533	8.485
(H) 2.504	M+			1.282	W	622	8.504
(G) 2.445	W+	222	8.469	(H) 1.257	W		
* 2.353	W			(H) 1.227	VW	444	8.501
(H) 2.195	M-			(H) 1.214	VW	$\begin{Bmatrix} 711 \\ 551 \end{Bmatrix}$	8.491
2.113	M-	400	8.452	(H) 1.189	W		
(H) 2.079	VW			(H) 1.160	W		
1.947	W+	331	8.487	(H) 1.140	W	642	8.531
* 1.899	VW			* 1.118	W		
(H) 1.833	M			1.107	VW	731	8.503
1.728	W	422	8.465	(H) 1.102	M		
(H) 1.687	M+			1.065	W (Br.)	800	8.520
* 1.667	W			(H) 1.055	W		

G=goethite.  
H=hematite.  
\* Unidentified.

The lattice constant of the spinel phase was determined by extrapolating the plot of the observed lattice constants for each ( $hkl$ ) reflection against the Nelson and Riley (1945) function

$$\frac{1}{2} \left( \frac{\cos^2 \theta}{\sin \theta} + \frac{\cos^2 \theta}{\theta} \right)$$

and found to be  $8.51 \pm 0.01 \text{\AA}$ .

#### DISCUSSION

At this point it is most appropriate to review the considerable discrepancies reported in the literature relative to the nomenclature, chemical composition, and lattice constants of the intermediate compounds belonging to the system whose end members are the cubic spinel, magnetite ( $\text{Fe}_3\text{O}_4$ ), and tetragonal hausmannite ( $\text{Mn}_3\text{O}_4$ ). Mason (1947) showed

that there was a complete range of solid solutions between  $\text{Fe}_3\text{O}_4$  and  $\text{Mn}_3\text{O}_4$  above  $1200^\circ\text{C}$ ; exhibiting a cubic structure at room temperature from 0 to 60 mol per cent  $\text{Mn}_3\text{O}_4$  and a tetragonal structure from 60–100 mol per cent  $\text{Mn}_3\text{O}_4$ . The unit cell dimension of the cubic phase increased with the mol per cent of  $\text{Mn}_3\text{O}_4$  and the  $c/a$  ratio of the tetragonal phase increased from 1.00 to 1.16 above 60 mol per cent  $\text{Mn}_3\text{O}_4$ . From the study of some mineral specimens belonging to the system  $\text{Fe}_3\text{O}_4$ – $\text{Mn}_3\text{O}_4$ , Mason found the evidence that compositions from approximately 54 to 91%  $\text{Mn}_3\text{O}_4$  will form two phases if allowed to reach equilibrium; one cubic and one tetragonal. This was demonstrated by the mineral vredenbergitte (an intergrowth of jacobsite and hausmannite). More recently Van Hook & Keith (1958) have verified Mason's findings and have investigated and characterized more completely the system  $\text{Fe}_3\text{O}_4$ – $\text{Mn}_3\text{O}_4$ . They have shown that below  $1160^\circ\text{C}$ . there is a "progressively widening region of solid immiscibility in which a cubic phase and a tetragonal phase can co-exist in equilibrium." Their data corroborates Mason's results on natural intergrowths in the region 54 to 91%  $\text{Mn}_3\text{O}_4$ . They have suggested that Mason's nomenclature and subdivisions in the system  $\text{Fe}_3\text{O}_4$ – $\text{Mn}_3\text{O}_4$  be continued:

<i>Mineral name</i>	<i>Mol per cent <math>\text{Mn}_3\text{O}_4</math></i>
magnetite	0– 10
jacobsite (magnetite-high hausmannite solid solution)	10– 54
vredenbergitte (intergrowths of jacobsite and low hausmannite)	54– 91
hausmannite (low)	91–100

The increase in lattice constant for the cubic spinel phase with increasing content of  $\text{Mn}_3\text{O}_4$  as reported by both Mason and Van Hook & Keith was found to follow an almost linear relationship. Although no single crystalline  $(\text{Fe},\text{Mn})_3\text{O}_4$  phase with from 54 to 91%  $\text{Mn}_3\text{O}_4$  is stable at room temperature, Van Hook & Keith obtained solid solutions in that compositional range only by quenching from higher temperature. Such cubic solid solutions are metastable at room temperature. This, of course, precludes their existence in minerals.

While it would be completely probable to find jacobsite with a lattice constant consistent with the appropriate amount of  $\text{Mn}_3\text{O}_4$  in the compositional range 10–54 mol %  $\text{Mn}_3\text{O}_4$  (Mason page 437), the synthetic manganese ferrite or  $.33 \text{Mn}_3\text{O}_4$ – $.66 \text{Fe}_3\text{O}_4$  would be expected to have one discrete unit cell dimension. This lattice constant would further depend on the ratio of  $\text{Mn}^{+2}$  and  $\text{Mn}^{+3}$  present and their relative occurrence on the A and B spinel sublattice sites. In Table 2 the reported lattice constants for jacobsite are compared with those of synthetic manganese ferrite. Among the synthetic manganese ferrites there is very good agree-

TABLE 2. REPORTED LATTICE CONSTANTS FOR JACOBSITE AND SYNTHETIC MANGANESE FERRITE

Specimen	Mn <sub>3</sub> O <sub>4</sub> content (mol per cent)	Lattice constant Å	Source	Reference
Jacobsite	? %	8.49	Jakobsberg, Sweden	Ramdohr (1956)
Jacobsite	33%	8.505	Weabonga, New South Wales	McAndrew (1952)
Jacobsite	19 to 54%	8.44 to 8.51	various	Mason (1947)
Jacobsite	54%	8.51	Negev, Israel	Katz (1959)
Manganese ferrite (MnFe <sub>2</sub> O <sub>4</sub> )	33%	8.515	synthetic	Economos (1955)
Manganese ferrite (MnFe <sub>2</sub> O <sub>4</sub> )	33%	8.507	synthetic	Gorter (1954)
Manganese ferrite (MnFe <sub>2</sub> O <sub>4</sub> )	33%	8.517	synthetic	Hastings & Corliss (1954)

ment. Hastings and Corliss (1954) made a neutron diffraction study of the distribution of the Mn<sup>+2</sup> and Mn<sup>+3</sup> cations amongst the A and B sublattice sites. They found no appreciable change in lattice constant or in Mn<sup>+2</sup> and Mn<sup>+3</sup> distribution in samples prepared either in air or nitrogen and subsequently either slow cooled or quenched. It is apparent that the lattice constant of synthetic manganese ferrite does not agree with the findings of Mason and Van Hook & Keith of about 8.46 Å for the .33 mol per cent Mn<sub>3</sub>O<sub>4</sub> composition. Mason *et al.*, however, only knew the Fe/Mn ratio of their samples and had no idea of the valence states and distribution of the manganese cations. Hence direct comparison of the two sets of data is not possible. In work with mineralogical specimens, the effect of impurity cations must be further considered. For these reasons the composition of the Negev specimen has been tentatively determined on the basis of Mason's *et al.* work as 54 mol per cent Mn<sub>3</sub>O<sub>4</sub> and 46 mol per cent Fe<sub>3</sub>O<sub>4</sub>.

#### ACKNOWLEDGMENTS

The author wishes to express his appreciation to Dr. C. Milton of the U. S. Geological Survey for his polished surface studies and to Dr. S. B. Levin of U. S. Army Signal Research and Development Laboratory for the benefit of his extensive research on manganese minerals. Mr. J. Mellichamp of the U. S. ASRDL performed the spectrochemical analysis. Discussions with Prof. Y. K. Bendor of the Israel Geological Survey have been most helpful.

## BIBLIOGRAPHY

- BARTH, T. F. W., AND POSNJAK, E. (1932), Spinel structures with and without variate atom equipoints, *Z. Krist.* **82**, 325-341.
- BRAGG, W. H. (1915) *Nature* **95**, 561.
- BENTOR, Y. K. (1956). The Manganese Occurrences at Timma (Southern Israel), a lagoonal deposit, *XX Congreso Geológico Internacional, Mexico*, 159-172.
- ECONOMOS, G. (1955) Magnetic Ceramics: II, Properties of magnetite and manganese ferrite fired in various atmosphere, *J. Am. Ceram. Soc.* **38**, 239 ff.
- GORTER, E. W. (1954) Saturation magnetization and crystal chemistry of ferrimagnetic oxides, *Philips Res. Rep.* **9**, 295-320.
- HASTINGS, J. M., AND CORLISS, L. M. (1956) Neutron diffraction study of manganese ferrite, *Phys. Rev.* **104**, 328.
- MASON, B. (1947) Mineralogical aspects of the system  $\text{Fe}_3\text{O}_4\text{-Mn}_3\text{O}_4\text{-ZnMn}_2\text{O}_4\text{-ZnFe}_2\text{O}_4$ , *Am. Mineral.* **32**, 426-441.
- MCANDREW, J. (1952) The cell-edge of jacobite, *Am. Mineral.* **37**, 453-460.
- NÉEL, L. (1948) *Ann. Phys., Paris* **3**, 137-198.
- NELSON, J. B., AND RILEY, D. P. (1945) An experimental investigation of extrapolation methods in the derivation of accurate unit cell dimensions of crystals, *Proc. Phys. Soc., Lond.*, **57**, 160-177.
- NISHIKAWA, S. (1915) *Proc. Tokyo Math-Phys. Soc.* **8**, 199-209.
- RAMDOHR, P. (1956) Die Manganerze, *XX Congreso Geológico Internacional, Mexico*, 19-73.
- STURM, E. (1953) Possible origins of manganese ore in the Negev, *Bull. Res. Council Israel* **III**, 177-192.
- VAN HOOK, H. J., AND KEITH, M. L. (1958) The system  $\text{Fe}_3\text{O}_4\text{-Mn}_3\text{O}_4$ , *Am. Mineral.* **43**, 69-83.
- VERWEY, E. J. W., AND HEILMANN, E. L. (1947) Physical properties and cation arrangements of oxides with spinel structure, *J. Chem. Phys.* **15**, 174-187.

THE AMERICAN MINERALOGIST, VOL. 45, MAY-JUNE, 1960

FULLER'S EARTH AS AN AGENT FOR PURIFYING  
HEAVY ORGANIC LIQUIDS\*

WALLACE R. GRIFFITTS AND A. P. MARRANZINO, *U. S.  
Geological Survey, Denver, Colorado.*

For several years we have been investigating trace amounts of metals in various rocks and minerals. Bromoform, diiodomethane (methylene iodide), and acetylene tetrabromide were used to separate igneous rocks into their constituent minerals. Because, in some cases, we were determining low level metal content (1 or 2 ppm.) in mineral separates it became important to know if the liquids could pick up enough metal to contaminate the minerals, and, if so, how the metal might be removed. The concern deepened when our colleague A. P. Pierce told us that bromoform picked up important amounts of uranium, and J. C. Antweiler noted that

\* Publication authorized by the Director, U. S. Geological Survey.