


AN EXPERIMENTAL STUDY ON THE LEUCITE- PSEUDOLEUCITE PROBLEM¹

YÔTARÔ SEKI² AND GEORGE C. KENNEDY, *Institute of Geophysics and
Planetary Physics, University of California, Los Angeles, California.*

ABSTRACT

Experimental works on leucite using a piston-anvil device shows the following chemical reaction is favored by increasing pressure and/or decreasing temperature:



The genesis of pseudoleucite is discussed and it is concluded that the breakdown of leucite into a mixture of sanidine and hexagonal kalsilite-nepheline solid solution caused by falling temperature under a substantial partial pressure of water is one of the most important mechanisms by which pseudoleucite is formed in some igneous rocks.

INTRODUCTION

The formation of pseudoleucite, a mixture of potash-feldspar and nepheline-kalsilite solid solution, in potash-rich igneous rocks has been studied for the last half century by many authors. The explanations proposed by these authors can be divided into three groups:

(1) Unmixing breakdown of leucite into potash-feldspar and nepheline-kalsilite solid solution (Knight, 1906; Scharizer, 1928; Larsen and Buie, 1938; Larsen *et al.*, 1939, 1941; Yagi, 1954).

(2) Chemical reaction between leucite crystals and magmatic or hydrothermal residual solutions (Bowen and Ellestad, 1937; Schairer and Bowen, 1955; Zies and Chayes, 1960).

(3) Decomposition of leucite into potash-feldspar and nepheline-kalsilite solid solution (Larsen *et al.*, 1938, 1939, 1941; Tilley, 1957; Fudali, 1957, 1963).

There is much petrographic evidence to indicate that pseudoleucite was usually formed after the magma reached its present position, after intrusion or extrusion, but before complete cooling of the rock. Hence the process of formation of pseudoleucite must have occurred within a cooling magma.

Though many geological, petrographical and mineralogical descriptions have been published, and many diverse opinions about the genesis of pseudoleucite have been presented, no experimental study over a wide range of temperature and pressure conditions has been published. In this paper we present the results of our experimental study on the stability of leucite over a temperature range of 200–850° C. and pressures up to 40 kilobars.

¹ Publication #303 Institute of Geophysics and Planetary Physics, University of California, Los Angeles, California.

² Department of Earth Sciences, Saitama University, Irawa, Japan.

EXPERIMENTAL METHODS AND STARTING MATERIALS

Our experiments were performed using the "simple squeezer" piston-anvil device, which has been already described by Griggs and Kennedy (1956 and Pistorius *et al.* (1962). Samples to be subjected to high pressure in the "simple squeezer" were placed in platinum foils in the form of a wet powder. Water, acting as a flux, accelerates the reaction rate even though it does not participate in the reaction. In all runs, pressure was first raised to the desired value and then temperature was raised. The duration of our runs in the "simple squeezer" was 2 hours for temperatures above 500° C., 4 hours at 400–500° C. and 12–24 hours below 400° C.

Our starting material was a natural leucite obtained from the mineral collection of the Geology Department of the University of California, Los Angeles. Na_2O content of this leucite was less than 0.5%, *i.e.*, it has almost pure KAlSi_2O_5 composition. X-ray powder data, unit-cell dimensions, and unit-cell volume of the leucite are shown in Table 1. These data also indicate that the leucite has almost pure leucite end member composition (Bannister, 1931; Prider and Cole, 1942).

Identification of materials formed in the experimental works was by x-ray diffractometer and the polarizing microscope. Quartz powder was used as an internal standard in detailed x-ray study.

RESULTS

Results obtained from our experimental work are summarized in Fig. 1. Leucite has been broken down into an assemblage of sanidine and hexagonal kalsilite under relatively high pressures. The assemblage of sanidine and hexagonal kalsilite formed from leucite in the "simple squeezer" was also reacted and transformed into leucite at decreased pressure and/or with increasing temperature. Thus the boundary between the field of leucite and that of sanidine+hexagonal kalsilite presented in Fig. 1 is believed to be an equilibrium boundary.

Neither the breakdown of leucite into sanidine+hexagonal kalsilite nor the chemical reaction of sanidine and hexagonal kalsilite to form leucite occurred with dry starting materials even with experiments of 2 to 5 days duration and high temperatures and pressures. This suggests that water plays a very important role in accelerating the breakdown or the chemical reaction.

X-ray powder patterns, unit-cell dimensions and unit-cell volumes of sanidine and hexagonal kalsilite formed as breakdown products of leucite are shown in Tables 2 and 3. Judging from these data, the sanidine and kalsilite are almost pure KAlSi_3O_8 and KAlSiO_4 respectively, and are very low in soda (Sahama *et al.*, 1956; Smith and Sahama 1954; Smith and

TABLE 1. X-RAY POWDER DATA AND UNIT-CELL DIMENSIONS OF LEUCITE USED AS A STARTING MATERIAL

hkl	Measured		Calculated	hkl	Measured		Calculated
	d(Å)	I	d(Å)		d(Å)	I	d(Å)
112	5.52	20	5.51	233}	2.842	40	2.844
121}	5.38	40	5.38	323}	2.814	27	2.814
211}				332			
022}	4.74	12	4.75	224	2.765	3	2.765
202}				422}			
013}	4.32	8	4.32	242}	2.687	5	2.687
103}				015}			
				105}			
213}	3.605	17	3.605	134}	2.644	12	2.644
123}				314}			
312}	3.539	17	3.540	143}	2.608	4	2.608
132}				413}			
004	3.440	100	3.439	215}	2.490	4	2.489
040}	3.266	100	3.266	125}	2.391	3	2.391
400}				251}			
033}	3.160	5	3.158	521}	2.368	32	2.368
303}				044}			
411}	3.091	8	3.089	404}	2.326	3	2.326
141}				305}			
204}	3.046	9	3.046	035}	2.309	4	2.310
024}				440			
402}	2.954	5	2.953	053}	2.271	4	2.271
042}				503}			
240}	2.923	41	2.924	343}			
420}				433}			

$a = 13.07$ (0) Å

$c = 13.74$ (4) Å

Tetragonal

Unit-cell volume = 146.7 Å^3

$\text{Na}_2\text{O} < 0.5\%$ (wt)

TABLE 1—(continued)

hkl	Measured		Calculated d(Å)	hkl	Measured		Calculated d(Å)						
	d(Å)	I			d(Å)	I							
442 } 325 } 235 }	2.191	2	2.191	217 } 127 }	1.862	5	1.862						
026 } 206 }				2.162				5	2.162	336	1.839	4	1.839
253 } 523 }										2.144			
523 } 352 }	2.130	5	2.132	037 } 307 }	1.791	3	1.791						
620 } 260 }				2.067				4	2.067		552 } 172 } 712 }	1.785	4
514 } 154 }	2.055	4	2.055		271 } 721 }	1.780	4			1.781			
136 } 316 }					2.005						2		
107 } 017 }	1.943	3	1.942	372 } 732 }		1.665	18	1.665					
444				1.916					4	1.917		651 } 561 } 028 } 208 }	1.662
046 } 406 }	1.875	4	1.876		446	1.654	6	1.645					

Tuttle, 1957), further proof of the low soda content of the starting leucite.

As shown in Fig. 1, leucite and the mixture of sanidine and hexagonal kalsilite made from leucite were transformed into the assemblage of hexagonal kalsilite and a new phase of the chemical composition of $\text{KAlSi}_3\text{O}_8 \cdot \text{H}_2\text{O}$ under very high water pressures.

The *x*-ray and other physical properties of the new phase, $\text{KAlSi}_3\text{O}_8 \cdot \text{H}_2\text{O}$, made from KAlSi_3O_8 glass + H_2O in the "simple squeezer", and the data for the hexagonal kalsilite in the breakdown products of leucite are shown in Table 4. The stability relations between the new phase and sanidine have been described in detail in another paper (Seki and Kennedy, 1964).

An assemblage of hexagonal kalsilite and $\text{KAlSi}_3\text{O}_8 \cdot \text{H}_2\text{O}$ formed from leucite was also easily and completely transformed into a mixture of hexagonal kalsilite and sanidine at water pressures lower than the upper pressure limit of sanidine. Thus, we believe that the boundary between the sanidine+hexagonal kalsilite field and $\text{KAlSi}_3\text{O}_8 \cdot \text{H}_2\text{O}$ +hexagonal kalsilite

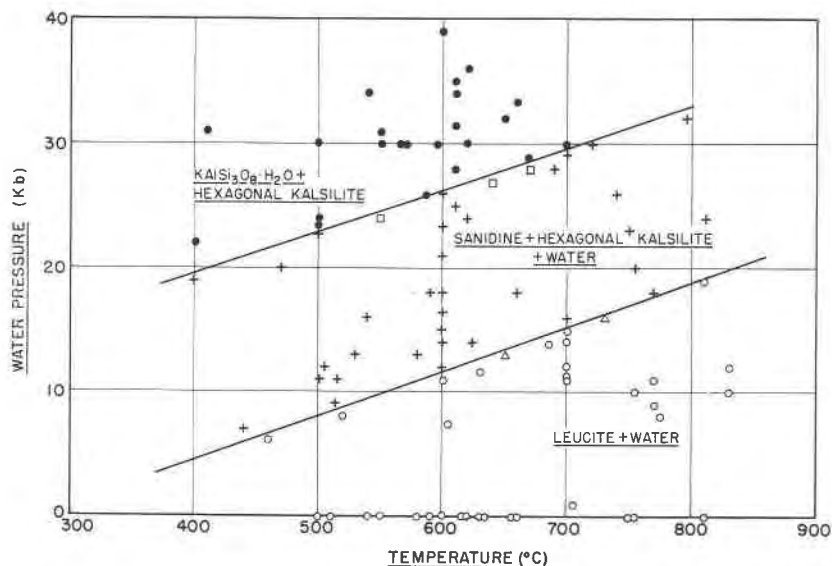


FIG. 1. Diagram showing the stability fields of leucite, sanidine+hexagonal kalsilite, and $\text{KAlSi}_3\text{O}_8 \cdot \text{H}_2\text{O}$ +hexagonal kalsilite determined by means of the simple squeezer under wet condition.

- leucite+water→leucite+water
- △ sanidine+hexagonal kalsilite+water→leucite+water
- + leucite+water→sanidine+hexagonal kalsilite+water
- $\text{KAlSi}_3\text{O}_8 \cdot \text{H}_2\text{O}$ +hexagonal kalsilite→sanidine+hexagonal kalsilite+water
- leucite+water→ $\text{KAlSi}_3\text{O}_8 \cdot \text{H}_2\text{O}$ +hexagonal kalsilite

ite field in Fig. 1 is an equilibrium boundary for the chemical reaction $\text{sanidine} + \text{H}_2\text{O} \rightleftharpoons \text{KAlSi}_3\text{O}_8 \cdot \text{H}_2\text{O}$.

Schairer and Bowen (1955) found in their experimental study of the system $\text{K}_2\text{O}-\text{Al}_2\text{O}_3-\text{SiO}_2$ that sanidine and hexagonal kalsilite are incompatible at high temperature (700–1700° C.) and atmospheric pressure. It is clear from this study, however, that these phases can coexist at high pressure.

DISCUSSION

Knight (1906) reported that leucite can have a moderate content of Na replacing K. The formation of pseudoleucite has often been thought as

TABLE 2. X-RAY POWDER DATA, UNIT-CELL DIMENSIONS
AND UNIT-CELL VOLUME OF SANIDINES

hkl	Sanidine synthesized from KAlSi ₃ O ₈ glass (20 kb, 600° C.) (this paper)			Sanidine formed by breakdown of leucite (L.97, 29 kb, 700° C.) (this paper)	
	Measured		Calculated	d(Å)	I
	e(Å)	I	d(Å)		
110 } 110 }	6.68	7	6.68	6.63	9
020	6.51	4	6.50	6.51	9
111	5.87	6	5.87	5.87	9
201	4.25	48	4.25	4.23	63
111	3.94	8	3.95	3.94	11
200 } 200 }	3.88	3	3.89	—	—
130 } 130 }	3.782	80	3.782	3.784	82
131	3.620	8	3.619	3.620	21
221	3.552	6	3.554	3.551	18
112	3.458	71	3.460	3.461	60
220 } 220 }	3.339	100	3.339	3.337	100
202	3.293	88	3.293	3.289	89
040	3.249	70	3.249	3.250	71
002	3.228	85	3.228	3.228	91
131	2.993	65	2.995	2.995	60
222	2.934	7	2.937	—	—
041	2.902	34	2.902	2.904	40
022	2.891	15	2.891	Kalsilite (003) ¹	
132	2.765	13	2.764	2.766	25
312	2.608	8	2.606	2.606	24
241	2.588	32	2.586	2.589	60
112	2.555	10	2.554	—	—
310 } 310 }	2.548	13	2.545	—	—

¹ Ill-defined peaks by association with kalsilite.

TABLE 2—(continued)

hkl	Sanidine synthesized from KAlSi ₃ O ₈ glass (20 kb, 600° C.) (this paper)			Sanidine formed by breakdown of leucite (L.97, 29 kb, 700° C.) (this paper)	
	Measured		Calculated	d(Å)	I
	d(Å)	I	d(Å)		
150 } 150 }	2.465	4	2.465	Kalsilite (111) ¹	
151	2.418	6	2.418	Kalsilite (103, 013) ¹	
242	2.316	8	2.314	2.315	12
042	2.290	8	2.290	2.290	10
332	2.276	15	2.276	2.275	16
223 } 132 }	2.231	14	2.231 22.33	2.231	12
151	2.204	4	2.204	2.204	12
060 } 313 }	2.167	27	2.166 2.165	Kalsilite (201) ¹	
311	2.083	6	2.082	2.079	10
133	2.071	6	2.070	2.069	6
222	1.975	25	1.978	1.976	20
261 } 351 }	1.930	13	1.931	1.929	13
243	1.917	6	1.917	1.918	14
113	1.855	6	1.855	1.853	10
350	1.835	6	1.836	—	—
043	1.794	24	1.794	1.796	30
153	1.747	6	1.746	1.746	7
334	1.632	11	1.631	—	—
	<i>a</i> = 8.66 (2) Å <i>b</i> = 13.00 (0) Å <i>c</i> = 7.18 (3) Å = 116° <i>C</i> 2/ <i>m</i> unit-cell volume = 181.7 Å ³			<i>a</i> = 8.66 (2) Å <i>b</i> = 13.01 (0) Å <i>c</i> = 7.18 (3) Å = 116° <i>C</i> 2/ <i>m</i> unit-cell volume = 181.8 Å ³	

TABLE 3. X-RAY POWDER DATA, UNIT-CELL DIMENSIONS AND UNIT-CELL VOLUME, OF HEXAGONAL KALSILITES

hkl	Hexagonal kalsilite formed by breakdown of leucite (29 kb, 700°) (this paper)			Synthesized kalsilite Ne:Ks=0:100 (Smith & Tuttle, 1957)	
	Measured		Calculated	d(Å)	I
	d(Å)	I	d(Å)		
002	4.34	25	4.34	4.3512	12
011} 101}	3.97	48	3.97	3.9733	45
102} 012}	3.117	100	3.116	3.1184	100
003	2.899	18	2.899	—	—
110	2.579	38	2.580	2.5789	50
111	2.473	21	2.473	2.4724	15
103} 013}	2.431	15	2.432	2.4319	10
020} 200}	2.236	12	2.236	2.236	3
112	2.218	10	2.218	2.2183	10
004	2.176	21	2.176	2.1753	17
201} 021}	2.166	20	2.166	2.164	5
202} 022}	2.988	11	1.989	1.9868	5
104} 014}	1.955	12	1.956	1.9546	3
113	1.929	8	1.929	1.9270	4
023} 203}	1.772	9	1.771	1.7703	3
114	1.662	5	1.662	1.6621	4
211} 121}	1.659	11	1.659	1.6580	4

TABLE 3—(continued)

hkl	Hexagonal kalsilite formed by breakdown of leucite (29 kb, 700°) (this paper)			Synthesized kalsilite Ne:Ks=0:100 (Smith & Tuttle, 1957)	
	Measured		Calculated	d(Å)	I
	d(Å)	I	d(Å)		
015 } 105 }	1.622	6	1.624	1.6220	6
212	1.567	15	1.567	1.5742	9
204	1.558	8	1.558	1.5588	3
300 } 030 }	1.490	17	1.492	1.4895	10
	$a = 5.16 (4) \text{ \AA}$ $c = 8.70 (5) \text{ \AA}$ Hexagonal Unit-cell volume = 100.5 \AA^3 $2\theta\text{CuK}\alpha (102) - 2\theta\text{CuK}\alpha (101) = 6.25^\circ$			$a = 5.159 (7) \text{ \AA}$ $c = 8.703 (2) \text{ \AA}$ } $\pm 0.002 \text{ \AA}$ Hexagonal Unit-cell volume = 100.3 \AA^3 $2\theta\text{CuK}\alpha (102) - 2\theta\text{CuK}\alpha$ $(101) = 6.26^\circ$	

due to unmixing of a "soda-leucite" (Larsen and Buie, 1938; Larsen *et al.*, 1939). However, Bowen and Ellestad (1937) suggested that leucite can contain no more than 1–1.5% by weight Na_2O . The average Na:K ratios for leucite from Africa (Sahama, 1952) and for leucite from Vesuvius (Tschirwinsky, 1931) are 8.5:91.5 and 15.4:84.6 respectively. Thus, leucite is believed to be generally very poor in soda.

The pseudoleucite is also believed to be derived from unmixing breakdown of a potash-analcite into potash-feldspar and nepheline (Fudali, 1957, 1963) Larsen and Buie, 1938; Larsen *et al.*, 1939, 1941; Tilley, 1957). Larsen and Buie (1938) have given the chemical analysis of a potash-rich analcite ($\text{Na}_2\text{O} = 8.48\%$, $\text{K}_2\text{O} = 4.48\%$ wt) which formed a primary phenocryst in basaltic rock of the Highwood Mountains in Montana. Barrer (1950) concluded from his experimental work that synthesized analcite may readily exchange Na for K in KCl-bearing aqueous solution. However, potash-rich analcite is very rare, and most natural analcites are very rich in soda and have only minor amounts of K_2O .

The hypothesis of chemical reaction between leucite crystals and magmatic or hydrothermal residual solutions which was originally presented

by Bowen and Ellestad (1937) has recently been supported with excellent evidence by Zies and Chayes (1960). Pseudoleucite chiefly composed of potash-feldspar and nepheline with minor kalsilite in solid solution may be fully explained by the reaction theory.

The results of our experimental work as described above, on the other

TABLE 4. X-RAY POWDER PATTERN, UNIT-CELL DIMENSIONS, UNIT-CELL VOLUME, DENSITY AND REFRACTIVE INDEX OF $\text{KAlSi}_3\text{O}_8 \cdot \text{H}_2\text{O}$ FORMED BY THE BREAKDOWN OF LEUCITE

hkl	d(Å)	I	hkl	d(Å)	I		
001	7.67	4	004	Kalsilite (113) ¹			
010}	4.61	28	113	1.847	10		
100}				120}	1.746	2	
101}	Kalsilite (011) ¹	100	210}				
011}				023}	1.714	4	
002}				203}			
102}	2.956		211}	1.700	4		
012}			121}				
110	2.665	74					
111	2.514	7	122}	1.591	15		
			212}				
200}	2.307	15	114	Kalsilite (212) ¹			
020}							
103	Kalsilite (020) ¹		005}	1.540	12		
			300}				
			030}				
201}	Kalsilite (112) ¹						
021}							

Hexagonal

$$a = 5.33 \text{ \AA}$$

$$c = 7.70 \text{ \AA}$$

$$\text{unit-cell volume} = 189 \text{ \AA}^3$$

$$\text{calculated density} = 2.60$$

$$n = 1.54$$

¹ Ill-defined peaks by association with kalsilite.

hand, are believed to show that the unmixing of leucite during the cooling stage of a magma may be also a very important process in the formation of pseudoleucite. From our data it is clear that pure leucite must be broken down into a mixture of sanidine and hexagonal kalsilite with increasing pressure and/or decreasing temperature by the following chemical reaction:

	2 leucite 2KAlSi ₂ O ₆	→	sanidine KAlSi ₃ O ₈	+	hexagonal kalsilite KAlSi ₃ O ₈
molecular volume	146.7 Å ³		181.8 Å ³		100.5 Å ³
total volume	293.4 Å ³		282.3 Å ³		

From the solid volume relations shown above (see also Table 5) increasing pressure will strongly favor the breakdown of leucite.

Figure 1 also shows that this chemical reaction will be favored by falling temperatures.

Yagi (1954) stressed the fact that pseudoleucite of the Tzu Chin Shan district of China is low in soda and high in potash and is chiefly composed of sanidine and kalsilite (potash-rich nepheline). He presents such excel-

TABLE 5. PHYSICAL PROPERTIES OF LEUCITE, SANIDINE, HEXAGONAL KALSILITE AND KAlSi₃O₈·H₂O

	Leucite	Sanidine	Hexagonal Kalsilite	KAlSi ₃ O ₈ ·H ₂ O
Density	2.47	2.57	2.59	2.60
Refractive index	5.508-1.509	1.520-1.53	1.537-1.542	1.54
Hardness	5.5-6	6	6	n.d.
Packing index	4.7	4.9-5.0	4.93	5.24

lent evidence that it is preferable to infer that the pseudoleucite was formed by unmixing of leucite rather than by reaction of the original leucite with a sodic residual magma.

It is certainly true that most pseudoleucite-bearing rocks have been hydrothermally altered. For example olivine crystals in pseudoleucite-bearing lavas were almost completely altered to chlorite or other ferromagnesian hydrous minerals (Balsillie, 1936; Prider and Cole, 1942; Wade and Prider, 1940). On the other hand, when the leucite-bearing rocks are fresh, no transformation of leucite into potash-feldspar-bearing mineral assemblages can be found (Davis and Fisset, 1947; Holmes, 1945; Sahama, 1952).

We have noted in our work that leucite never alters into another phase or phases under dry conditions even in the long, high temperature and high pressure experimental runs. Barrer and Hinds (1950) and Barrer, Hinds and White (1953) reported that synthesized pure leucite in the aqueous solution of K₂CO₃ and Na₂CO₃ was broken into a mixture containing orthoclase after 6 hours at 195-200° C. in an autoclave. They also succeeded in converting pure leucite into kalsilite by keeping the leucite

saturated with 3N-KOH solution at 250–350° C. for 2 or 3 days in the autoclave.

Thus, it is quite possible that the presence of water, aqueous solution or vapor is necessary for the formation of pseudoleucite.

Throughout this paper we have treated our experimental results as though total pressure and partial pressure of water were the same. This assumption is of no importance in locating the boundary between the leucite—sanidine plus kalsilite field, but it is of importance in locating the boundary between the fields of sanidine and $KAlSi_3O_8 \cdot H_2O$. Here the partial pressure of water is certainly not the total pressure on the system as undoubtedly large and nonstoichiometric amounts of potash, alumina and silica are dissolved in the water, thus changing the chemical potential and partial pressure of the water. We show the boundary, thus, for our experimental conditions with relatively “small” amounts of fluid at high pressures.

ACKNOWLEDGEMENTS

We would like to express our sincere thanks to Dr. K. Yagi of Hokkaido University for giving us helpful information about pseudoleucite he has studied. We are also indebted to Mrs. E. Szentvari for her chemical analysis of soda content of leucite.

Partial financial support was provided by our contract for Mineral Synthesis, Office of Naval Research, Nonr 233(28).

REFERENCES

- BALSILLIE, D. (1936) Leucite-basanite from east Lothian. *Geol. Mag.* **73**, 16–19.
- BANNISTER, F. A. (1931) The distinction of analcime from leucite in rocks by x-ray methods. *Mineral Mag.* **22**, 469–476.
- AND M. H. HEY (1942) Kalsilite, a polymorph of $KAlSiO_4$ from Uganda. *Mineral. Mag.* **26**, 218–224.
- AND Th. G. SAHAMA (1953) Kalsilite in venanzite from San Venanzo, Umbria, Italy. *Mineral. Mag.* **30**, 46–48.
- BARRER, R. M. (1950) Ion-exchange and Ion-sieve processes in crystalline zeolite. *Jour. Chem. Soc. London*, 2342–2350.
- BARRER, R. M. AND L. HINDS (1950) Hydrothermal synthesis of potash feldspar in the range 195–200° C. *Nature*, **166**, 562.
- L. HINDS AND E. A. D. WHITE (1953) The hydrothermal chemistry of silicates, III, Reactions of analcite and leucite. *Jour. Chem. Soc. London*, 1466–1475.
- AND J. W. BAYNHAM (1956) The hydrothermal chemistry of the silicates, VII, synthetic potassium aluminosilicates. *Jour. Chem. Soc. London*, 2882–2891.
- BOWEN, N. L. AND R. B. ELLESTAD (1937) Leucite and pseudoleucite. *Am. Mineral.* **22**, 409–415.
- COMBE, A. D. AND A. HOLMES (1945) The kalsilite-bearing lavas of Kabirenge and Lyak-auli, south-west Uganda. *Trans. Roy. Soc. Edinburgh*, **61**, 359–379.

- DAVIS, K. A. AND C. B. FISSET (1947) The geology and mineral resources of Uganda. *Bull. Imp. Inst. London*, **45**, 161–180.
- FUDALI, R. F. (1957) On the origin of pseudoleucite. *Trans. Am. Geophys. Un.* **38**, 391.
- (1963) Experimental studies bearing on the origin of pseudoleucite and associated problems of alkali rock systems. *Bull. Geol. Soc. Am.* **74**, 1101–1126.
- GRIGGS, D. T. AND G. C. KENNEDY, (1956) A simple apparatus for high pressures and temperatures. *Am. Jour. Sci.* **254**, 722–735.
- HOLMES, A. (1942) A suite of volcanic rocks from south-west Uganda containing kalsilite (a polymorph of $KAlSiO_4$). *Mineral Mag.* **26**, 197–217.
- (1945) Leucitized granite xenoliths from the potash-rich lavas of Bunyaraguri, south-west Uganda. *Am. Jour. Sci.* **243A**, 313–332.
- HURLBUT, C. S. JR. AND D. T. GRIGGS (1939) Igneous rocks of the Highwood Mountains, Montana. *Bull. Geol. Soc. Am.* **50**, 1043–1112.
- JAY, A. H. AND K. W. ANDREWS (1947) X-ray reflections of kalsilite ($K_2O \cdot Al_2O_3 \cdot 2SiO_2$). *Mineral. Mag.* **28**, 88–89.
- KNIGHT, C. W. (1906) A new occurrence of pseudoleucite. *Am. Jour. Sci.* **21**, 286–295.
- LARSEN, E. S. AND B. F. BUIE Potash analcime and pseudoleucite from the Highwood Mountains of Montana. *Am. Mineral.* **23**, 837–849.
- (1939) C. S. HURLBUT, JR., C. H. BURGESS AND B. F. BUIE (1941) Igneous rocks of the Highwood Mountains, Montana. *Bull. Geol. Soc. Am.* **52**, 1733–1868.
- PISTORIUS, C. W. F. T., G. C. KENNEDY AND S. SOURIRAJAN (1962) Some relations between the phase anorthite, zoisite and lawsonite at high temperatures and pressures. *Am. Jour. Sci.* **260**, 44–56.
- PRIDER, R. T. AND W. F. COLE (1942) The alteration products of olivine and leucite in the leucite-lamproites from the west Kimberley area, western Australia. *Am. Mineral.* **27**, 373–384.
- RIGBY, G. R. AND H. M. RICHARDSON (1947) The occurrence of artificial kalsilite, and allied potassium aluminium silicates in blast-furnace linings. *Mineral. Mag.* **28**, 75–89.
- SAHAMA, TH. G. (1952) Leucite, potash nepheline, and clinopyroxene from volcanic lavas from southwestern Uganda and adjoining Belgian Congo. *Am. Jour. Sci., Bowen Vol.*, 457–470.
- K. J. NEUVONEN AND K. HYTONEN (1956) Determination of the composition of kalsilite by an x-ray method. *Mineral Mag.* **31**, 200–208.
- SCHAIRER, J. F. AND N. L. BOWEN (1955) The system $K_2O-Al_2O_3-SiO_2$. *Am. Jour. Sci.* **253**, 681–746.
- SCHARIZER, R. (1928) Stochiometrische Betrachtungen. *Neues Jahrb. Mineral. Abt. A*, **57**, 57–62.
- SEKI, Y. AND G. C. KENNEDY (1964) The breakdown of potash feldspar at high temperature and high pressure (in press).
- SMITH, J. V. AND TH. G. SAHAMA (1954) Determination of the composition of natural nephelines by an x-ray method. *Mineral. Mag.* **30**, 439–449.
- AND O. F. TUTTLE, (1957) The nepheline-kalsilite system: I. X-ray data for the crystalline phases. *Am. Jour. Sci.* **255**, 282–305.
- TILLEY, C. E. (1957) Problems of alkali rock genesis. *Quart. Jour. Geol. Soc. London*, **113**, 323–360.
- TSCHIRWINSKY, P. (1931) Durchschnittliche chemische Zusammensetzung der wichtigen Mineralien der Eruptivgesteine und der Meteorite. *Neues Jahrb. Mineral. Ref.* **II**, 160–170.
- WADE, A. AND R. T. PRIDER (1940) The leucite-bearing rocks of the west Kimberley area, western Australia. *Quart. Jour. Geol. Soc. London*, **96**, 39–98.

- WYART, J. (1937) Sur un cas de polymorphisme par passage progressif d'un arrangement cristallin a un autre plus symetrique, observe sur la leucite. *Compt. Rend. Acad. Sci. Paris*, **205**, 1077-1079.
- (1938) Étude sur la leucite. *Bull. Soc. Franc. Min.* **61**, 228-238.
- (1941) Structure atomique de la leucite. *Compt. Rend. Acad. Sci. Paris*, **212**, 356-358.
- AND M. MICHEL-LEVY (1949), Cristallisation du melange $\text{Na}_x\text{K}_{1-x}\text{AlSiO}_4$ en présence d'eau sous pression (formation de nepheline, kalsilite, hydrocancrinite, kydro-sodalite, mica). *Compt. Rend. Acad. Sci. Paris*, **229**, 131-133.
- YAGI, K. (1954) Pseudoleucite from Tzu Chin Shansi, North China. *Jap. Jour. Geol. Geog.* **24**, 93-100.
- ZIES, E. G. AND F. CHAYES (1960) Pseudoleucite in a tinguaite from the Bearpaw Mountains, Montana. *Jour. Petrol.* **1**, 86-98.

Manuscript received, January 23, 1964; accepted for publication, April 13, 1964.