

The structure of margarosanite is probably very similar to that of synthetic  $\text{Ca}_2\text{BaSi}_3\text{O}_9$ . This in turn is closely related to other substances containing  $\text{X}_3\text{O}_9$  rings: compare the cell dimensions given.

These data show the existence of a series of metasilicates of large divalent cations containing  $\text{X}_3\text{O}_9$  rings. These structures can also exhibit cation ordering; thus the Ca/Ba ratio is known to be fixed in  $\text{Ca}_2\text{BaSi}_3\text{O}_9$ , and it does not form solid solutions with either  $\alpha\text{-CaSiO}_3$  or  $\text{BaSiO}_3$ . Water is not an essential constituent of  $\text{Ca}_2\text{BaSi}_3\text{O}_9$  as crystals are readily grown from melts at  $\sim 1320^\circ\text{C}$ .

The authors hope that other less well characterized metasilicates of large cations will be studied to enable an extension of this classification.

## REFERENCES

- ARMSTRONG, R. L. (1963) *Am. Mineral* **48**, 698.  
 GLASSER, F. P. AND L. S. DENT GLASSER (1961) *Zeit. Krist.* **116**, 263.  
 HILMER, W. (1958) *Naturwiss.* **45**, 238.  
 JEFFERY, J. W. AND L. HELLER (1953) *Acta Cryst.* **3**, 210.  
 ROBBINS, C. R. (1960) *Jour. Am. Ceram. Soc.* **43**, 610.  
 ZACHARIASEN, W. H. (1930) *Zeit. Krist.* **74**, 139.

THE AMERICAN MINERALOGIST, VOL. 49, MAY-JUNE, 1964

THE THORITE→HUTTONITE PHASE TRANSFORMATION AS DETERMINED  
 BY GROWTH OF SYNTHETIC THORITE AND  
 HUTTONITE SINGLE CRYSTALS

C. B. FINCH, L. A. HARRIS AND G. W. CLARK, *Metals and Ceramics  
 Division, Oak Ridge National Laboratory, Oak Ridge, Tennessee.*

The phase transformation, tetragonal  $\text{ThSiO}_4$  (thorite)→monoclinic  $\text{ThSiO}_4$  (huttonite) is contrary to expectation, in that it involves formation of the denser modification at a higher temperature. The transformation and/or synthesis of either phase have been investigated by Pabst (1951, 1952), Frondel and Collette (1957), Fuchs (1958), Harris (1959) and Mumpton and Roy (1961), none of whom restricted the equilibrium transformation to a narrow temperature interval. Pabst, studying impure natural thorite, suggested that the transformation occurred over the temperature range  $700\text{--}1200^\circ\text{C}$ . Harris, using solid state methods, was able to synthesize only huttonite at temperatures  $\geq 1250^\circ\text{C}$ . Mumpton and Roy indicated the possibility that huttonite is stable at all temperatures, with thorite a metastable phase.

The present authors investigated the transformation using solution growth of the preferred modification of  $\text{ThSiO}_4$  single crystals as a criterion for phase stability at a given temperature. Experiments designed

to grow  $\text{ThSiO}_4$  from alkali ditungstate or dimolybdate solutions revealed that only thorite could be grown below  $1225 \pm 10^\circ \text{C}$ ., whereas above this temperature only huttonite could be grown. These data suggest that the equilibrium transformation temperature (1 atm) is  $1225^\circ \pm 10^\circ \text{C}$ .

The growth experiments were performed in air atmosphere in covered platinum containers, as described in Fig. 1. Absolute temperatures as well as thermal gradients were determined by use of the Pt-Pt<sub>90</sub>Rh<sub>10</sub>

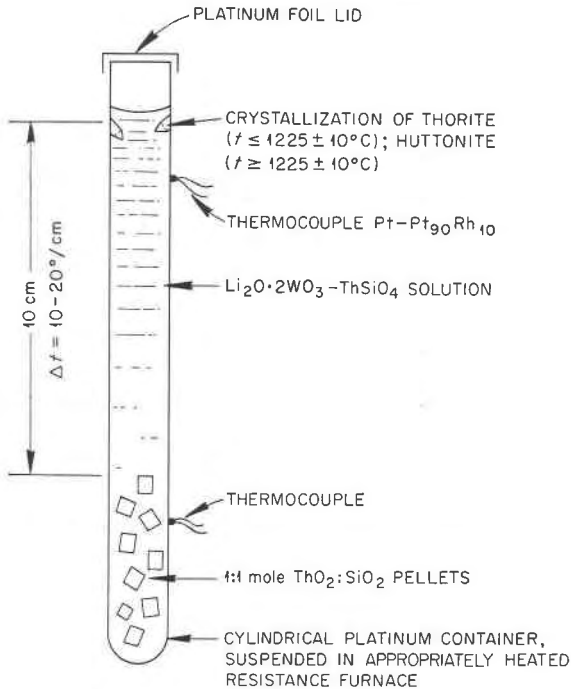


FIG. 1. Method for growth of thorite and huttonite crystals.

thermocouples shown in Fig. 1. For a given temperature use of  $\text{Li}_2\text{O} \cdot 2\text{WO}_3$ ,  $\text{Li}_2\text{O} \cdot 2\text{MoO}_3$ , or  $\text{Na}_2\text{O} \cdot 2\text{WO}_3$  as solvents for  $\text{ThSiO}_4$  (solubility of  $\text{ThSiO}_4$  in each of these solvents increases with temperature) resulted in formation of crystals of identical crystallographic modification and crystal habit. Nutrient material, in the hottest region of the container (bottom), was in the form of 1:1 mole  $\text{ThO}_2 : \text{SiO}_2$  pellets, pressed from 99.9%  $\text{SiO}_2$  and 99.9%  $\text{ThO}_2 < 200$  mesh powders. Supersaturation required to induce nucleation and growth of either modification was obtained using thermal gradients  $10-20^\circ/\text{cm}$ . Under these conditions nucleation occurred within 24 hrs at  $1200 \pm 100^\circ \text{C}$ . in the coolest regions

of the solution, usually at solution-platinum interfaces. After runs of three days to one week in duration, the solution was decanted off the crystals at as near as possible their formation temperature. The crystals, adhering to the upper container wall, were readily removed at room temperature.

The synthetic thorite crystals (Fig. 2a), identified by *x*-ray methods, have a growth habit typical of zircon with well-developed prism  $\{110\}$  and dipyramid  $\{111\}$  forms. The largest crystals attained dimensions 5 mm (parallel to  $\langle c \rangle$ )  $\times 2 \times 2$  mm. Good quality crystals are transparent and colorless with indices of refraction,  $\omega = 1.827 \pm 0.003$ ,  $\epsilon = 1.885 \pm 0.003$ . A spectrographic analysis of optically clear crystals revealed

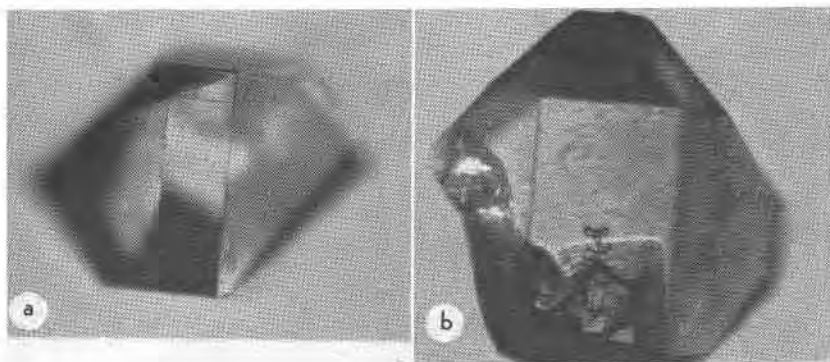


FIG. 2a. Synthetic thorite single crystal grown from  $\text{Li}_2\text{O} \cdot 2\text{WO}_3$  solvent at  $1150 \pm 10^\circ \text{C} \times 35$ .

FIG. 2b. Synthetic huttonite single crystal grown from  $\text{Li}_2\text{O} \cdot \text{WO}_3$  solvent at  $1250 \pm 10^\circ \text{C} \times 35$ .

$< 0.1$  wt % W as the only detectable impurity. Their density determined by pycnometer is  $6.63 \pm 0.10$  g/cm<sup>3</sup>, comparing to a density of  $6.67$  g/cm<sup>3</sup>, computed from *x*-ray data.

The growth habit of synthetic huttonite (Fig. 2b) resembles monazite with  $\{100\}$  faces well developed. The largest crystals were  $2 \times 2 \times 2$  mm. Spectrographic analysis of the best crystals revealed approximately 0.1 wt % W (or Mo) as the only detectable impurity. Their pycnometer density is  $7.20 \pm 0.10$  g/cm<sup>3</sup>, comparing with an *x*-ray density of  $7.18$  g/cm<sup>3</sup>. The crystals are colorless and transparent with indices of refraction  $\alpha = 1.900 \pm 0.003$ ,  $\gamma = 1.930 \pm 0.005$ . They displayed no sign of inverting to thorite when air-quenched from  $1225$  to  $25^\circ \text{C}$ .

The general approach of growing single crystals from various solvents at different temperatures as criterion for phase stability may be applica-

ble to the study of other sluggish phase transformations when it is important to know the true equilibrium crystal structure for a given temperature. The principal limitation is availability of solvents which do not contaminate the crystallizing phase under study.

## REFERENCES

- FRONDEL, C. AND R. L. COLLETTE (1957) *Am. Mineral.* **42**, 759-765.  
FUCHS, L. H. (1958) *Am. Mineral.* **43**, 367-368.  
HARRIS, L. A. (1959) *Jour. Am. Ceram. Soc.* **42**, 74-77.  
MUMPTON, F. A. AND R. ROY (1961) *Geochim. Cosmochim. Acta.* **21**, 217-238.  
PABST, A. (1951) *Am. Mineral.* **36**, 60-65.  
——— (1952) *Am. Mineral.* **37**, 137-157.

THE AMERICAN MINERALOGIST, VOL 49, MAY-JUNE, 1964

## A DISTINCTION BETWEEN NATURAL AND SYNTHETIC EMERALDS

ICHIRO SUNAGAWA, *Geological Survey of Japan, Hisamoto-cho 135, Kawasaki, Japan.*

## INTRODUCTION

When crystals are grown under different physico-chemical conditions, their crystal faces exhibit different growth patterns. Growth patterns on crystal faces vary so sensitively according to the differences in growth conditions that one can easily notice the difference in localities if he observes surface structures of crystal faces under a reflection microscope. The writer previously reported in this journal that hematite crystals from different localities exhibit different characteristics of surface structures, from which he deduced the differences in supersaturation conditions of hematite formation between each locality (Sunagawa, 1962). Tolansky and Sunagawa (1959, p. 60) also observed distinct differences of surface structures of crystal faces between natural and synthetic diamonds and discussed the differences of mechanism and conditions of crystal growth between the two diamonds.

A result of comparative studies on the surface structures of crystal faces of natural and synthetic emeralds will be reported in this paper. The present observations using a reflection and phase contrast microscope have shown that a clear distinction can be made between natural and synthetic emeralds. These observations have also given information concerning the differences in conditions of crystal growth between the two emeralds, which will also be discussed in this paper.

A hexagonal prismatic crystal of Chatham's synthetic emerald was