

NEW DATA ON KENTROLITE AND MELANOTEKITE:
TERNARY PHASE RELATIONS IN THE SYSTEM
 $\text{PbO}\cdot\text{Fe}_2\text{O}_3\cdot\text{SiO}_2$

F. P. GLASSER, *Department of Chemistry, University of Aberdeen,
Old Aberdeen, Scotland.*

ABSTRACT

A phase identical with melanotekite is readily prepared by heating the composition $2\text{PbO}\cdot\text{Fe}_2\text{O}_3\cdot 2\text{SiO}_2$ in an air atmosphere at $650^\circ\text{--}700^\circ\text{C}$. Results of heating experiments and crystallographic examination of naturally occurring melanotekite confirm this formula. Melanotekite is orthorhombic, space group P^{***} , $a=6.97$, $b=11.0$, $c=9.83$ Å. Kentrolite, $2\text{PbO}\cdot\text{Mn}_2\text{O}_3\cdot 2\text{SiO}_2$, is isostructural with melanotekite; $a=7.00$, $b=11.0$, $c=9.97$ Å. $Z=4$.

Laboratory studies to determine the subsolidus compatibility triangles show that at 650°C , melanotekite can coexist with the following minerals: alamosite (PbSiO_3), quartz, hematite, magnetoplumbite ($\text{PbO}\cdot 6\text{Fe}_2\text{O}_3$), and plumboferrite ($\text{PbO}\cdot 2\text{Fe}_2\text{O}_3$). In addition a new ternary phase, probably $12\text{PbO}\cdot\text{Fe}_2\text{O}_3\cdot 2\text{SiO}_2$, has been encountered.

INTRODUCTION

Analyses of kentrolite by Damour and Von Rath (1880) and of melanotekite by Lindstrom (1880) indicated the approximate chemical composition $2\text{PbO}\cdot\text{R}_2\text{O}_3\cdot 2\text{SiO}_2$ ($\text{R}=\text{Mn}, \text{Fe}$). Goniometric data indicated that kentrolite and melanotekite were members of an isomorphous series. At that time it was not certain that the manganese and iron were present in the tripositive oxidation state. Warren (1898) established that iron and manganese were tripositive. However, his analyses of single crystals of melanotekite indicated a molar ratio $(\text{Fe}_4^{3+}\text{O}_3)_3 \text{Pb}_3(\text{SiO}_4)_3$ or $3\text{PbO}\cdot 2\text{Fe}_2\text{O}_3\cdot 3\text{SiO}_2$. Gabrielson (1962) was apparently unaware of Warren's study and therefore used the Flink formula, $\text{Pb}_2(\text{R}^{3+})_2 \text{Si}_2\text{O}_9$; $\text{R}=\text{Mn}, \text{Fe}$. The density and unit-cell volume indicated that the unit cell contained four formula units. Gabrielson also determined the crystal structure of kentrolite ($\text{R}=\text{Mn}^{3+}$).

STUDIES OF NATURAL KENTROLITE AND MELANOTEKITE

Samples of kentrolite and melanotekite were obtained from the United States National Museum and were designated as follows: C3224, melanotekite, Långban, Sweden; R3889 kentrolite, Långban,* Sweden; C3223, kentrolite, Långban. The latter specimen contained kentrolite crystals in a matrix of other phases and a handpicked kentrolite concentrate was prepared from this specimen. The bulk densities of the massive specimens C3224, and R3889 were 6.040 and 5.961 ± 0.005 g/cc., respectively. The density of the kentrolite concentrated as determined from 3.5 gm.

* Designated Långbanshyttan in the U.S.N.M. collection; the longer name is not used in Sweden.

was 6.2 ± 0.1 g/cc. Densities were determined with a Beckman air comparison pycnometer.

† Typical X-ray powder patterns of kentrolite and melanotekite are shown in Table 1. Single crystals of kentrolite were readily extracted from C3223. X-ray rotation and Weissenberg photographs gave a primitive orthorhombic cell with $a=7.00$ Å, $b=11.04$ Å, $c=9.97$ Å. The axial ratios derived from these cell dimensions (0.634, 1.00, 0.903) are in good agreement with those derived from goniometric study (orthorhombic; 0.633, 1.00, 0.899 respectively); Strunz (1957). Determination of the space group is handicapped by a large number of systematic weaknesses and it is difficult to distinguish the true absences from weaknesses. For

TABLE 1. INDEXED POWDER X-RAY DATA FOR KENTROLITE
(U.S.N.M. C3223)

$d\text{Å}$	I	hkl	$d\text{Å}$	I	hkl	$d\text{Å}$	I	$d\text{Å}$	I
5.56	ms	020	2.90	vs	113	2.28 ₈	w	1.943	mw
5.10	mw	111	2.86	vs	202, 211	2.22 ₈	vw	1.892	m
5.01	w	002		2.84	s		023, 221	2.20 ₆	vw
3.71	s	022	2.73 ₅	vs	040, 212	2.17 ₁	vw	1.834	m
3.51	s	200	2.70 ₅	w	132	2.12 ₇	m	1.818	w
3.24	s	122, 130	2.60 ₇	vw	123	2.11 ₀	m	1.791	vw
3.17	vw	013, 211	2.55 ₀	w	140	2.09 ₄	w	1.751	w
3.11	w	131	2.48 ₃	w		2.03 ₁	vw	1.732	vw
3.04	mw	?	2.42 ₁	w		1.99 ₄	w	1.704	mw
2.96	m	032, 220	2.35 ₆	vw		1.97 ₃	w	1.652	mw
				2.23 ₃	vw				

Melanotekite (USNM C3224). The first 17 powder lines from $d = \infty$ to 2.5 Å, have the following d (Å) and relative intensities:

5.62, s; 5.05, s; 4.95, w; 3.78, s; 3.57, s; 3.32, s; 3.22, vw; 3.16, w; 3.01, w; 2.95, vs; 2.92, vs; 2.91, s; 2.89, m; 2.78, vs; 2.72, mw; 2.61, vw; 2.59₆ mw.

example, amongst the $h00$ reflections only reflections equal to $2n$ appeared to be present. It was first thought that of the $00l$ reflections only those equal to $2n$ appeared to be present but long exposures disclosed that $l=5$ was present, but weak. Kentrolite and melanotekite crystals gave identical patterns of systematic weaknesses. Therefore the space group could not be positively determined but the crystals definitely have a primitive diffraction aspect. Gabrielson gives a unit cell virtually identical with that obtained in the present study. However, he concluded that the crystals were centered, and produced a structure based on the space group $C222_1$ (No. 20). Consideration of the strong sets of reflections only leads to Gabrielson's space group: consideration of the systematically weak reflections, found in all the crystals examined in this study, leads to the primitive aspect. The weak reflections were most

readily apparent in Weissenberg photographs parallel to c ; Gabrielson had no photographs in this direction. This, together with the limited range of F_{obs} , suggests that the weak reflections may well have been present, but overlooked, in Gabrielson's study. In general the 'R' factor for Gabrielson's data (calculated by the present writer as 32–34 percent in the hOl and Okl sections) suggest that the silicon and oxygen positions are not very well established. A new structure determination is now being made by L. S. Dent Glasser. In addition, several crystals gave a few weak, nonintegral reflections: these belong to some other crystalline phase. The other phase was not visible upon optical examination of the crystals and was not identified further.

TABLE 2. CHEMICAL ANALYSES OF MELANOTEKITE—KENTROLITE

	Melanotekite				Kentrolite		Atomic Ratios			
	Lindstrom		Warren		Damour	Flink	Lindstrom II	Warren (average)	Damour	Flink
	I	II	I	II						
SiO ₂	17.32	17.22	15.51	15.48	15.95	17.68	2.18	2.06	1.98	2.36
PbO	55.26	58.42	55.50	55.63	59.79	55.72	2.00	2.00	2.00	2.00
Fe ₂ O ₃	23.18	22.81	27.49	27.52	—	5.58	—	—	—	—
Mn ₂ O ₃	0.76	0.63	—	—	22.26	21.18	1.10	1.37	1.00	1.27
H ₂ O	—	—	0.68	0.67	—	—	—	—	—	—
CaO	—	—	—	—	—	0.91	—	—	—	—
X*	3.59	0.84	—	—	—	—	—	—	—	—
	Mole Fraction									
SiO ₂	0.420	0.412	0.381	—	0.393	0.412	—	—	—	—
PbO	0.363	0.378	0.367	—	0.398	0.351	—	—	—	—
R ₂ O ₃	0.217	0.210	0.252	—	0.209	0.237	—	—	—	—

* X = CaO, MgO, Na₂O, K₂O, BaO, CuO, FeO, P₂O₅ and Cl.

Melanotekite crystals from C3224 gave a primitive orthorhombic cell with $a = 6.97 \text{ \AA}$, $b = 11.0 \text{ \AA}$, $c = 9.93 \text{ \AA}$. The two crystals examined did not give any nonintegral reflections.

Dana (1898) gives 6.19 as the density of kentrolite. The unit-cell volume as determined in the present study is 760 \AA^3 . The Warren formula for this series ($3\text{PbO} \cdot 2\text{M}_2\text{O}_3 \cdot 3\text{SiO}_2$) gives a formula weight of 1165.5 for kentrolite. The number of formula units per cell, Z , is 2.4. If, however, the "rejected" formula is used, the formula weight becomes 724.3 and $Z = 3.91$. For $Z = 4.00$, the theoretical density would be 6.31. Thus the formula $2\text{PbO} \cdot \text{M}_2\text{O}_3 \cdot 2\text{SiO}_2$ provides a better fit to the crystallographic data. The analytical data are compared in Table 2.

The analytical data for both Mn and Fe-rich end members are included. Both members have the same symmetry and complete solid solution exists between them (Professor C. Frondel, oral communication).

Except for Warren's data, the analyses are compatible with the 2:1:2 ratio.

Samples of kentrolite (USNM C 3223) and melanotekite (USNM C 3224) were heated to 120°C and 700°C. Handpicked concentrates of both kentrolite (C 3223) and melanotekite (C 3224) lost some weight on heating to 120°C (0.04 and 0.02 wt. % resp.). On further heating to 700°C, neither lost more than an additional 0.02 weight percent, and the X-ray pattern remained unchanged. Differential thermal analysis of kentrolite did not reveal any thermal effects between 22°C–840°C. The sample was still unmelted at 840°C and gave an unchanged powder pattern after cooling to room temperature.

Studies on PbO-Fe₂O₃-SiO₂ and PbO-Mn₂O₃-SiO₂ compositions. A mixture of composition 2PbO·Fe₂O₃·2SiO₂ heated to 700°C in air gave an apparently single-phase product. Guinier photographs showed that the powder pattern was identical with that obtained from natural melanotekite. However, the composition 3PbO·2Fe₂O₃·3SiO₂ reacted at 700°C, gave a powder pattern of a two phase mixture: melanotekite plus hematite. The hematite remained even after repeated crushing and resintering. Thus this composition lies at least approximately on the join melanotekite-hematite.

Oxide mixtures of the composition 2PbO·Mn₂O₃·2SiO₂ sintered at 700°C in air yield an apparently single-phase preparation. The powder pattern matched that of kentrolite at the larger spacings. The over-all fit, especially for the weaker lines, became less perfect at spacings below approximately 2.5 Å. The differences between the two powder patterns may be due to slight differences in symmetry between natural and synthetic phases, but it is more likely that the appreciably large cell dimensions of the synthetic product, compared with those of kentrolite, are sufficient to cause the minor differences observed. No chemical analyses of the kentrolite were available, but kentrolite commonly contains a relatively high iron content (Table 2), and its unit-cell size is appreciably smaller than that of the synthetic Mn end-member. The sintered preparations did not yield single crystals suitable for X-ray diffraction study.

It was felt that a knowledge of the subsolidus compatibility triangles would be helpful in further confirming the formula of melanotekite. In addition to melanotekite, the PbO-Fe₂O₃-SiO₂ system contains six compositions which are represented by one or more naturally-occurring phases. The compositions and polymorphic forms relevant to the present study are: SiO₂: quartz, PbSiO₃: alamosite, PbO: litharge, massicot: PbO·2Fe₂O₃, plumboferrite: PbO·6Fe₂O₃, magnetoplumbite and Fe₂O₃:

hematite. In addition the phases $2\text{PbO}\cdot\text{SiO}_2$, $4\text{PbO}\cdot\text{SiO}_2$ (α , β and γ polymorphs) and $2\text{PbO}\cdot\text{Fe}_2\text{O}_3$ are known from phase equilibrium studies of the $\text{PbO}\text{-SiO}_2$ and $\text{PbO}\text{-Fe}_2\text{O}_3$ systems. In order to understand the ternary phase relationships, it was necessary to make a few additional experiments on the limiting one and two component systems.

The effect of SiO_2 and Fe_2O_3 on the polymorphism of PbO . PbO occurs in two well characterized polymorphs: the low temperature form is red PbO , or litharge: the high form is yellow PbO , or massicot. The high-low inversion at $\sim 450^\circ\text{C}$ is sluggish, and yellow PbO is readily preserved to room temperature even during slow cooling. Appropriate mixtures of either yellow or red PbO and SiO_2 were heated to 650°C and subsequently cooled. Only yellow PbO and $\gamma\text{-}4\text{PbO}\cdot\text{SiO}_2$ were identified. However, appropriate $\text{PbO}\text{-Fe}_2\text{O}_3$ mixtures gave only red PbO under the same conditions. A few $\text{PbO}\text{-Fe}_2\text{O}_3\text{-SiO}_2$ compositions gave both red and yellow PbO phases, but several regrindings and refrirings resulted in complete conversion of the PbO to litharge. Differential thermal analyses of several litharge-containing compositions did not reveal any heat effects which might be due to the partial or complete conversion of massicot \rightarrow litharge during the cooling stage. It is probable that Fe_2O_3 has a stabilizing influence on red PbO . Powder patterns of this stabilized red PbO were identical in spacings and relative intensities with those reported for pure red PbO (Swanson and Fuyat, 1954) except that the 101, 200 and 202 reflections were diffuse; the others were sharp.

The lead silicates. Geller, Creamer and Bunting (1934) reported the existence of three polymorphs of $4\text{PbO}\cdot\text{SiO}_2$. The β phase was stable from $720^\circ\text{-}140^\circ\text{C}$; at the lower temperature it underwent a rapid inversion to $\gamma\text{-}4\text{PbO}\cdot\text{SiO}_2$. This was also confirmed in the present study by D.T.A.; a reversible heat effect was found to extend over a $5\text{-}10^\circ\text{C}$ range, centered at $143^\circ \pm 2^\circ\text{C}$. The existence of the other reported polymorphic form, $\alpha\text{-}4\text{PbO}\cdot\text{SiO}_2$, stable from 720°C to the incongruent melting point at 725°C , is less certain. It was found that runs quenched from 732°C or slightly over, yielded yellow PbO in glass. However at 727°C , the PbO was partially surrounded by a fibrous birefringent phase together with some glass. This birefringent phase gave a characteristic X-ray powder pattern and is presumably " $\alpha\text{-}4\text{PbO}\cdot\text{SiO}_2$ ". It was also obtained at 720°C together with PbO and $\beta\text{-}4\text{PbO}\cdot\text{SiO}_2$, but not at lower temperatures. The texture of the birefringent phase in the 732°C run certainly suggests that the α phase arises from devitrification of part of the liquid during the quenching stage. It is thus uncertain if its composition is

$4\text{PbO}\cdot\text{SiO}_2$. Powder data are shown in Table 3. Powder data for the other lead silicates are in good agreement with those reported by Argyle and Hummel (1960).

The lead ferrites. Berger and Pawlek (1957) and Mountvala and Ravitz (1962) studied the lead ferrites. Three compounds were found: $2\text{PbO}\cdot\text{Fe}_2\text{O}_3$, $\text{PbO}\cdot 2\text{Fe}_2\text{O}_3$ and $\text{PbO}\cdot 6\text{Fe}_2\text{O}_3$. Mountvala and Ravitz were unable to synthesize these phases at temperatures below 650, 750, and 760°C, respectively and assumed that these temperatures corresponded to the lower limit of stability of the phases. In the present study, fine-grained PbO and Fe_2O_3 were observed to have reacted, forming $2\text{PbO}\cdot\text{Fe}_2\text{O}_3$ at 600°C, and $2\text{PbO}\cdot 2\text{Fe}_2\text{O}_3$ and $\text{PbO}\cdot 6\text{Fe}_2\text{O}_3$ at 650°C. Crystalline samples of each of the three phases showed no tendency to decompose in runs of 10 days' duration at 600° and 14 days at 550°C. Therefore, there is no positive evidence that these phases have the lower limit of stability shown by Mountvala and Ravitz. Likewise, no positive evidence for the variable composition reported for these phases was found. The natural occurrences of plumboferrite and magnetoplumbite do not suggest temperatures of formation above 750–760°C, nor do the limited number of analyses of natural minerals suggest the existence of a relatively wide band of compositions. Powder data for the $2\text{PbO}\cdot\text{Fe}_2\text{O}_3$ phase are reported in Table 3. The strong reflections can be indexed on the basis of a primitive cubic cell with $a\approx 3.89$ Å. On account of the high pseudosymmetry it would be unwise to deduce a true cell from the remaining weaker powder reflections.

Ternary phase relations. Thirty-one $\text{PbO}\text{-Fe}_2\text{O}_3\text{-SiO}_2$ compositions were prepared. The phases present in the heated compositions were determined and these data used to construct the subsolidus compatibility triangles as shown in Figure 1. In addition to melanotekite, another ternary phase, designated as *X* in Figure 1, was encountered. This phase gives the characteristic X-ray diffraction pattern shown in Table 3. Its exact composition is uncertain, but lies at or close to the molar ratio $12\text{PbO}\cdot\text{Fe}_2\text{O}_3\cdot 2\text{SiO}_2$. An apparently single-phase preparation of this composition has a density of 8.1 g/cc: it is weakly ferromagnetic. The relatively low content of Fe_2O_3 and SiO_2 , coupled with the high formula weight of lead makes it difficult to locate the composition to an accuracy better than ± 2 mole percent. The X-ray powder pattern of the *X* phase bears a striking resemblance to that of red PbO , except that the reflections of the *X* phase are shifted considerably to shorter spacings. The strongest lines can thus be indexed on the basis of a primitive tetragonal pseudocell having $a=3.83$, $c=4.82$ Å. This represents a substantial

TABLE 3. X-RAY POWDER DATA FOR SELECTED $\text{PbO} \cdot \text{Fe}_2\text{O}_3 \cdot \text{SiO}_2$ PHASES

“ α - $4\text{PbO} \cdot \text{SiO}_2$ ” ¹		$2\text{PbO} \cdot \text{Fe}_2\text{O}_3$ ²			Phase X, probably $12\text{PbO} \cdot \text{Fe}_2\text{O}_3 \cdot 2\text{SiO}_2$ ²		
$d\text{\AA}$	<i>I</i>	$d\text{\AA}$	<i>I</i>	<i>hkl</i> ³	$d\text{\AA}$	<i>I</i>	<i>hkl</i> ⁴
6.60	w	4.52	w		6.80	m	
5.62	mw	4.00	vw		5.35	w	
5.43	mw	3.88	s	100	4.70	m	
5.40	vw	3.50	ms		3.75	w	
4.25	vw	3.12	ms		3.34	m	
4.19	vw	3.06	m		3.05	w	
4.00	mw ⁵	2.75–7 ⁶	vvs	110	3.00	vs	101 (vvs)
3.77	ms	2.34	s	111	2.71	s	110 (vs)
3.49	mw	2.17	w		2.64	w	
3.41	mw	1.970	w		2.41	m	002 (m)
3.34	m	1.94 ⁶	vs	200	2.39	w	
3.29	ms	1.870	w		2.36	mw	
3.21	m	1.74 ⁶	w	210	2.30	w	
3.09	s ⁵	1.59 ⁶	vs	211	2.19	w	102 (vw)
3.05	m	1.375	vs	220	2.17	w	
3.02	vs	1.230	s	310	2.04	w	
2.92	s ⁵				1.922 ⁶	ms	200 (m)
2.84	s				1.918	ms	
2.82	m	<i>a</i>	3.90 \AA		1.835	mw	
2.78	m				1.805	s	112 (s)
2.74	m ⁵				1.710	w	
2.69	s				1.698	vw	
2.67	w				1.615	s	211 (s)
2.56	vw				1.580	vw	
2.49 ₅	ms				1.550	w	
2.42 ₀	m				1.502	m	202 (w)
2.30 ₅	s				1.484	m	103 (m)
2.29 ₅	w				1.460	w	113 (w)
2.24 ₀	m				1.435	vw	
2.23 ₀	w				1.356	ms	220 (s)
2.22 ₀	m						
2.170	m						
2.115	w						
1.998	s ⁵						
1.880	m						
1.810	m						

¹ Sample prepared by heating $4\text{PbO} \cdot \text{SiO}_2$ composition 4 hrs. at 727°C .

² Guinier photograph.

³ Pseudo cubic cell.

⁴ Pseudo tetragonal cell with $a = 3.83 \text{\AA}$, $c = 4.82 \text{\AA}$. Intensities in parentheses after the (*hkl*) values are those for red PbO : Tetragonal, $a = 3.973$, $c = 5.019 \text{\AA}$.

⁵ Probably yellow PbO .

⁶ Diffuse reflection.

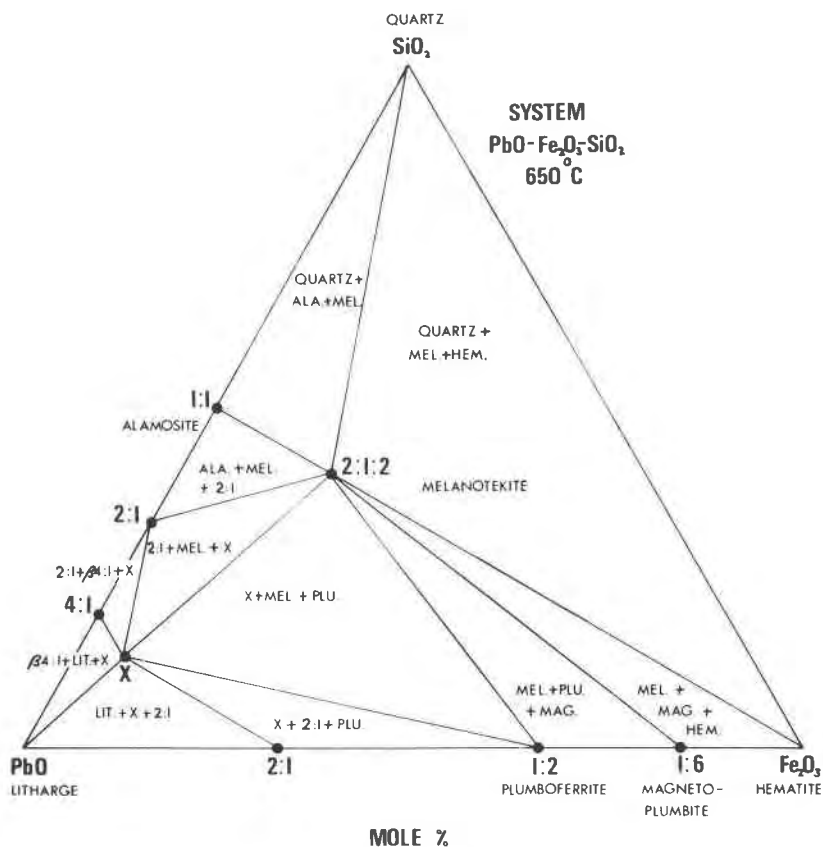


FIG. 1. Subsolidus compatibility relations. Phase X is probably $12\text{PbO} \cdot \text{Fe}_2\text{O}_3 \cdot 2\text{SiO}_2$; see text. Phases known to occur in nature have been designated with their mineralogical names; the first three letters of these names are used as abbreviations.

contraction in cell dimensions: litharge has $a = 3.97$, $c = 5.02$ Å. Mixtures on the PbO-X join were examined to see if the X phase might represent a solid solution based on litharge itself. However, the position and intensity of reflections in the powder patterns suggest that PbO and X occur as discrete phases and that the similarity in powder patterns is not caused by solid solution in the litharge phase. It is suggested that the arrangement of lead atoms in the X phase is basically similar to that found in red PbO. Differential thermal analysis of the X phase did not reveal any heat effects between 24° and 740°C. The X phase remained unmelted at 740°C. Weight change studies were made on the X-phase composition to see if it gained or lost oxygen upon heating in air. Previously dried

PbO, SiO₂ and Fe₂O₃ were used as starting materials. After heating the 12 PbO·Fe₂O₃·2SiO composition in air for three days at 650°C, three days at 675, and three days at 700°C a 10-gram sample had a cumulative weight loss of 0.0012 gram. It is not therefore likely that the X phase contains lead or iron in some higher oxidation state *e.g.*, Pb⁴⁺, Fe⁴⁺, unless the rather unlikely assumption is made that the lead present in some higher oxidation state is gravimetrically balanced *e.g.*, by reduction of iron to Fe²⁺.

ACKNOWLEDGMENTS

The author would like to acknowledge the assistance of two of his students, Mr. C. Fraser and Mr. P. W. Vipond. Their enthusiasm in making preparations and analyzing X-ray patterns contributed greatly to elucidation of the compatibility relations in this system. The cooperation of the United States National Museum in loaning specimens was essential to the present investigation.

REFERENCES

- ARGYLE, J. F. AND F. A. HUMMEL (1960) Dilatometric and X-ray data for lead compounds. *J. Amer. Ceram. Soc.*, **43**, 452-57.
- BERGER, W. AND PAWLEK, F. (1957) Krystallographische und magnetische Untersuchungen in System Dleioxyd (PbO)-Eisenoxyd (Fe₂O₃). *Arch. Eisenhüttenwerken* **28**, 101-108.
- DAMOUR, A. AND G. VOM RATH, (1880) Über den Kentrolit, eine neue Mineralspecies. *Z. Kristallogr.* **5**, 32.
- DANA, E. S. (1892) *Dana's System of Mineralogy*, 6 ed. Wiley and Sons, N. Y., p. 1039.
- FLINK, G. (1891). Kentrolit von Långbanshyttan, Mineralogische Notizen III. *Kon. Svenska Vetensk. Akad. Handl. Bihang*, **16**, part II, No. 14, p. 14.
- GABRIELSON, O. (1963) The crystal structures of kentrolite and melanotekite. *Ark. Mineral. Geol.* **3**, No. 7, 141.
- GELLER, R. F., A. S. CREAMER, AND E. N. BUNTING (1934) The system PbO-SiO₂. *J. Res. (U.S.) Nat. Bur. Stand.* **13**, 237-244.
- LINDSTROM G. (1880) Analyser av tvenne mineral från Långban. *Kon. svenska Vetensk. Akad. Forhandl. Ofvers.* **35**, No. 6, 53.
- MOUNTVALA, A. J. AND S. F. RAVITZ (1962) Phase relations and structures in the system PbO-Fe₂O₃. *J. Amer. Ceram. Soc.* **45**, 285-288.
- WARREN, C. H. (1895) Mineralogical notes, 1. On the occurrence of melanotekite at Hillsboro, New Mexico, and on the chemical composition of melanotekite and kentrolite. *Amer. J. Sci.* **156**, 116-119.
- STRUNZ, H. (1957) *Mineralogische Tabellen*. Akademische Verlagsgesellschaft, Leipzig.
- SWANSON, H. E. AND FUYAT, R. K. (1954). Standard X-ray diffraction patterns. (*U. S.*) *Nat. Bur. Stand. Circ.* **539**, 30-32.

Manuscript received, September 1, 1966; accepted for publication, October 24, 1966.