

- (1965) *Nat. Bur. Stand. [U.S.] Monogr.* **25**, (Sec 4,) 21–22.  
ZAMBONINI, F. AND L. MALOSI (1931) *Z. Kristallogr.* **80**, 442–454.  
———, AND F. LAVES (1932) *Z. Kristallogr.* **83**, 26–28.  
ZEMANN, J. (1960) *Acta crystallogr.* **13**, 863–867.

THE AMERICAN MINERALOGIST, VOL. 54, SEPTEMBER–OCTOBER, 1969

DIFFERENTIAL THERMAL ANALYSIS OF HIGH-  
ALUMINA ALLOPHANE

KENNETH G. SNETSINGER, *Space Sciences Division, NASA,  
Ames Research Center, Moffett Field, California 94035,*

AND

W. D. KELLER, *Department of Geology, University of Missouri,  
Columbia, Missouri 65201.*

ABSTRACT

A differential thermalgram of high-alumina allophane ( $\text{SiO}_2 \cdot 2\text{Al}_2\text{O}_3 \cdot 8\text{H}_2\text{O}$ ) shows an endothermal peak at  $90^\circ\text{C}$  representing loss of water; there is no evidence of  $\text{OH}^-$ . Amounts of fluxing ions were apparently insufficient to suppress a high-temperature exothermal reaction at  $990^\circ\text{C}$ , tentatively ascribed to formation of an Al-Si spinel.

Since publication of the article on high-alumina allophane (Snetsinger, 1967), several inquiries have been received regarding availability of differential thermal analytical data on this material. A thermalgram has subsequently been obtained, done on a scant milligram of pure allophane using a microholder unit manufactured by the Robert L. Stone Company (Tracor Instruments) of Austin, Texas; the sample was run in a combined cup-and-differential thermocouple. Referring to Figure 1, the strong endothermal peak at about  $90^\circ\text{C}$  probably represents loss of absorbed water, while the small exothermal effect at  $340^\circ \text{ca.}$  may be due to (1) oxidation of a very small amount of organic material or (2) oxidation of a trace of ferrous iron. Irregularities in the baseline occur above  $400^\circ\text{C}$ ; these are due to electronic noise. The exothermal peak at  $990^\circ\text{C}$  is tentatively ascribed to formation of an Al-Si spinel. Amounts of ferrous iron and organic material in the high-alumina allophane are insufficient to have suppressed any dehydroxylation endotherm in the  $330^\circ\text{C}$  range, and no other dehydroxylation peaks occur. This is in agreement with the lack of infrared evidence for presence of hydroxyl (Snetsinger, 1967).

Presence or absence of an exothermal peak above  $900^\circ\text{C}$  in allophane has been of interest to several investigators. Fieldes (1955) classified as "allophane A" ones that yielded exothermal peaks near  $900^\circ\text{C}$ , whereas his "allophane B" lacked such peaks. Campbell *et al.* (1968) found that the height of high-temperature exothermal peaks of allophanes increases as particle size of allophane decreases; organic matter apparently en-

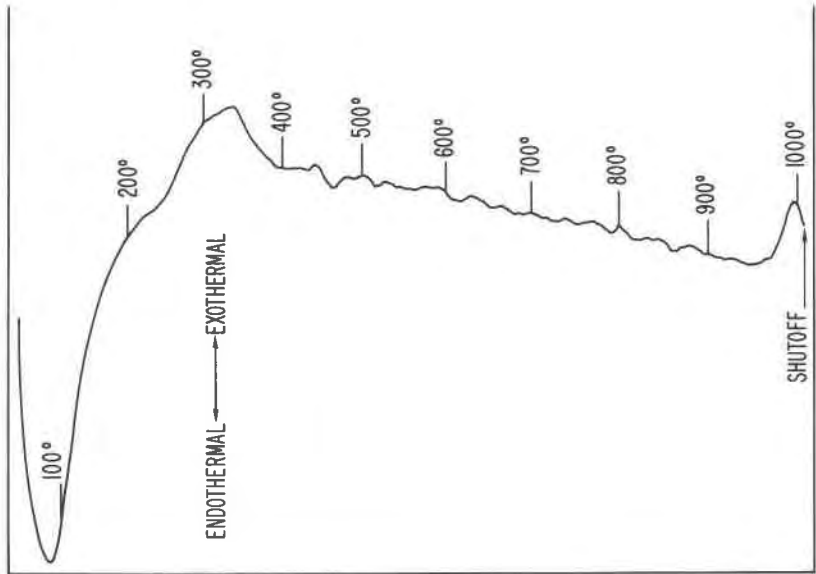


FIG. 1. Differential thermalgram of high-alumina allophane.

hances the sharpness of allophane exotherms. Gruver *et al.* (1949) found that Na compounds added to kaolinite tended to subdue or suppress the high-temperature peak. It is probable that fluxing ions, such as Na, would develop a glassy product in the Al-Si system, rather than the mineral inversion releasing exothermic energy which occurs as an Al-Si spinel is formed.

#### REFERENCES

- CAMPBELL, A. S., MITCHELL, B. D., AND J. M. BRACEWELL (1968) Effects of particle size, pH and organic matter on the thermal analysis of allophane. *Clay Minerals*, **7**, 451-454.
- FIELDS, M. (1955) Clay mineralogy of New Zealand soils, part II: Allophane and related mineral colloids. *N. Z. J. Sci. Tech.*, **37**, 336-350.
- GRUVER, R. M., HENRY, E. C., AND H. HEYSTEK (1949) Suppression of thermal reactions in kaolinite. *Amer. Mineral.*, **34**, 869-874.
- SNETSINGER, K. G. (1967) High-alumina allophane as a weathering product of plagioclase. *Amer. Mineral.*, **52**, 254-262.