

Effects of Preferred Orientation on X-Ray Diffraction Patterns of Gypsum

P. E. GRATTAN-BELLEW

National Research Council of Canada, Division of Building Research
Ottawa, Canada K1A 0R6

Abstract

Intensities of the stronger reflections 020, 021, and 041 obtained from X-ray powder photographs of gypsum from pyritic shale and other sources differ from those listed in the Joint Committee on Powder Diffraction Standards files. The differences are shown to be due to the effect of preferred orientation on (010) planes.

Two X-ray diffraction patterns for gypsum are listed in the Joint Committee on Powder Diffraction Standards (JCPDS) files, both shown as highly reliable. Intensities of the stronger reflections, notably 020, 021, and 041, measured with a Debye-Scherrer camera from a sample of gypsum taken from black pyritic shale (Penner, Eden, and Grattan-Bellew, 1973) differed significantly from those on JCPDS cards 6-46 and 21-816 (Table 1).

Samples of gypsum from other sources produced diffractograms similar to those of the gypsum taken from the shale (Table 2). Diffractograms obtained by means of a powder diffractometer showed intensities that matched those on JCPDS card 6-46. All samples for the diffractometer were prepared by sedimenting gypsum on a glass slide. Gypsum, when ground, forms either flat, plate-like crystals or acicular crystals, both having well developed (010) faces (Fig. 1). The crystals tend to lie on the (010) faces, giving rise to marked, preferred orientation that results in greatly enhanced intensity of the 020 reflection observed in diffractometer traces.

The intensities shown on JCPDS card 6-46 were also obtained from a diffractometer trace. The usual methods of sample preparation (Klug and Alexander, 1974) were used without success to try to eliminate preferred orientation from the diffractometer mounts. A dilute suspension of gypsum sedimented on a flat piece of polyurethane foam made into a sample holder produced a pattern of intensities essentially free from the effect of preferred orientation, but the intensities were so weak that only the strongest could be observed. When the intensities were increased by the addition of more gypsum, preferred orientation was reintroduced.

Debye-Scherrer photographs were obtained from

TABLE 1. Interplanar Spacings, Intensities, and Indices of Gypsum

-A-			-B-		-C-		
D	I/I ₀	HKL	D	I/I ₀	D	I/I ₀	HKL
7.61	45	020	7.6454	80	7.56	100	020
4.74	4	11 $\bar{1}$	4.7606	3	-	-	-
4.28	90	021	4.2820	100	4.27	50	12 $\bar{1}$
3.80	8	150}	3.8018	18	3.79	20	040}
		040}					
3.17	4	111	3.1690	15	3.163	4	11 $\bar{2}$
3.07	30	041	3.0623	92	3.059	55	141
		22 $\bar{1}$ }					
2.871	100	200}	2.8699	59	2.867	25	002
		200}					
2.788	20	11 $\bar{2}$	2.7955	12	2.786	6	21 $\bar{1}$
2.684	50	150}	2.6812	37	2.679	28	051}
		220}					022}
2.595	2	15 $\bar{1}$ }	2.58	6	2.591	4	150}
		002}					202}
		-			2.530	<1	060
2.486	20	20 $\bar{2}$	2.4998	11	2.495	6	200
2.475	2	13 $\bar{2}$	-	-	-	-	-
2.454	6	022	2.4538	9	2.450	4	22 $\bar{2}$
2.406	2	24 $\bar{1}$	2.4028	4	2.400	4	141
2.220	6	151	2.2125	19	2.216	6	15 $\bar{2}$
2.142	2	042	-	-	2.139	2	24 $\bar{2}$
2.087	14	24 $\bar{2}$	2.0785	30	2.080	10	12 $\bar{3}$
		31 $\bar{1}$ }					11 $\bar{2}$ }
2.073	20	15 $\bar{2}$ }	-	-	2.073	8	251}
		112}					
2.048	4	112	2.0473	-	-	-	-
1.993	2	17 $\bar{1}$	1.9918	3	1.990	4	170
1.954	6	31 $\bar{2}$	1.9491	2	1.953	2	211
1.900	4	310}	1.9009	19	1.898	16	080}
		260}					062}
1.8..	6	241	1.8787	18	1.879	10	143
1.865	4	113	-	-	1.864	4	312
1.812	4	062	1.8104	19	1.812	10	26 $\bar{2}$
1.798	6	223	-	-	1.796	4	32 $\bar{1}$
1.778	4	262	1.7758	14	1.778	10	260
		-			1.711	2	253
1.685	2	023	-	-	1.684	2	323
1.664	4	243	1.6622	8	1.664	4	341
1.646	2	261	-	-	1.645	2	163
1.622	4	202}	1.6172	12	1.621	6	204, ETC.
		281}			1.599	<1	35 $\bar{2}$, 190
		-					
1.587	2	311}	1.5797	5	1.584	2	224, ETC.
		222}					
1.552	2	402	-	-	1.532	2	282
1.521	2	42 $\bar{2}$, ETC.	-	-	1.522	2	222, 134
1.440	4	441	-	-	-	-	-
		133}					
1.434	4	400}					
		204}					
1.418	2	204					
1.402	2	423					

-A- JCPDS card 21-816 (with indices listed on card)
-B- Authors No. 1073
-C- JCPDS card 6-0046 (with indices listed on card)

Brackets join indices of reflections not resolved on diffractograms.

TABLE 2. Interplanar Spacings and Intensities of Gypsum

HKL	-A-		-B-		-C-		-D-		-E-	
	D	I/I ₀	D	I/I ₀	D	I/I ₀	D	I/I ₀	D	I/I ₀
020	7.5879	84	7.6454	80	7.5806	81	7.5891	100	7.576	100
11 $\bar{1}$	4.7450	1	4.7606	3	4.7354	2	-	-	-	-
021	4.2741	100	4.2820	100	4.2822	100	4.2716	54	4.276	6
130	3.7943	14	3.8018	18	3.8181	18	3.7968	23	3.798	22
040										
111	3.1611	3	3.1690	15	3.1640	18	-	-	-	-
041	3.0597	73	3.0623	92	3.0676	73	3.0601	52	3.061	7
22 $\bar{1}$	2.8690	44	2.8699	59	2.8744	53	2.8669	22	2.866	1
200	-	-	-	-	NOT OBSERVED	-	-	-	-	-
11 $\bar{2}$	2.7841	7	2.7955	12	2.7955	7	2.7876	3	-	-
150	2.6799	36	2.6812	37	2.6852	31	2.6880	16	2.68	2
220										
151	2.5890	3	2.58	6	2.5945	5	2.5971	3	-	-
002										
202	2.49	11	2.4998	11	2.4931	11	2.4977	3	-	-
13 $\bar{2}$	-	-	-	-	NOT OBSERVED	-	-	-	-	-
022	2.4507	9	2.4538	9	2.4535	8	2.4546	2	-	-
24 $\bar{1}$	2.4082	3	2.4028	4	2.4059	5	2.4062	1	-	-
151	2.2130	12	2.2125	19	2.2151	13	2.2220	8	2.21	1
042	-	-	-	-	2.1348	6	-	-	-	-
24 $\bar{2}$	2.0792	30	2.0785	30	2.0809	27	2.0837	10	-	-
221	-	-	-	-	NOT OBSERVED	-	-	-	-	-
311	-	-	-	-	NOT OBSERVED	-	-	-	-	-
15 $\bar{2}$	-	-	-	-	NOT OBSERVED	-	-	-	-	-
112	2.0434	3	2.0473	-	2.0407	10	-	-	-	-
17 $\bar{1}$	1.9878	1	1.9918	3	1.9938	7	1.9956	2	-	-
312	1.9512	1	1.9491	2	1.9193	7	1.9572	1	-	-
310	1.8953	19	1.9009	19	1.9010	15	1.9044	9	1.899	2
260										
080	-	-	-	-	NOT OBSERVED	-	-	-	-	-
241	1.8733	16	1.8787	18	1.8788	14	1.8851	5	-	-
113	-	-	-	-	NOT OBSERVED	-	-	-	-	-
082	1.8069	17	1.8104	19	1.8104	12	1.8159	6	-	-
223	-	-	-	-	NOT OBSERVED	-	-	-	-	-
262	1.7775	14	1.7758	14	1.7759	11	1.7841	6	-	-
023	-	-	-	-	NOT OBSERVED	-	-	-	-	-
243	1.6614	7	1.6622	8	1.6636	17	1.6676	2	-	-
261	-	-	-	-	-	-	-	-	1.6481	1
202	1.6200	10	1.6117	12	1.6204	10	1.6234	5	-	-
281+										
311	-	-	-	-	-	-	-	-	-	-
222+	-	-	1.5797	5	1.6060	11	1.5859	1	-	-
133	-	-	1.4361	6	1.4381	11	-	-	-	-

- A- PWD photo 1079 (hydrated pottery plaster)
 -B- PWD photo 1073 (gypsum from pyritic shale)
 -C- PWD photo selenite
 -D- Diffractometer trace of selenite on urethane foam sample holder
 -E- Diffractometer trace of selenite, smear mount on glass slide

Brackets join reflections which were not resolved.

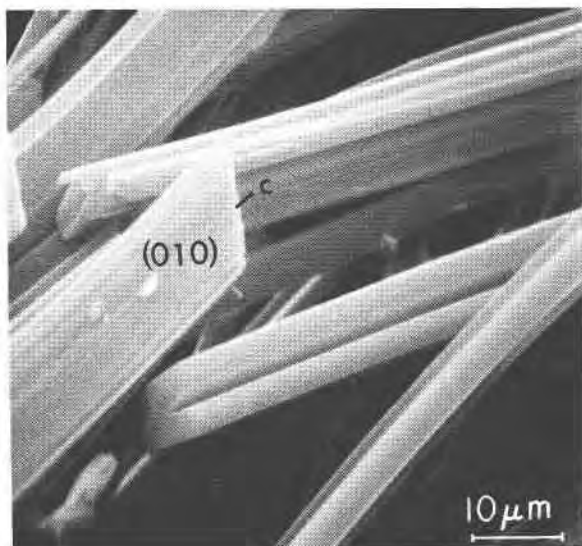
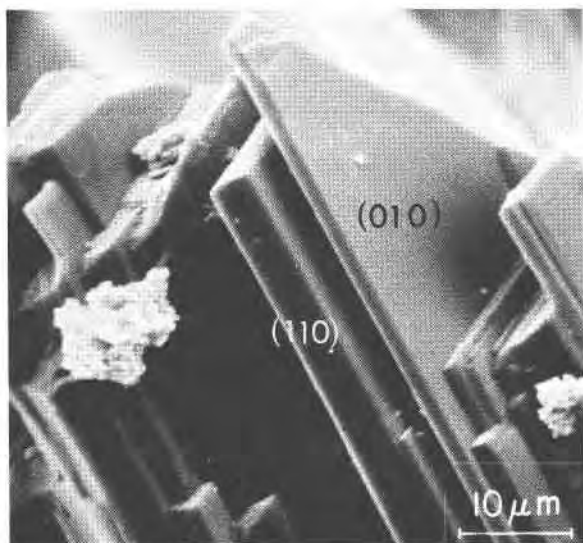


FIG. 1. Gypsum crystals on the surface of fragments of shale, magnified about 2,000 times in the scanning electron microscope. Either tabular morphology (1a) or acicular morphology (1b) is obtained when larger crystals of gypsum are crushed for X-ray powder diffraction examination. It is evident that it would be difficult to avoid preferred orientation in diffractometer mounts owing to the tendency of the crystals to lie on the well developed (010) faces.

samples of gypsum packed into lithium glass capillary tubes; intensities were measured from microdensitometer traces of the photographs. Intensities from the powder photographs matched those obtained from a crystal of gypsum mounted on a single crystal diffractometer, indicating that the X-ray powder photographs were essentially free from the effect of preferred orientation. A similar pattern of intensities was observed on a powder pattern obtained from a single crystal mounted on a Gandolfi camera (Gandolfi, 1967) and by Becherer and Fiedler (1955) using a Debye-Scherrer camera.

The intensities listed on JCPDS card 21-816 are different from those of card 6-46 and from those found by the author (Table 1). The reason for this is not apparent because the geometry of the transmission powder camera and the experimental details used to obtain the intensity data for card 21-816 are not given.

Acknowledgments

The author is grateful to Dr. A. W. Hanson, Division of Biological Sciences, National Research Council of Canada, for useful discussions and for his contribution of single-crystal measurements. The author also wishes to thank P. J. Lefebvre for maintaining the X-ray laboratory and for taking many of the diffractograms used in this study.

This paper is a contribution from the Division of Building Research, National Research Council of Canada, and is published with the approval of the Director of the Division.

References

- BECHERER, G., AND H. FIEDLER (1955) Über röntgenografische Untersuchungen des Abbindevorganges bei Gips. *Silikattechnik* 6.Jg. 7, 292-295.
- GANDOLFI, G. (1967) Discussion upon methods to obtain X-ray powder patterns from a single crystal. *Micr. Petrogr. Acta*, 13, 67-74.
- KLUG, H. P., AND L. E. ALEXANDER (1974) *X-Ray Diffraction Procedures for Polycrystalline and Amorphous Materials*. 2nd ed, John Wiley and Sons, p. 368-376.
- PENNER, E., W. J. EDEN, AND P. E. GRATTAN-BELLEW (1973) *Expansion of Pyritic Shales*. National Research Council of Canada, Division of Building Research, CBD 152.