

## Thermodynamics of Formation of Some Compounds with the Pseudobrookite Structure and of the $\text{FeTi}_2\text{O}_5\text{-Ti}_3\text{O}_5$ Solid Solution Series

ALEXANDRA NAVROTSKY

Department of Chemistry, Arizona State University,  
Tempe, Arizona 85281

### Abstract

The enthalpy of formation of pseudobrookite,  $\text{Fe}_2\text{TiO}_5$ , from  $\text{Fe}_2\text{O}_3$  and  $\text{TiO}_2$  is found by oxide melt solution calorimetry to be  $+1.99 \pm 0.15$  kcal mol<sup>-1</sup> ( $+8.33 \pm 0.63$  KJ mol<sup>-1</sup>). Thermochemical data for other compounds with the pseudobrookite structure are summarized. Pseudobrookites are "entropy-stabilized" high temperature phases with partially disordered cation distributions. Their decomposition at low temperatures to assemblages of binary oxides (for  $A_2^{3+}B^{4+}O_5$  pseudobrookites) or to assemblages of phases of ilmenite and rutile structure (for  $A^{2+}B_2^{4+}O_5$  pseudobrookites) reflects the balance between endothermic enthalpies of formation from these assemblages and the substantial positive entropies of formation arising from the substitutional disorder. A simple cation distribution model is applied to the distribution of iron between  $4c$  ( $A$ ) and  $8f$  ( $B$ ) sites in the  $\text{FeTi}_2\text{O}_5\text{-Ti}_3\text{O}_5$  system, from which high  $\text{Ti}_3\text{O}_5$  is predicted to have the cation distribution  $(\text{Ti}^{4+}_{0.06}\text{Ti}^{3+}_{0.94})_A(\text{Ti}^{4+}_{0.96}\text{Ti}^{3+}_{0.04})_B\text{O}_5$ . Interchange enthalpies (or free energies) for the reactions:  $\text{Mg}^{2+}_A + \text{Ti}^{4+}_B = \text{Mg}^{2+}_B + \text{Ti}^{4+}_A$ ,  $\text{Fe}^{2+}_A + \text{Ti}^{4+}_B = \text{Fe}^{2+}_B + \text{Ti}^{4+}_A$ , and  $\text{Ti}^{3+}_A + \text{Ti}^{4+}_B = \text{Ti}^{3+}_B + \text{Ti}^{4+}_A$  are +8.6, +13, and +10 kcal mol<sup>-1</sup> respectively (36.0, 54, and 42 KJ mol<sup>-1</sup>, respectively).  $\text{MgTi}_2\text{O}_5$  exhibits somewhat disordered pseudobrookite structures derived from a "normal" structure stable at low temperature, while  $\text{Ti}_3\text{O}_5$  and probably also  $\text{Fe}_2\text{TiO}_5$ ,  $\text{Al}_2\text{TiO}_5$ , and  $\text{Ga}_2\text{TiO}_5$  have somewhat disordered structures derived from an "inverse structure stable at low temperature. Thus  $\text{Ti}^{4+}$  appears to have a strong preference for the  $8f$  ( $B$ ) sites in all these compounds of pseudobrookite structure.

### Introduction

Study of lunar basalts has resulted in considerable interest in minerals with the pseudobrookite structure. These include  $\text{Fe}_2\text{TiO}_5$  (pseudobrookite),  $\text{FeTi}_2\text{O}_5$  (ferropseudobrookite),  $\text{MgTi}_2\text{O}_5$  (karrooite),  $(\text{Mg,Fe})\text{Ti}_2\text{O}_5$  (armalcolite), and solid solutions in the  $\text{Fe}_2\text{TiO}_5\text{-Ti}_3\text{O}_5$  series. The purpose of this paper is threefold: (a) to present new high temperature solution calorimetric data for the enthalpy of formation of  $\text{Fe}_2\text{TiO}_5$ , (b) to review the existing thermochemical data for ternary oxides with the pseudobrookite structure, and (c) to correlate the thermodynamic and structural data and to apply a simple thermodynamic model to the cation distributions in  $\text{MgTi}_2\text{O}_5$ ,  $\text{FeTi}_2\text{O}_5$ , and the  $\text{FeTi}_2\text{O}_5\text{-Ti}_3\text{O}_5$  solid solution series.

### The Pseudobrookite Structure

Early structure determinations were by Pauling (1930) and Hamelin (1958). Recently, Lind and Housley (1972) have performed structure refinements on synthetic single crystals of karrooite,  $\text{MgTi}_2\text{O}_5$ , and armalcolite,  $\text{Mg}_{0.5}\text{Fe}_{0.5}\text{Ti}_2\text{O}_5$ . In the orthorhombic pseudobrookite structure, space group  $Bbmm$ ,

with 4  $AB_2O_5$  formula units in the unit cell, all the cations are in octahedral coordination. There are two kinds of octahedral sites, with fourfold ( $4c$  or  $A$  sites) and eightfold ( $8f$  or  $B$  sites) multiplicity. Three octahedra share edges to form units which are then linked together into double chains as building blocks for the structure. In monoclinic pseudobrookites such as  $\text{Ti}_3\text{O}_5$  and the titanium-rich members of the  $\text{Ti}_3\text{O}_5\text{-FeTi}_2\text{O}_5$  solid solution series (Grey and Ward (1973), the  $8f$  ( $B$ ) site is further split into two non-equivalent sites. For armalcolite, Lind and Housley (1972) give the following metal oxygen distances for the  $4c$  and  $8f$  octahedra— $8f$ , 2.061, 1.845, 1.993, 2.172, 1.938, and 1.938 Å;  $4c$ , 1.960, 2.191, 1.960, 2.191, 2.030, and 2.030 Å. Thus, both octahedra are distorted. The average bond length in  $8f$  is  $1.992 \pm 0.114$  (s.d.) Å; that in  $4c$  is  $2.072 \pm 0.096$  Å. Thus the  $A$  site is somewhat larger and slightly less distorted than the  $B$  site. For the present paper, the most important feature of the pseudobrookite structure is that the two sites are sufficiently similar to allow considerable substitutional disorder of the cations occupying them. As in the spinels, we can recognize two limiting distributions, the normal,  $(A)_{4c}(B_2)_{8f}O_5$  and

TABLE 1. Enthalpy of Solution of Pseudobrookite in  $3\text{Na}_2\text{O}\cdot 4\text{MoO}_3$  at  $692^\circ\text{C}$ 

$\text{Fe}_2\text{TiO}_5$ (in mg)	cal/obs	$\Delta H_{\text{sol}}$ (kcal mol <sup>-1</sup> )
46.07	-0.050	-0.26
86.06	-0.020	-0.06
114.46	$\pm 0.000$	$\pm 0.00$
43.60	-0.015	-0.08
49.25	-0.019	-0.09
AV = $-0.10 \pm 0.10$		


the inverse,  $(B)_{\text{ac}}(AB)_{\text{bf}}\text{O}_5$ , and we can anticipate that, especially at high temperature, intermediate distributions will be the rule rather than the exception.

#### Calorimetric Determination of the Enthalpy of Formation of Pseudobrookite at $692 \pm 2^\circ\text{C}$

$\text{Fe}_2\text{TiO}_5$  was prepared by ignition of a stoichiometric mixture of dried Baker Analyzed Reagent  $\text{Fe}_2\text{O}_3$  (hematite) and  $\text{TiO}_2$  (rutile) for a total of 72 hours in a platinum crucible in air at  $1350^\circ\text{C}$ , with four intermediate grindings of the sample. At the end of each firing, the sample was cooled relatively rapidly in air. The powder X-ray diffraction pattern of the product showed it to be single phase pseudobrookite.

The high temperature Calvet-type twin micro-calorimeter and the sample assembly for measuring the heat of solution of a solid oxide sample in a molten oxide solvent have been described previously (Navrotsky and Kleppa, 1968). Navrotsky and Kleppa (1967a, 1968) have shown that a sodium molybdate melt of the composition  $3\text{Na}_2\text{O}\cdot 4\text{MoO}_3$  is a suitable solvent for the calorimetric study of anatase, rutile,  $\text{Ti}^{4+}$ -containing spinels,  $\text{Fe}_2\text{O}_3$ , and  $\text{ZnFe}_2\text{O}_4$ . A similar calorimeter and essentially identical conditions were used in the present work. In each solution experiment, 50–100 mg of solute was dissolved in 10–15 g of solvent at  $692 \pm 2^\circ\text{C}$ . Two experiments each on  $\alpha\text{-Fe}_2\text{O}_3$  and  $\text{TiO}_2$  (rutile) fell within experimental error of the values of the heat of solution of these oxides reported previously by Navrotsky and Kleppa (1968). Accordingly, those values,  $+2.38$  kcal mol<sup>-1</sup> and  $-0.49 \pm 0.05$  kcal mol<sup>-1</sup> were used in the present work for the enthalpies of solution of rutile and hematite, respectively.<sup>1</sup> No difficulty was encountered in the solution

of  $\text{Fe}_2\text{TiO}_5$ , although its molar enthalpy of solution was fortuitously very close to zero, so that the heat effects actually measured were always less than 0.1 calorie in magnitude. The results of five solution experiments (Table 1) give a mean of  $-0.10 \pm 0.10$  kcal mol<sup>-1</sup>. One may then calculate, for the reaction:



$$\Delta H_{965}^\circ = +1.99 \pm 0.15 \text{ kcal mol}^{-1}$$

#### Discussion of the Stability of $\text{Fe}_2\text{TiO}_5$ and other Compounds with the Pseudobrookite Structure

##### $\text{Fe}_2\text{TiO}_5$

The calorimetric data show the enthalpy of formation of pseudobrookite from hematite plus rutile to be *positive*. This suggests that the ternary oxide is stabilized at high temperatures by a positive entropy of formation and should become unstable relative to the binary oxides at low temperatures. Such decomposition has indeed been found by Haggerty and Lindsley (1970), with an equilibrium temperature of  $565 \pm 15^\circ\text{C}$ . We can calculate the entropy of the formation reaction since at 838 K its free energy change is zero.

$$\Delta S^\circ = \frac{+1990}{838} = +2.4 \text{ cal K}^{-1} \text{ mol}^{-1} \quad (2)$$

The free energy of formation of  $\text{Fe}_2\text{TiO}_5$  from  $\text{Fe}_2\text{O}_3$  and  $\text{TiO}_2$  is then given by the equation:

$$\Delta G^\circ = +1990 - 2.4 T (T \text{ in K}) \quad (3)$$

This equation gives  $\Delta G^\circ$  with an estimated error of  $\pm 300$  cal in the range 700–1200 K, since the difference in heat capacity between reactants and products should be small at high temperatures and one can neglect any changes in cation distribution with temperature. To our knowledge, no enthalpy or free energy of formation data have been reported for  $\text{Fe}_2\text{TiO}_5$ . Heat content and standard entropy values are tabulated by Robie and Waldbaum (1968) and by Kelley (1960). From these tabulations, the entropy of formation of pseudobrookite from hematite and rutile is given in Table 2. The agreement with our value at 858 K is excellent but, we believe, may be fortuitous. The heat capacity and heat content data are to be questioned on two counts. First, the calculated entropy of formation of pseudobrookite varies rather strongly with temperature, which is somewhat surprising. If this is a real effect, it may be related to the anomalously small thermal expansion coefficients reported for pseudobrookite-type com-

<sup>1</sup> Throughout this paper, heat effects are given in calories, where 1 cal = 4.184 joule.

pounds (Bayer, 1971), or to changes in the cation distribution (see below). The data for  $MgTi_2O_5$  (Table 2) show no such anomaly, though the values of  $\Delta S^\circ$  scatter somewhat. In addition, the tabulated values do not include any contribution for the configurational entropy arising from an "inverse" or partially disordered cation distribution of  $Fe^{3+}$  and  $Ti^{4+}$  over nonequivalent octahedral sites. Waldbaum (1973) has discussed this point. If the cation distribution in  $Fe_2TiO_5$  is indeed inverse as Lind and Housley (1972) suggest, then, as Waldbaum (1973) recommends, one should add  $2R\ln 2 = 2.76 \text{ cal K}^{-1} \text{ mol}^{-1}$  to the standard entropy of pseudobrookite. This would make the entropy of formation of  $Fe_2TiO_5$  calculated from the corrected heat capacity data more positive by about  $3 \text{ cal K}^{-1} \text{ mol}^{-1}$  than the entropy we calculate at the decomposition temperature, 838 K. Assuming our calorimetric data to be correct, this discrepancy may have several causes.  $Fe_2TiO_5$  may indeed have the normal cation distribution, since the X-ray data are not totally convincing and one does not really know the site preference of  $Fe^{3+}$  compared to  $Ti^{4+}$ . With an inverse distribution at high temperatures, the  $Fe^{3+}$  and  $Ti^{4+}$  ions may possibly order on their sublattice at lower temperatures, producing local order or even a superstructure. If this ordering occurs gradually over a range of temperature, it might not be detected as such in the heat capacity measurements, but the solid would not have much zero point entropy. The kinetics of such an ordering process probably cannot be estimated on the basis of current knowledge. Lastly, a systematic error is possible in the third law entropy of  $Fe_2TiO_5$  (or even of  $Fe_2O_3$  or  $TiO_2$ ). The heat capacity of  $Fe_2TiO_5$  was measured only down to 50 K (Todd and King, 1953), and the extrapolation to 0 K may produce greater uncertainty than previously thought (Waldbaum, 1974, personal communication). In addition, problems associated with the magnetic entropy of oxides containing transition metal ions with partially filled  $d$  shells may cause this discrepancy.

Regardless of the details of the third law entropy of  $Fe_2TiO_5$ , this work has clearly established a positive enthalpy of formation for pseudobrookite from the oxides, which is compensated by a positive entropy of formation, resulting in the stability of  $Fe_2TiO_5$  at high temperature only.

### $M^{3+}_2TiO_5$

The known thermodynamic data for some other compounds with the pseudobrookite structure are summarized in Table 3. Two other  $M^{3+}_2TiO_5$

TABLE 2. Lattice Entropies (Calorimetric Entropies) of Formation of  $Fe_2TiO_5$  and  $MgTi_2O_5$  from the Oxides

$T, K$	$TiO_2^a$	$MgO^a$	$Fe_2O_3^a$	$Fe_2TiO_5^a$	$\Delta S_T^\circ$	$MgTi_2O_5^b$	$\Delta S_T^\circ$
	$S_T^\circ$	$S_T^\circ$	$S_T^\circ$	$S_T^\circ$		$S_T^\circ$	
298	12.04	6.44	20.89	37.40	+4.47	30.40	-0.12
800	27.85	16.98	51.64	81.75	+2.26	71.65	-1.03
1200	34.98	21.93	66.69	102.45	+0.78	91.33	-0.56
1600	40.24	25.53	76.52	117.60	+0.84	106.71	-0.70

a. Source of data, R. A. Robie and D. R. Waldbaum, U.S. Geol. Survey Bull. 1259 (1968).

b. Data for  $MgTi_2O_5$  from S. S. Todd, J. Amer. Chem. Soc. **74**, 4669 (1952) and R. L. Orr and J. P. Coughlin, J. Amer. Chem. Soc. **74**, 3186 (1952).

c.  $\text{cal K}^{-1} \text{ mol}^{-1}$

pseudobrookites,  $Ga_2TiO_5$  and  $Al_2TiO_5$ , are even less stable than  $Fe_2TiO_5$ ; their decompositions, observed by differential thermal analysis, occur at higher temperature with markedly exothermic effects. It is hard to envision that lattice effects alone could produce enough entropy to stabilize these energetically unfavorable phases, so these data argue for configurational disorder in those pseudobrookites as well. Quantitative calorimetric study of these compounds is planned.

### $M^{2+}Ti_2O_5$

The  $M^{2+}Ti_2O_5$  compounds present an analogous picture; thermodynamic data are summarized in Table 3.  $CoTi_2O_5$ ,  $FeTi_2O_5$ , and  $MgTi_2O_5$  are stable only at high temperature, the assemblage rutile plus  $MTiO_3$  being stable at low temperature. The compounds  $NiTi_2O_5$  and  $MnTi_2O_5$  are apparently never stable with respect to  $MTiO_3$  and  $TiO_2$ , but estimates of their free energies of formation have been obtained from the thermodynamics of extensive solid solutions in some ternary  $AO-BO-TiO_2$  systems (Evans and Muan, 1971a, b). The instability of  $NiTi_2O_5$  probably stems from the loss of ligand field stabilization of  $Ni^{2+}$  in the distorted octahedral sites of the pseudobrookite structure; a similar factor is probably partly responsible for the instability of  $NiSiO_3$  and  $NiGeO_3$  pyroxenes (Navrotsky, 1971b). The instability of  $MnTi_2O_5$  suggests that  $Mn^{2+}$  may be somewhat too large for sites in the pseudobrookite structure.

The existence of  $CoTi_2O_5$ ,  $FeTi_2O_5$ , and  $MgTi_2O_5$  as high temperature phases only is consistent with positive entropies of formation from the oxides, coupled with enthalpies of formation close to those of the corresponding ilmenite analogs. Since both  $FeTi_2O_5$  and  $MgTi_2O_5$  have somewhat disordered cation distributions (Lind and Housley, 1972; also, see below), and since the equilibrium degree of disorder

TABLE 3. Thermodynamics of Formation of Compounds with Pseudobrookite Structure from the Component Oxides

	$\Delta G_f^\circ$ (at K) kcal mol <sup>-1</sup>	$\Delta H_f^\circ$ (at K) kcal mol <sup>-1</sup>	$\Delta S_f^\circ$ (at K) cal K <sup>-1</sup> mol <sup>-1</sup>	Decomposition
Fe <sub>2</sub> TiO <sub>5</sub>	0 (838 ± 15) <sup>a</sup>	+1.99 ± 0.15 (965) <sup>b</sup> very small <sup>l</sup>	+ 2.4 <sup>c</sup>	Fe <sub>2</sub> O <sub>3</sub> + TiO <sub>2</sub> below 838 K <sup>a</sup>
FeTi <sub>2</sub> O <sub>5</sub>	-4.3 ± 0.1 (1573) <sup>d</sup>			FeTiO <sub>3</sub> + TiO <sub>2</sub> below 1413 ± 10 K <sup>a</sup>
high Ti <sub>3</sub> O <sub>5</sub>	-18.0 ± 1.5 (1304) <sup>e</sup>			low Ti <sub>3</sub> O <sub>5</sub> , ~500 K <sup>f</sup>
MgTi <sub>2</sub> O <sub>5</sub>	-6.8 ± 1.0 (1573) <sup>g</sup> -7.3 ± 1.0 (1673) <sup>j</sup>	[-4.45 (298)] <sup>h</sup>	[+ 1.5] <sup>l</sup>	MgTiO <sub>3</sub> + TiO <sub>2</sub> below ~823 K
CoTi <sub>2</sub> O <sub>5</sub>	-3.9 (1473) <sup>m</sup>			CoTiO <sub>3</sub> + TiO <sub>2</sub> below 1413 <sup>o</sup> ± 5 K <sup>m</sup>
Al <sub>2</sub> TiO <sub>5</sub>		endothermic <sup>l</sup>		α-Al <sub>2</sub> O <sub>3</sub> + TiO <sub>2</sub> at 1273 K <sup>l</sup>
Ga <sub>2</sub> TiO <sub>5</sub>		endothermic <sup>l</sup>		β-Ga <sub>2</sub> O <sub>3</sub> + TiO <sub>2</sub> at 1273 K <sup>l</sup>
(NiTi <sub>2</sub> O <sub>5</sub> )	-2.0 ± 0.4 (1673) <sup>j</sup>			unstable relative to NiTiO <sub>3</sub> + TiO <sub>2</sub> at all T <sup>j</sup>
(MnTi <sub>2</sub> O <sub>5</sub> )	-6.3 ± 0.8 (1523) <sup>k</sup>			unstable relative to MnTiO <sub>3</sub> + TiO <sub>2</sub> at all T <sup>k</sup>

a. S. Haggerty and D. Lindsley, *Carnegie Inst. Yearbook* **68**, 247 (1970). S. Kesson and D. H. Lindsley, personal communication.

b. This work.

c. Calculated from a. and b.,  $\Delta S_f^\circ = +1990/838$ .

d. R. E. Johnson, E. Woermann, and A. Muan, *Amer. Jour. Sci.* **271**, 278 (1971).

e. Calculated from data of R. R. Merritt and B. G. Hyde, *Phil. Trans. Roy. Soc. London* **A274**, 627 (1973) for reaction  $TiO_2 + Ti_2O_3 = Ti_3O_5$ .

f. G. Asbrink and A. Magnelli, *Acta Chem. Scand.* **21**, 1977 (1967).

g. B. Brezny and A. Muan, *Thermochim. Acta* **2**, 107 (1971).

h. K. K. Kelley, S. S. Todd, and E. G. King, *U.S. Bur. Mines Rept. Inv.* 5059 (1954). Hydrofluoric acid calorimetry.

i. Estimated from g. and h.,  $\Delta S_f^\circ = [-4450 - (-6800)]/1573$ , see text for discussion.

j. L. G. Evans and A. Muan, *Thermochim. Acta* **2**, 121 (1971).

k. L. G. Evans and A. Muan, *Thermochim. Acta* **2**, 277 (1971).

l. G. Bayer, *J. Less Common Metals* **24**, 129 (1971), decomposition temperatures do not represent reversals.

m. B. Brezny and A. Muan, *J. inorg. nucl. Chem.* **31**, 649 (1969).

is expected to increase with increasing temperature, it seems clear that these materials are "entropy stabilized" in the same sense as are copper spinels (Navrotsky and Kleppa, 1968).

In their early calorimetric work on titanates, Kelley, Todd, and King (1954) found that the formation of MgTi<sub>2</sub>O<sub>5</sub> from TiO<sub>2</sub> and MgTiO<sub>3</sub> is endothermic by 1.0 kcal at 298 K. They noted that structural

disorder in this material, then of unknown structure, could cause its stabilization at high temperature.

We have several independent means for estimating the entropy change,  $\Delta S^\circ$ , associated with the decomposition:

MTi<sub>2</sub>O<sub>5</sub> (pseudobrookite structure)



The preliminary data of Kesson and Lindsley (1974, unpublished) for the decomposition of karrooite to geikelite and rutile gave a pressure-temperature slope,  $\partial P/\partial T$  of about 23.4 bar/deg. Since  $\Delta V$  for this transition is  $-5.39$  cc/mol at atmospheric conditions (volume data from Robie and Waldbaum, 1968, and Lind and Housley, 1972), we can estimate from the Clausius-Clapeyron equation that  $\Delta S^\circ = 23.4 \times -5.39 \times 0.0242 = -3.0$  cal  $K^{-1}$ . Evans and Muan (1971a) have determined the standard free energies of formation from the oxides of  $MgTi_2O_5$  and  $MgTiO_3$  to be  $-7.3 \pm 0.8$  and  $-5.1 \pm 0.5$  kcal  $mol^{-1}$  at  $1400^\circ C$ , respectively. Thus for decomposition Reaction (4),  $\Delta G^\circ = 0$  at  $550^\circ C$  and  $+2.2$  kcal at  $1400^\circ C$ . Since  $(\partial \Delta G^\circ/\partial T)_P = -\Delta S^\circ$ , we can calculate  $\Delta S^\circ = 2200/850 = -2.6$  cal  $K^{-1}$ . Lastly, the calorimetric data of Kelley, Todd, and King (1954) give an enthalpy for Reaction (4) at 823 K of  $-5.85 + 4.55 = -1.30$  kcal. Then the entropy change is  $-1300/823 = -1.6$  cal  $K^{-1}$ . This last calculation does not take into account any configurational entropy.

Similar calculations are possible for  $CoTi_2O_5$ . The decomposition temperature at one atmosphere occurs near  $1135^\circ C$ , and Brezny and Muan (1969) give values of free energies of formation such that for Reaction (4),  $\Delta G^\circ = -0.1$  kcal at  $1100^\circ C$  and  $+0.8$  kcal at  $1300^\circ C$ . This gives  $\Delta S^\circ = -900/200 = -4.5$  cal  $K^{-1}$ .

Johnson, Woermann, and Muan (1971) give the free energies of formation from the oxides for  $FeTiO_3$  and for  $Fe_2TiO_5$  as  $-4.3 \pm 1.0$  kcal  $mol^{-1}$  at  $1300^\circ C$ . Since decomposition to ilmenite plus rutile occurs below  $1140^\circ C$  in this system (Haggerty and Lindsley, 1970), a value close to zero for Reaction (4) at  $1300^\circ C$  is reasonable. However, the data do not permit an estimate of the entropy change for this reaction.

The calculated values of  $\Delta S^\circ$  range from  $-1.6$  to  $-4.5$  cal  $K^{-1}$  for decomposition Reaction (4) for different metals. In view of the large uncertainties arising both from uncertainties in the equilibrium measurements and calorimetric data and from the assumptions in the calculations, this scatter is not at all surprising. Rather, the data are quite consistent and point to a probable value of  $\Delta S^\circ$  of  $-3 \pm 1$  cal  $K^{-1}$ . This value looks very reasonable in light of the probable configurational disorder in the pseudobrookite structure, although it is not altogether too large in magnitude to be caused by lattice vibrational effects alone.


### Cation Distributions in $AB_2O_5$ Compounds and in the $FeTi_2O_5$ - $Ti_3O_5$ Solid Solution Series

$Fe_2TiO_5$ ,  $Al_2TiO_5$ ,  $Ga_2TiO_5$

Re-evaluation of the crystallographic data favors an inverse cation distribution for  $Fe_2TiO_5$  (Lind and Housley, 1972). The positive enthalpies of formation of these compounds and their instability at low temperature is consistent with substitutional disorder. Very probably these materials have intermediate cation distributions, which would be temperature dependent. The configuration of greatest entropy, the random distribution  $(M_{2/3}Ti_{1/3})_{4c}(M_{4/3}Ti_{2/3})_{8f}O_5$ , may be approached at high temperature. This point has been discussed in detail for spinels (Navrotsky and Kleppa, 1967b; Waldbaum, 1973), and analogous arguments hold for the pseudobrookite structure.  $Al_2TiO_5$  may be a better candidate for crystallographic study than  $Fe_2TiO_5$  because of the larger difference between the two cations in scattering factors for X-rays.

$MgTi_2O_5$ ,  $CoTi_2O_5$ , and  $FeTi_2O_5$

X-ray diffraction study of  $MgTi_2O_5$  quenched from  $1500^\circ C$  (Lind and Housley, 1972) has given a cation distribution  $(Mg_{0.684}Ti_{0.316})_{4c}(Mg_{0.316}Ti_{1.684})_{8f}O_5$ . In terms of the simple disordering model applied to spinels by Navrotsky and Kleppa (1967b), this corresponds to a degree of disorder,  $x$ , of 0.316 ( $x = 0$  for a normal,  $2/3$  for a random, and 1 for an inverse cation distribution). The interchange enthalpy for the reaction



is then given by

$$-\frac{\Delta H_{int}}{RT} = \ln \frac{x^2}{(1-x)(2-x)} \quad (6)$$

with  $\Delta H_{int} = +8.6$  kcal  $mol^{-1}$ . This value has previously been calculated by Waldbaum (1973).<sup>2</sup>


<sup>2</sup> The model used by Navrotsky and Kleppa (1967b) for cation distributions in spinels and that discussed by Waldbaum (1973) for nonconvergent disordering in melilites, pseudobrookites, and spinels, are essentially equivalent if one assumes the "lattice entropies" of Navrotsky and Kleppa (= the "calorimetric entropies" of Waldbaum) to be independent of the degree of order. Waldbaum's order parameter,  $Z$ , is equal to  $1-x$ , where  $x$  is our degree of disorder. His calculation of the difference in enthalpy between normal and inverse (ordered and antiorordered) distributions for  $MgTi_2O_5$  from the site population of a sample quenched from  $1500^\circ C$  is entirely equivalent conceptually to our calculation of interchange enthalpies for some thirteen spinels from their cation distributions, each known for one temperature.

For  $\text{FeTi}_2\text{O}_5$  quenched from  $1400^\circ\text{C}$ , Grey and Ward (1973) give a distribution, determined by Mössbauer spectroscopy,  $(\text{Fe}_{0.720}\text{Ti}_{0.280})_{4c}(\text{Fe}_{0.280}\text{Ti}_{1.72})_{8f}\text{O}_5$ . If  $\text{FeTi}_2\text{O}_5$  has all iron present as  $\text{Fe}^{2+}$  and all titanium as  $\text{Ti}^{4+}$ , which seems reasonable, then  $\Delta H_{\text{Int}} = 9.2 \text{ kcal mol}^{-1}$ , calculated from Equation (5). However, Grey and Ward suggest that the true percent of total iron in  $4c$  sites may be greater than their estimate because of difficulties in fitting the Mössbauer spectra. This would make  $\Delta H_{\text{Int}}$  more positive for  $\text{FeTi}_2\text{O}_5$ . This point is discussed further below.

#### Solid Solutions in the $\text{Fe}_{1-x}\text{Ti}_{2+x}\text{O}_5$ Series

The distribution of iron between  $A(4c)$  and  $B(8f)$  sites has been studied by Grey and Ward (1973) using Mössbauer spectroscopy. Their data can be subjected to thermodynamic analysis using the simple model applied by Navrotsky and Kleppa (1967b) to spinels and by Navrotsky (1971a) to  $(\text{Mg,Fe})\text{SiO}_3$  pyroxene solid solutions.


Consider the solid solution series  $\text{FeTi}_2\text{O}_5\text{--Ti}_3\text{O}_5$ . If one assumes that all iron is present as  $\text{Fe}^{2+}$ , and that the reduced titanium is present as  $\text{Ti}^{3+}$  only, then the solid solution series may be written as  $\text{Fe}^{2+}_{1-x}\text{Ti}^{3+}_{2x}\text{Ti}^{4+}_{2-x}\text{O}_5$ , where the mole fraction of  $\text{Ti}_3\text{O}_5$  is given by  $x$ . Calling the  $4c$  sites  $A$  and the  $8f$  sites  $B$ , we have, nominally, six site population parameters:  $\text{Fe}^{2+}_A$ ,  $\text{Ti}^{3+}_A$ ,  $\text{Ti}^{4+}_A$ ,  $\text{Fe}^{2+}_B$ ,  $\text{Ti}^{3+}_B$ ,  $\text{Ti}^{4+}_B$ , where each symbol stands for the number of moles of the given ion on the appropriate site. For the distribution of the three cations,  $\text{Fe}^{2+}$ ,  $\text{Ti}^{4+}$ , and  $\text{Ti}^{3+}$  over the two sites,  $A$  and  $B$ , we can write two independent exchange reactions which lead to two independent equilibrium constants. For the first exchange reactions,



with

$$K_1 = \frac{X_{\text{Fe}^{2+}_B} X_{\text{Ti}^{4+}_A}}{X_{\text{Fe}^{2+}_A} X_{\text{Ti}^{4+}_B}} \quad (8)$$

where each  $X$  is the mole fraction of a given ion on the specified site, and, in the simple model, approximates the activity. For the second exchange reaction,



with

$$K_2 = \frac{X_{\text{Ti}^{3+}_B} X_{\text{Ti}^{4+}_A}}{X_{\text{Ti}^{3+}_A} X_{\text{Ti}^{4+}_B}} \quad (10)$$

However, the bulk composition, charge balance, and site balance require that

$$\text{Fe}^{2+}_A + \text{Fe}^{2+}_B = 1 - x \quad (11)$$

$$\text{Ti}^{3+}_A + \text{Ti}^{3+}_B = 2x \quad (12)$$

$$\text{Ti}^{4+}_A + \text{Ti}^{4+}_B = 2 - x \quad (13)$$

and

$$\text{Fe}^{2+}_A + \text{Ti}^{3+}_A + \text{Ti}^{4+}_A = 1 \quad (14)$$

$$\text{Fe}^{2+}_B + \text{Ti}^{3+}_B + \text{Ti}^{4+}_B = 2 \quad (15)$$

Thus, for a given composition,  $x$ , there are only two independent site population parameters,<sup>3</sup> which we may pick as

$$\text{Fe}^{2+}_A = X_{\text{Fe}^{2+}_A} \quad \text{and} \quad \text{Ti}^{3+}_A = X_{\text{Ti}^{3+}_A}$$

and we may re-write our equilibrium constants as

$$K_1 = \frac{(1 - x - \text{Fe}^{2+}_A)(1 - \text{Fe}^{2+}_A - \text{Ti}^{3+}_A)}{\text{Fe}^{2+}_A(1 - x + \text{Fe}^{2+}_A + \text{Ti}^{3+}_A)} \quad (16)$$

and

$$K_2 = \frac{(2x - \text{Ti}^{3+}_A)(1 - \text{Fe}^{2+}_A - \text{Ti}^{3+}_A)}{\text{Ti}^{3+}_A(1 - x + \text{Fe}^{2+}_A + \text{Ti}^{3+}_A)} \quad (17)$$

The Mössbauer data of Grey and Ward (1973) give  $\text{Fe}^{2+}_A$  as a function of composition,  $x$ , for  $\text{FeTi}_2\text{O}_5\text{--Ti}_3\text{O}_5$  solid solution samples quenched from  $1400^\circ\text{C}$ . For pure  $\text{FeTi}_2\text{O}_5$ ,  $\text{Fe}^{2+}_A = 0.72$  from the Mössbauer data and  $\text{Fe}^{2+}_A = 0.75$  from a neutron diffraction study. This gives, from Equation (16) with  $(\text{Ti}^{3+}_A) = 0$ , and  $x = 0$ ,  $K_1 = 0.06$  and  $K_1 = 0.05$ , respectively. Knowing  $K_1$ ,  $x$ , and  $\text{Fe}^{2+}_A$ , Equations (16) and (17) can be treated as simultaneous equations in two unknowns,  $\text{Ti}^{3+}_A$  and  $K_2$ , and solved at each value of  $x$  for a value of  $\text{Ti}^{3+}_A$  (which will vary with  $x$ ) and of  $K_2$  (which will remain constant if the model holds and the data are accurate). Because Grey and Ward experienced some difficulty in fitting their Mössbauer data at compositions near  $\text{FeTi}_2\text{O}_5$ , they suggest that their value of  $\text{Fe}^{2+}_A$  for pure  $\text{FeTi}_2\text{O}_5$  may be somewhat underestimated (leading to an overestimate of  $K_1$ ). (From their data a graph of the percentage of the total iron on the  $4c$  sites *vs* composition shows a maximum; but a plot of the fraction of the  $4c$  sites occupied by Fe *vs* composition does not; see Fig. 1.) Thus, some uncertainty exists in the value chosen for  $K_1$ ; consequently, we have calculated the values of  $\text{Ti}^{3+}_A$  and of  $K_2$  for values of  $K_1$  from 0.06 to 0.01. The results of some of these calculations are shown in Table 4. Whereas the calculated values of

<sup>3</sup> Of the 5 equations 11–15, only 4 are independent.

$K_2$  show some scatter, they do not appear to vary systematically with composition,  $x$ . We may then take the average calculated value of  $K_2$ , and use it with the assumed value of  $K_1$  to then calculate back values of  $\text{Fe}^{2+}_A$  (and  $\text{Ti}^{3+}_A$ ) as functions of composition,  $x$ . Using Equations (16) and (17), curves of  $\text{Fe}^{2+}_A$  vs  $x$  for several values of  $K_1$  (and  $K_2$ ) are given in Figure 1, together with the experimental data points. In addition, the limits corresponding to a completely ordered distribution of iron corresponding to "normal"  $\text{FeTi}_2\text{O}_5$  and of a random distribution, with one third of the iron on the  $4c$  site, are shown. We can conclude the following. On the iron-poor side ( $x > \sim 0.5$ ), the calculated distribution of iron is rather insensitive to the actual values chosen for  $K_1$ . To discriminate among values of  $K_1$  which vary by a factor of six (from 0.01 to 0.06), one must look at the points with  $x < 0.5$ . For these data, and allowing that the point at  $x = 0$  should lie somewhat higher than 0.72, one sees that curves for  $K_1$  from 0.04 to 0.01 approximate the data. We do not believe that a statistical fit to the data would add much information, and would say rather that the experimental data are consistent with a value of  $K_1$  of 0.025 ( $\pm \sim 0.02$ ) and  $K_2 = 0.055$  ( $\pm 0.04$ ). Using these values and Equations (16) and (17), one can calculate  $\text{FeTi}_2\text{O}_5$  to have the distribution  $(\text{Fe}^{2+}_{0.81}\text{Ti}^{4+}_{0.19})_A$  ( $\text{Fe}^{2+}_{0.19}\text{Ti}^{4+}_{1.81})_B\text{O}_5$  and  $\text{Ti}_3\text{O}_5$  to have the distribution  $(\text{Ti}^{4+}_{0.05}\text{Ti}^{3+}_{0.95})_A(\text{Ti}^{4+}_{0.95}\text{Ti}^{3+}_{1.05})_B\text{O}_5$  at  $1400^\circ\text{C}$ . That is, the iron distribution data are quite well explained with the assumptions that  $\text{FeTi}_2\text{O}_5$  has a slightly disordered normal pseudobrookite struc-

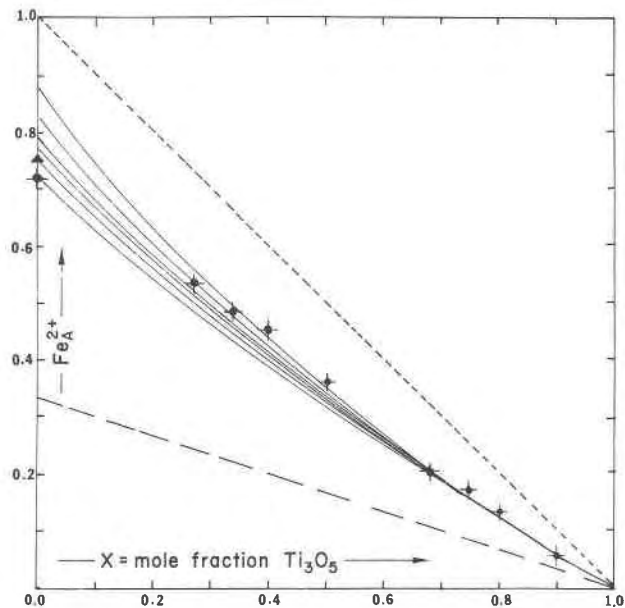


FIG. 1. Variation of fraction of  $4c$  sites occupied by iron ( $\text{Fe}^{2+}_A$ ) with mol fraction  $\text{Ti}_3\text{O}_5$ ,  $x$ . Curves, in order of increasing  $\text{Fe}^{2+}_A$  are for: (1) random distribution,  $K_1 = 1$ ; (2)  $K_1 = 0.060$ ,  $K_2 = 0.187$ ; (3)  $K_1 = 0.050$ ,  $K_2 = 0.135$ ; (4)  $K_1 = 0.040$ ,  $K_2 = 0.093$ ; (5)  $K_1 = 0.030$ ,  $K_2 = 0.061$ ; (6)  $K_1 = 0.020$ ,  $K_2 = 0.035$ ; (7)  $K_1 = 0.010$ ,  $K_2 = 0.015$ ; (8) completely ordered distribution (no  $\text{Fe}^{2+}$  on  $8f$  sites),  $K_1 = 0$ . Filled circles are cation distributions determined from Mössbauer spectra; triangle is cation distribution determined by neutron diffraction.

ture and  $\text{Ti}_3\text{O}_5$  has a slightly disordered inverse pseudobrookite structure. For  $\text{Ti}_3\text{O}_5$ , the predicted presence of  $\text{Ti}^{3+}$  and  $\text{Ti}^{4+}$  on one sublattice raises problems analogous to those in magnetite; that is, are

TABLE 4. Calculated Values of Equilibrium Constant for Exchange Reactions in  $\text{FeTi}_2\text{O}_5\text{-Ti}_3\text{O}_5$  Solid Solutions

$x$	$(\text{Fe}^{2+}_A)_{\text{exp}}$	$K_1 = 0.06$		$K_1 = 0.04$		$K_1 = 0.02$	
		$(\text{Ti}^{3+}_A)_{\text{calc}}$	$K_2$	$(\text{Ti}^{3+}_A)_{\text{calc}}$	$K_2$	$(\text{Ti}^{3+}_A)_{\text{calc}}$	$K_2$
0.27	0.534	0.223	0.232	0.296	0.089	0.377	0.024
0.34	0.488	0.271	0.258	0.343	0.112	0.423	0.035
0.40	0.453	0.297	0.313	0.371	0.142	0.454	0.047
0.50	0.361	0.437	0.201	0.498	0.105	0.565	0.040
0.68	0.201	0.678	0.102	0.715	0.061	0.756	0.027
0.75	0.170	0.689	0.150	0.732	0.089	0.779	0.039
0.80	0.132	0.743	0.134	0.782	0.081	0.823	0.036
0.90	0.061	0.845	0.106	0.874	0.066	0.906	0.031
			$K_{2\text{av}} =$		$K_{2\text{av}} =$		$K_{2\text{av}} =$
			0.187 $\pm$		0.093 $\pm$		0.035 $\pm$
			0.077		0.026		0.007

the  $Ti^{3+}$  and  $Ti^{4+}$  ions distinguishable, and can  $Ti_3O_5$  have anomalously high electrical conductivity due to the hopping of electrons over sites in the  $8f$  sublattice?

With  $K_1 = 0.025$  and  $K_2 = 0.055$ , we calculate, for the exchange Reactions (1) and (2),  $\Delta G_1 = +13.0 (\pm 5)$  kcal and  $\Delta G_2 = +10.2 (\pm 5)$  kcal. In the simple model of Navrotsky and Kleppa (1967b) these values are just the interchange enthalpies for the above reactions.

The model used has assumed (a) that the molar interchange enthalpy is independent of composition and of degree of disorder, and (b) that the entropy of forming the solid solution is simply the change in configurational entropy, calculated from the cation distribution.<sup>4</sup> In particular, this neglects effects of the change from orthorhombic to monoclinic symmetry with increasing  $Ti_3O_5$  content in the solid solution series. Since this structural change causes changes in the metal-oxygen bond lengths and angles (Grey and Ward, 1973), its neglect in the thermodynamic model is clearly an oversimplification. However, the present data do not seem to warrant equations using a larger number of parameters, and the model used appears adequate as a first approximation.

### Acknowledgments

This work was supported by NSF Grant GH 39767. Stimulating discussions with S. Kesson, D. Lindsley, and D. Waldbaum are appreciated.

### References

- BAYER, G. (1971) Thermal expansion characteristics and stability of pseudobrookite-type compounds,  $Me_3O_5$ . *J. Less Common Metals*, **24**, 129-138.
- BREZNY, B., AND A. MUAN (1969) Phase relations and stabilities of compounds in the system  $CoO-TiO_2$ . *J. Inorg. Nucl. Chem.* **31**, 649-655.
- EVANS, L. G., AND A. MUAN (1971a) Activity-composition relations and stabilities of end-member compounds in the system  $MgO-NiO-TiO_2$  in contact with metallic nickel at 1400°C. *Thermochim. Acta*, **2**, 121-134.
- GREY, I. E., AND J. WARD (1973) Activity-composition relations of solid solutions and stabilities of manganese and nickel titanates at 1250°C as derived from equilibria in the systems  $MnO-CoO-TiO_2$  and  $MnO-NiO-TiO_2$ . *Thermochim. Acta*, **2**, 277-292.
- GREY, I. E., AND J. WARD (1973) An X-ray and Mössbauer study of the  $FeTi_2O_5-Ti_3O_5$  system. *J. Solid State Chem.* **7**, 300-307.
- HAGGERTY, S. E., AND D. H. LINDSLEY (1970) Stability of the pseudobrookite ( $Fe_2TiO_5$ )-ferropseudobrookite ( $FeTi_2O_5$ ) series. *Carnegie Inst. Wash. Year Book*, **68**, 247-249.
- HAMELIN, M. (1958) The structure of the composition,  $TiO_2-Al_2O_3$ , in comparison with the pseudobrookite. *Bull. Soc. Chim. France*, **1958**, 1559-1566.
- JOHNSON, R. E., E. WOERMANN, AND A. MUAN (1971) Equilibrium studies in the system  $MgO-FeO-TiO_2$ . *Am. J. Sci.* **271**, 278-292.
- KELLEY, K. K. (1960) Contributions to the data on theoretical metallurgy XIII, high temperature heat content and entropy data for the elements and inorganic compounds. *U. S. Bur. Mines Bull.* **584**.
- , AND E. G. KING (1961) Contributions to the data on theoretical metallurgy SiV; Entropies of the elements and inorganic compounds. *U.S. Bur. Mines Bull.* **592**.
- , S. S. TODD, AND E. G. KING (1954) Heat and free energy data for titanates of iron and the alkaline earth metals. *U.S. Bur. Mines Rep. Invest.* **5059**.
- LIND, M. D., AND R. M. HOUSLEY (1972) Crystallization studies of lunar igneous rocks; crystal structure of synthetic armalcolite. *Science*, **175**, 521-523.
- NAVROTSKY, A. (1971a) The intracrystalline cation distribution and the thermodynamics of solid solution formation in the system  $FeSiO_3-MgSiO_3$ . *Am. Mineral.* **56**, 201-211.
- NAVROTSKY, A. (1971b) Thermodynamics of formation of the silicates and germanates of some divalent transition metals and of magnesium. *J. Inorg. Nucl. Chem.* **33**, 4035-4050.
- , AND O. J. KLEPPA (1967a) Enthalpy of the anatase-rutile transformation. *J. Am. Ceram. Soc.* **50**, 626.
- , AND ——— (1967b) The thermodynamics of cation distributions in simple spinels. *J. Inorg. Nucl. Chem.* **29**, 2701-2714.
- , AND ——— (1968) Thermodynamics of formation of simple spinels. *J. Inorg. Nucl. Chem.* **30**, 479-498.
- PAULING, L. (1930) The crystal structure of pseudobrookite. *Z. Kristallogr.* **73**, 97-112.
- ROBIE, R. A., AND D. R. WALDBAUM (1968) Thermodynamic properties of minerals and related substances at 298.15°K (25.0°C) and one atmosphere (1.013 bars) pressure and at higher temperatures. *U.S. Geol. Surv. Bull.* **1259**.
- TODD, S. S., AND E. G. KING (1953) Heat capacities at low temperatures and entropies at 298.16°K of titanomagnetite and ferric titanate. *J. Am. Chem. Soc.* **75**, 4547-4551.
- WALDBAUM, D. R. (1973) The configurational entropies of  $Ca_2MgSi_2O_7-Ca_2SiAl_2O_7$  melilites and related minerals. *Contrib. Mineral. Petrol.* **39**, 33-54.

Manuscript received, June 10, 1974; accepted for publication, November 8, 1974.

<sup>4</sup> This model is again essentially identical to that used by Waldbaum (1973) for the melilite solid solution series, when the assumption that the  $\Delta S = 0$  is used. Waldbaum wrote his equations for the free energy of a phase relative to the elements or the oxides; we write ours for the free energy of mixing between end members.