

Crystal chemistry and petrology of coexisting galaxite and jacobsite and other spinel solutions and solvi¹

E. J. ESSENE AND D. R. PEACOR

Department of Geological Sciences
The University of Michigan
Ann Arbor, Michigan 48109

Abstract

Galaxite ($Gx:MnAl_2O_4$) and jacobsite ($Jb:MnFe_2O_4$)-rich spinels occur together in the metamorphosed manganese deposit near Bald Knob, North Carolina. They show limited mutual solubility with 12–19% *Jb* in *Gx* and 19–22% *Gx* in *Jb*. The implied solvus is consistent with syntheses of Ishida *et al.* (1977) along the *Gx*–*Jb* pseudobinary. Refinement of the structure of one galaxite ($Gx_{85}Jb_{10}Sp_4Gh_1$) reveals that Mn is located on tetrahedral sites and Al on octahedral sites and that galaxite is therefore a normal spinel. All available data suggest that jacobsite is also a normal spinel at low temperatures, and the solvus between galaxite and jacobsite does not seem to be caused by differences in normality/inverseness. Chemical and experimental data available for $(Mg,Zn,Mg,Fe^{2+})(Fe^{3+},Al)_2O_4$ spinels suggest that the ferrites (jacobsite, franklinite, magnesioferrite and magnetite) show extensive solid solution and are separated from aluminate solid solutions (galaxite, gahnite, spinel (*s.s.*) and hercynite) by wide solvi at metamorphic temperatures.

Introduction

The manganese deposit near Bald Knob, North Carolina contains a wide range of unusual manganese minerals which have equilibrated under amphibolite facies metamorphic conditions (Winter *et al.*, 1981). The deposit was originally described by Ross and Kerr (1932). We have subsequently carried out extensive mineralogical–petrological studies of the several mineral groups occurring there (Peacor *et al.*, 1974; Winter *et al.*, 1981, in prep.; Simmons *et al.*, 1981). The spinel group minerals (galaxite and jacobsite) found at Bald Knob are relatively simple in composition and therefore serve as a source of insights into the crystal-chemical and phase relations of spinels. This paper is a description of the mineralogy and petrology of those manganese spinels.

Only a limited amount of experimental data are available regarding the nature of solvi among spinels at low to moderate temperatures. Turnock and Eugster (1962) experimentally determined the magnetite–hercynite solvus showing complete solid solution above 870°C and a wide miscibility gap below 600°C. These two spinels are largely inverse and normal, respectively. The area of complete solution probably represents a continuum of cation distributions, but the occurrence of the solvus must be related in part to ordering into the inverse versus the normal cation distribution. Experiments on the binaries

Fe_3O_4 – Fe_2TiO_4 (Vincent *et al.*, 1957; Price, 1981; Lindsley, 1981) and Fe_3O_4 – $ZnFe_2O_4$ (Valentino and Sclar, 1982) suggest that the solvus observed in natural materials must form below 500–600°C. Experiments in the systems $MnFe_2O_4$ – $MnAl_2O_4$ (Ishida *et al.*, 1977) and $ZnFe_2O_4$ – $ZnAl_2O_4$ (Carvalho, 1978) reveal extensive miscibility gaps at metamorphic temperatures of 500–700°C with the crest of the solvi located at 900–1100°C. Experiments of Muan *et al.* (1972) on the ternaries $FeAl_2O_4$ – Fe_2TiO_4 – $FeCr_2O_4$ and $MgAl_2O_4$ – Mg_2TiO_4 – $MgCr_2O_4$ show solvi extending to more than 1300°C between the aluminate and titanate species but with complete solution at $T > 1000^\circ C$ engendered with addition of 30–40% of the chromites. There are no experiments on the join $MgAl_2O_4$ – Fe_3O_4 and one must turn to natural occurrences to estimate the form of this solvus.

Surprisingly few examples exist of observations on naturally occurring two-phase spinels despite the fact that such observations may have the advantage of demonstrating equilibrium cation distributions at relatively low temperatures. Studies of minerals in lunar basalts have revealed high-temperature solvi in the system $(Mg, Fe^{2+})Al_2O_4$ – $(Mg, Fe^{2+})Cr_2O_4$ – $(Mg, Fe^{2+})_2TiO_4$ (Haggerty, 1971, 1972a,b,c; El Goresy *et al.*, 1972, 1976; Nehru *et al.*, 1974). Muir and Naldrett (1973) and Berg (1976) analyzed coexisting spinels and magnetites from igneous rocks, finding a wide miscibility gap in the system Fe_3O_4 – $MgAl_2O_4$ which contracts with increasing Cr in solid solution. Plaksenko (1980) describes incipient exsolution in chrome spinels from ultramafic rocks. Kuno

¹ Contribution No. 375 from the Mineralogical Laboratory, Department of Geological Sciences, the University of Michigan.

(1960) and Bowman (1978) report analytical data on metamorphic spinel-magnetite pairs which equilibrated at ca. 700°C and show even less mutual solution. The system $MgAl_2O_4$ - Fe_3O_4 appears to have a wide, symmetrical miscibility gap from temperatures of less than 1100°C. Manganese and zinc spinels have both ferrite and aluminate representatives in nature but the solubilities involving Mn vs. Zn, and Al vs. Fe^{3+} are still poorly understood. Franklinite ($ZnFe_2O_4$) has extensive miscibility at high temperatures with jacobsonite ($MnFe_2O_4$) and magnetite (Deer *et al.*, 1963). Frondel and Klein (1965) and Carvalho (1978) have described exsolution blebs of gahnite in franklinite consistent with the existence of a low-temperature solvus in this system. We have examined many franklinite samples and found one with similar blebs with compositions of a complex aluminate ($Mg, Zn, Mn, Fe^{2+})(Al, Fe^{3+})_2O_4$ in a matrix of franklinite ($(Zn, Mn)Fe_2O_4$); the phases are thus multi-component and do not contribute to general conclusions regarding solvi.

Galaxite ($MnAl_2O_4$) is known from only a few localities and only limited data are available on its miscibility with other spinels. Hirowatari (1969) and Chopin (1980) have reported the existence of two-phase jacobsonite-galaxite

mixtures. At Bald Knob galaxite is restricted to carbonate-rich rocks undersaturated in silica which also contain tephroite or the Mn-humites—manganhumite, alleghanyite or sonolite (Ross and Kerr, 1932; Winter *et al.*, 1983). The color of galaxite is variable in thin-section and ranges from golden-yellow to deep red to red-black apparently as a function of iron content. When deep red it is easily confused with associated pyrophanite but that mineral is anisotropic and has higher reflectivity. While routinely examining polished sections, we noticed a second ten to twenty micron-sized opaque phase with higher relief and higher reflectivity coexisting with galaxite. Qualitative microprobe analysis suggested that it was jacobsonite with some Al in solution. The mineral assemblages noted in each sample are:

635: manganhumite-sonolite-spessartine-kutnahorite-galaxite-kellyite-jacobsonite

BK6: alleghanyite-kutnahorite-galaxite-jacobsonite-pyrophanite-alabandite-cattierite-kellyite-stilpnomelane-fluorapatite

BK11: alleghanyite-kutnahorite-galaxite-jacobsonite-pyrophanite-alabandite-cattierite-caryopilite-kellyite

Table 1. Electron microprobe analyses of jacobsonite and galaxite from near Bald Knob, N. C.

Sample Mineral	635 Gx	BK6-1 Gx	Jb	BK6-2 Gx	Jb	BK11 Gx	Jb	BK14 Gx	BK22 Gx	Jb
Oxide Wt%										
TiO ₂	<0.05	<0.05	0.37	0.67	9.4	0.13	0.38	<0.05	<0.05	0.34
Al ₂ O ₃	56.3	49.4	10.4	49.3	6.2	44.5	8.14	50.5	45.1	9.7
V ₂ O ₃	0.14	0.14	0.66	0.87	0.58	n.d.	n.d.	0.20	0.25	0.39
¹ Fe ₂ O ₃	46.0	14.5	57.6	12.5	44.2	18.7	59.5	9.0	16.6	57.6
¹ FeO	0.0	1.4	3.3	5.8	5.9	0.7	0.5	5.9	1.4	3.1
MnO	39.1	33.5	29.8	32.1	33.5	36.3	32.1	30.4	35.7	29.2
ZnO	0.43	0.97	<0.05	<0.05	0.62	n.d.	n.d.	0.61	0.10	0.13
CoO	0.25	0.70	0.21	0.62	0.71	n.d.	n.d.	1.07	0.84	0.62
MgO	0.83	1.47	0.02	1.30	0.19	1.44	0.03	0.92	0.53	<0.05
sum	101.7	102.1	102.4	103.2	101.3	101.8	100.6	98.6	100.5	101.1
Cations/3 Cations										
Ti	0.00	0.00	0.01	0.01	0.26	0.00	0.01	0.00	0.00	0.01
Al	1.90	1.77	0.43	1.70	0.27	1.57	0.35	1.80	1.62	0.38
V	0.00	0.00	0.01	0.02	0.01	n.d.	n.d.	0.00	0.00	0.01
¹ Fe ³⁺	0.10	0.23	1.55	0.27	1.20	0.42	1.62	0.20	0.38	1.46
¹ Fe ²⁺	0.00	0.03	0.10	0.14	0.18	0.02	0.02	0.15	0.04	0.09
Mn	0.95	0.86	0.90	0.79	1.03	0.92	0.99	0.77	0.92	0.83
Zn	0.01	0.02	0.00	0.00	0.02	n.d.	n.d.	0.01	0.00	0.00
Co	0.00	0.02	0.00	0.01	0.02	n.d.	n.d.	0.03	0.02	0.02
Mg	0.04	0.07	0.00	0.06	0.01	0.07	0.01	0.04	0.02	0.00

¹Fe²⁺/Fe³⁺ calculated to yield 0=4
n.d. = not determined

BK14: manganhumite–sonolite–kutnahorite–galaxite–(jacobsite) – alabandite – stilpnomelane – caryopilite – kellyite–fluorapatite

BK22: alleghanyite–kutnahorite–galaxite–jacobsite–alabandite–cattierite–cobaltite–kellyite–fluorapatite.

A consideration of the solubility limits of galaxite and jacobsite as represented by those Bald Knob samples, their cation distribution and the nature of the solvus between them comprises the subject matter of this note.

Chemical analysis

Electron microprobe analyses were obtained under operating conditions of an accelerating potential of 15 kV, an emission current of 150 nA, a sample current of 0.01 μ A and using digitized beam current. Standards used were synthetic TiO_2 , Al_2O_3 , V_2O_5 , Mn_2O_3 , MgAl_2O_4 , Fe_2O_3 , Co_3S_4 , ZnS and NiS . Spectrometer data were corrected for atomic number, fluorescence, absorption and drift effects using the program EMPADR VII written by Rucklidge and Gasparrini (1969). Analyses of the spinels are given in Table 1. The totals deviate by 2–3% from 100% when Fe^{2+} is estimated by the equation $\text{Fe}^{2+} = \frac{1}{2}(\text{Al} + \text{V} + \Sigma\text{Fe}) + \frac{4}{3}(\text{Ti}) - \frac{1}{2}(\text{Mn} + \text{Mg} + \text{Zn} + \text{Co})$ generating four oxygens for spinels normalized to three cations. While imperfect, these estimates and totals are judged adequate for the purposes of this paper.

The jacobsite and galaxite show a relatively symmetrical miscibility gap with about 12–20% mutual solution of each component. Only minor amounts of additional components are generally present in solid solution. We have plotted our analyses along with those reported by Hirowatari (1969) and Chopin (1980) in the system MnAl_2O_4 – MnFe_2O_4 – MgAl_2O_4 – MgFe_2O_4 (Fig. 1). They define a reasonable miscibility gap when the analyses are combined with the binary experiments of Kwestroo (1959) and of Ishida *et al.*, (1977). Ross and Kerr's (1932) analysis of Bald Knob galaxite falls slightly within the inferred solvus. Few other analyses are available which are reasonably represented by the composition space of Figure 1. Most jacobsites have either Fe_3O_4 , ZnFe_2O_4 , or Mn_3O_4 in solid solution. Spinel analyses are also plotted in the composition space MnAl_2O_4 – MnFe_2O_4 – ZnAl_2O_4 – ZnFe_2O_4 (Fig. 2). A relatively symmetrical solvus separating Mn, Zn aluminates from Mn, Zn ferrites can be inferred by combining our data with the binary experiments and observations of Ishida *et al.* (1977) and of Carvalho (1978). Ignoring the substantial Fe^{2+} , the titanian jacobsite of BK-6 is plotted in the composition space MnAl_2O_4 – MnFe_2O_4 – Mn_2TiO_4 for comparison with data of Fukuoka and Hirowatari (1980) and of Fukuoka (1981) (Fig. 3). It can be seen that there is substantial solution between MnFe_2O_4 and Mn_2TiO_4 at metamorphic temperatures. It is anticipated that a new spinel mineral species with dominant Mn_2TiO_4 will eventually be found in a metamorphosed titaniferous manganese deposit.

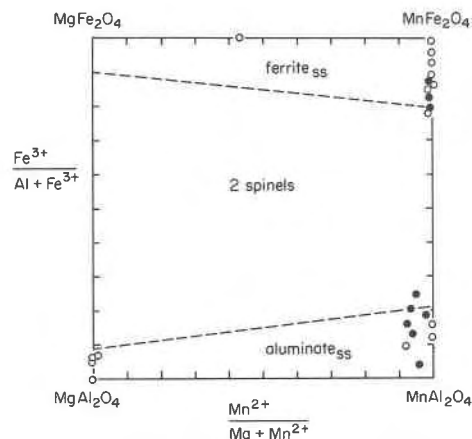


Fig. 1. The composition space MnAl_2O_4 – MnFe_2O_4 – MgAl_2O_4 – MgFe_2O_4 with spinel analyses plotted. Closed circles: data on Bald Knob spinels; open circles: data from other occurrences. References: Ross and Kerr (1932) Stillwell and Edwards (1951), Lee (1968), Kuno (1960), Deer *et al.*, (1962), Berg (1976), Bowman (1978), Carvalho (1978), Chopin (1978), Fukuoka and Hirowatari (1980), Fukuoka (1981). Spinel with >0.05 Zn, Fe^{2+} , Mn^{3+} or Ti per four oxygens are excluded.

Cation ordering

A yellow-colored galaxite from Bald Knob, sample no. 635 (collection of D. R. Peacor), was analyzed and found to contain approximately 92 mol% component MnAl_2O_4 (Table 1), making it the purest naturally occurring galaxite which we have been able to obtain. Because we wished to determine its cation distribution in detail, crystals were separated for single-crystal X-ray diffraction. Film data confirmed the existence of extinctions as consistent with the usual space group for spinels, $Fd\bar{3}m$. The unit translation was determined to be $a = 8.181(2)\text{Å}$

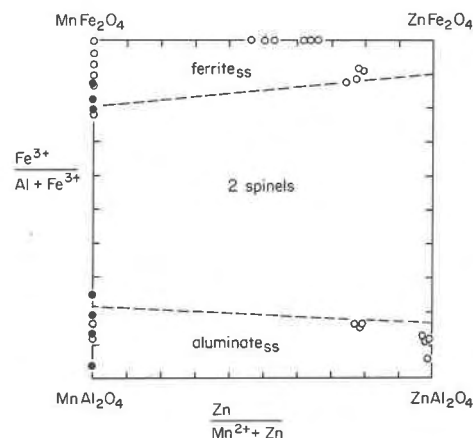


Fig. 2. The composition space MnAl_2O_4 – MnFe_2O_4 – ZnAl_2O_4 – ZnFe_2O_4 with spinel analyses plotted. Symbols and references the same as for Fig. 1, with additional references: Palache (1935), Kayupova *et al.* (1970), Vogel *et al.*, (1976). Spinel with >0.05 Mg, Fe^{2+} , Mn^{3+} or Ti per four oxygens are excluded.

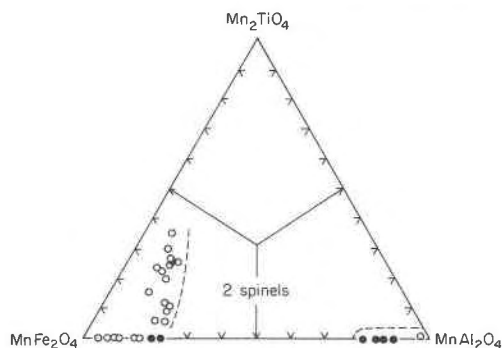


Fig. 3. The composition space MnAl_2O_4 – MnFe_2O_4 – Mn_2TiO_4 with spinel analyses plotted. Symbols and references the same as for Figure 1. Spinel with $>0.30 \text{ Fe}^{2+}$, or 0.10 Mg , Zn , Mn^{3+} are excluded.

using data from an internally standardized powder diffractometer pattern.

Three-dimensional intensity data were measured using a Supper-Pace automated system, employing measurement of background on both sides of a peak and graphite monochromated $\text{MoK}\alpha$ radiation. The crystal used was an octahedron with an average edge length of approximately 0.11 mm which was obtained from the same area of the same specimen as the analyzed material. Data were corrected for Lorentz-polarization and absorption ($\mu = 66.5 \text{ cm}^{-1}$) effects. Up to six symmetry-related intensities were measured to a $\sin\theta$ limit of 0.60 . Following averaging of symmetry related values, the final data set consisted of 82 structure amplitudes. Of these, one (044) was subsequently found to be seriously affected by extinction and excluded from the refinement, and seven were below minimum observable values. Refinement was carried out using the program *RFINE* (Finger and Prince, 1975) using neutral form factors of Doyle and Turner (1968). Form factors for Al and Mn were used both for the octahedral and tetrahedral sites, the small amount of Mg being represented by the Al form factor and the iron and traces of Co, Ti, V, and Zn by the Mn form factor. Refinement was carried out by varying the single oxygen coordinate, anisotropic temperature factors and the occupancies of the tetrahedral and octahedral sites. The final conventional unweighted R-value, excluding unobserved data, is 2.8%. Structure factors are listed in Table 2² and final atomic parameters in Table 3.

Occupancy values for the tetrahedral site are $0.11(3)$ and 0.89 for the Al and Mn form factors, respectively, and 1.03 and -0.03 for the octahedral site. The latter values are consistent with complete ordering of Al on the octahedral site, and those for the tetrahedral site also imply the presence of some Al, taking into consideration

that each form factor represents minor amounts of elements other than Al and Mn. The total Al (plus Mg) required by these occupancies is slightly greater than that indicated by the analysis ($1.94 \text{ Al} + \text{Mg}$, per 8 O). However, there is some variation in composition of different crystals within the specimen serving as a source for the crystal used for the diffraction data. The results of the refinement of the occupancy values can therefore be interpreted as consistent with a complete, or nearly complete normal cation distribution, with Al and Mn occupying only the octahedral and tetrahedral sites, respectively.

The cation ordering is also confirmed by the cation-oxygen distances which are $1.991(1)$ and $1.927(1) \text{ \AA}$ for the tetrahedral and octahedral sites respectively. This result differs somewhat from the study of Greenwald *et al.* (1954) who found that synthetic MnAl_2O_4 is approximately 70% normal. This exemplifies the importance of using natural materials to determine low-temperature ordering parameters where possible as synthetic materials may have metastable states of order due in part to relatively rapid rates of formation.

Prediction of cation ordering in jacobsite is somewhat uncertain. While some writers (Verwey and Heilman, 1947; Gorter, 1950, 1954; McClure, 1957; Dunn *et al.*, 1965; Burns, 1970; Strunz, 1970) regard jacobsite as probably inverse, measurements of synthetic materials show that it is approximately 80–90% normal (Hastings and Corliss, 1956; Harrison *et al.*, 1957; Butler and Büsser, 1962; Lotgering, 1964; Sawatzky *et al.*, 1967, 1969; Lotgering and Van Diepen, 1973; Brabers and Klerk, 1974). Jacobsite has extensive solution with frank-

Table 3. Atomic parameters for galaxite

Tetrahedrally coordinated site	
occupancy	$0.89(3) \text{ Mn} + 0.11 \text{ Al}$
temperature factor	$\beta_{11} = 0.00717(15)$ $B_{\text{eq}} = 0.46 \text{ \AA}^2$
M-O	$1.991(1) \text{ \AA}$
Octahedrally coordinated site	
occupancy	$1.03(2) \text{ Al} - 0.03 \text{ Mn}$
temperature factors	$\beta_{11} = 0.00105(16)$ $\beta_{12} = -0.00018(8)$ $B_{\text{eq}} = 0.28 \text{ \AA}^2$
M-O	$1.927(1) \text{ \AA}$
Oxygen	
x	$0.2655(2)$
temperature factors	$\beta_{11} = 0.00230(19)$ $\beta_{12} = -0.00011(15)$ $B_{\text{eq}} = 0.62 \text{ \AA}^2$

² To obtain a copy of Table 2, order Document AM-83-216 from the Business Office, Mineralogical Society of America, 2000 Florida Ave. N.W., Washington, D.C., 20009. Please remit \$1.00 in advance for microfiche.

linite (ZnFe_2O_4) and studies show that these solutions are normal or close to normal (Knoavitch *et al.*, 1963; König 1966; König and Chol, 1968; Morrish and Clark, 1975; Korneev *et al.*, 1975; Vogel *et al.*, 1976). Jacobsite also has extensive solution with magnetite at high temperatures (Mason, 1947) but the cation ordering in these solutions is unknown. Natural jacobites are most likely to be normal spinels; the solvus between jacobite and galaxite (like that for franklinite and gahnite) involves two normal spinels and is not driven by differences in cation distributions.

Status of jacobite


The status of jacobite as a distinct mineral has been questioned by Mason (1943, 1947) and by Van Hook and Keith (1958), who described jacobite as an intermediate member of the magnetite-high hausmannite series based on experiments along the join Fe_3O_4 - Mn_3O_4 . Because jacobite is a normal spinel, $(\text{Mn}^{2+})^{\text{IV}}(\text{Fe}^{3+})_2^{\text{VI}}\text{O}_4$, it is *not* a disordered solid solution $(\text{Mn}_{.33}^{2+}\text{Fe}_{.67}^{3+})^{\text{IV}}(\text{Mn}_{.67}^{2+}\text{Fe}_{.33}^{3+})^{\text{VI}}\text{O}_4$ nor a compound obtained by combination of $\frac{1}{3}\text{Mn}_3\text{O}_4$ and $\frac{2}{3}\text{Fe}_3\text{O}_4$, $(\text{Mn}_{.33}^{3+}\text{Fe}_{.67}^{3+})^{\text{IV}}(\text{Mn}_{.33}^{2+}\text{Fe}_{.67}^{2+}\text{Mn}_{.33}^{3+}\text{Fe}_{.67}^{3+})^{\text{VI}}\text{O}_4$. It is a unique end-member with distinctive cationic valency and distribution. Mason's (1943) definitions of spinels on the Mn_3O_4 - Fe_3O_4 join should be discarded and jacobite accepted as a valid mineral.

Petrology

Galaxite should only be stable in undersaturated rocks for it should react to form spessartine and an aluminosilicate in the presence of quartz:




The instability of galaxite with quartz is an important factor in explaining its scarcity. Reactions of galaxite with other manganese silicates may be considered:





Galaxite-rhodonite/pyroxmangite and tephroite-spessartine assemblages are both known at Bald Knob, and three samples (BK4, BK8, BK18) have all four phases apparently coexisting. Reaction (2) is apparently bridged by assemblages at Bald Knob presumably due to variable solid solution and could be of great use in metamorphosed manganese deposits once determined. Reaction (3) will limit spessartine-rhodochrosite to lower temperatures and/or CO_2 -rich fluids, but the reaction cannot be located until adequate thermodynamic or experimental data are available for these phases.

Reactions involving jacobite are complicated by possible variations in the oxidation state of iron and perhaps manganese. Jacobsite will be reduced to a manganwüstite at oxygen fugacities about one order of magnitude higher

than the reduction of magnetite to wüstite (Ulrich *et al.*, 1966; Shchepetkin and Chufarov, 1972). Jacobsite will also oxidize to hematite_{ss} and a more Mn-rich spinel:



The upper limit of oxygen fugacity permitted for jacobite is about two orders of magnitude higher than that for magnetite-hematite (Ono *et al.*, 1971; Pelton *et al.*, 1979). Thus jacobite has the same wide oxidation and reduction stability as magnetite but shifted to somewhat more oxidizing conditions. This is in qualitative agreement with the oxygen fugacities estimated at Bald Knob by Winter *et al.* (1981). More complicated reactions involving manganese silicates can be inferred for jacobite:



but present thermodynamic data are inadequate for calculation of these reactions. Winter *et al.* (1981) have shown that the Bald Knob rocks with jacobite and galaxite have formed at relatively low oxygen fugacity (near quartz-fayalite-magnetite) and high sulfur fugacity (near pyrrhotite-pyrite) and with $X_{\text{CO}_2} = 0.5$ for $T = 575^\circ\text{C}$ and $P = 5$ kbar. These conditions should be consistent with the left-hand side of reactions (4) and (5) since jacobite is found with pyroxmangite at Bald Knob. Other more complicated oxidation-reduction-carbonation-hydration reactions may be balanced for various humites, pyroxenoids, carbonates and jacobite. Such reactions probably buffered the ratios of various fluid species during metamorphism of the jacobite-bearing rocks.

Note added in press:

The wt.% Fe_2O_3 of Gx635 in Table 1 should read 4.6 wt.%.

Acknowledgments

We wish to thank W. B. Simmons Jr. who first introduced us to the Bald Knob deposit, and G. A. Winter and J. W. Geissman who aided in some of the analyses. We also thank W. C. Bigelow and his staff of the University of Michigan Microbeam Laboratory for providing facilities for analysis.

References

- Berg, J. H. (1976) Metamorphosed mafic and ultramafic rocks in the contact aureoles of the Nain complex, Labrador, and the miscibility gap between spinel and magnetite in natural Cr-Al-Fe³⁺-Ti spinels. Geological Society of America Abstracts with Programs, 8, 773.
- Bowman, J. R. (1978) Origin of C-O-H skarn fluids in the Black Butte aureole. Ph.D. thesis, University of Michigan, Ann Arbor.
- Brabers, V. A. M. and Klerk, J. (1974) The infrared absorption spectrum and the inversion degree of manganese ferrite. Solid State Communications, 14, 613-615.
- Burns, R. G. (1970) Mineralogical applications of crystal field theory. Cambridge University Press, Cambridge, England.

- Butler, S. R. and Büssem, W. R. (1963) Magnetization of Mn ferrite. *Journal of Applied Physics*, 34, 1754 (1957).
- Carvalho, A. V. III (1978) Gahnite-franklinite intergrowths at the Sterling Hill zinc-deposit, Sussex County, New Jersey; an analytical and experimental study. M.S. thesis, Lehigh University, Bethlehem, Penn.
- Chopin, C. (1978) Les parageneses reduites on oxydes de concentrations manganisifères des schistes lustrés de Haute-Maurienne (Alpes françaises). *Bulletin de Minéralogie*, 101, 514–531.
- Deer, W. A., Howie, R. A. and Zussman, J. (1962) *Rock-forming Minerals*. Vol. 5. Nonsilicates. Longmans, Green and Co. Ltd., London.
- Doyle, P. A. and Turner, P. S. (1968) Relativistic Hartree-Fock X-ray and electron scattering factors. *Acta Crystallographica*, A24, 390–397.
- Dunn, T. M., McClure, D. C. and Pearson, R. G. (1965) Some aspects of crystal field theory. Harper and Row, New York.
- El Goresy, A., and Ramdohr, P., and Taylor, L. A. (1972) Fra Mauro crystalline rocks: mineralogy, geochemistry and subsolidus reactions of opaque minerals. *Proceedings of the Third Lunar Science Conference*, 333–350.
- Finger, L. W. and Prince, E. (1975) A system of Fortran IV computer programs for crystal structure calculations. National Bureau of Standards, U.S. Technical Note, 854.
- Frondel, C. and Klein, C. (1965) Exsolution in franklinite. *American Mineralogist*, 50, 1670–1680.
- Fukuoka, M. (1981) Mineralogical and genetical study on alabandite from the manganese deposits of Japan. *Memoirs of the Faculty of Science, Kyushu University, Series D, Geology*, 24, 207–251.
- Fukuoka, M. and Hirowatari, F. (1980) Chemical compositions of jacobssites from the bedded manganese ore deposits. *Science Reports, Department of Geology, Kyushu University*, 13, 239–249.
- Gorter, E. W. (1950) Magnetization in ferrites. Saturation magnetization of ferrites with spinel structure. *Nature* 165, 7098–800.
- Gorter, E. W. (1954) Saturation magnetization and crystal chemistry of ferrimagnetic oxides. *Phillips Research Reports*, 9, 403–443.
- Greenwald, S., Pickart, S. and Grannis, F. (1954) Cation distribution and factors of certain spinels containing Ni, Mn, Co, Al Ga, and Fe. *Journal of Chemical Physics*, 22, 1597–1600.
- Haggerty, S. E. (1971) Compositional variations in lunar spinels. *Nature: Physical Sciences*, 233, 156–160.
- Haggerty, S. E. (1972a) Apollo 14: subsolidus reduction and compositional variations of spinels. *Proceedings of Third Lunar Science Conference*, 305–332.
- Haggerty, S. E. (1972b) Luna 16: an opaque mineral study and systematic examination of compositional variations of spinels from Mare Fecunditatis. *Earth and Planetary Science Letters*, 13, 328–352.
- Haggerty, S. E. (1972c) Solid solutions, subsolidus reduction and compositional characteristics of spinels in some Apollo 15 basalts. *Meteoritics*, 7, 353–370.
- Harrison, F. W., Osmond, W. P. and Teale, R. W. (1957) Cation distribution and magnetic moment of manganese ferrite. *Physical Review*, 106, 865–866.
- Hastings, J. M. and Corless, L. M. (1956) Neutron diffraction study of manganese ferrite. *Physical Review*, 104, 328–331.
- Hirowatari, F. (1969) Jacobsite with inclusions of exsolved galaxite from Kiruagi mine, Japan. *Science Reports, Faculty of Science, Kyushu University, Geology*, 9, 159–166.
- Ishida, K., Momoi, H. and Hirowatari, F. (1977) Hydrothermal synthesis of the jacobssite-galaxite join. *Kyushu Daigaku Rigakubu Kenkyu Hokoku, Chishitsugaku*, 12, 289–297.
- Kayupova, M. M., Marzuvanov, V. L. and Polyakova, T. P. (1970) Zinc-containing jacobssite from Atasui deposits in central Kazakhstan. *Doklady akademii Nauk USSR Earth Science Section*, 192, 110–113.
- Konakovitch, Ya. and Saksonov, Y. G. (1963) A neutron diffraction study of a manganese-zinc ferrite. *Soviet Physics. Crystallography*, 8, 18–22.
- König, U. (1966) Kationenverteilung und Magnetische Momente der Ionen der Tetraeder- und Oktaederplätze des Mangan-zinkferrites $Mn_{.55}Zn_{.37}Fe_{2.08}O_4$. *Zeitschrift für Angewandte Physik*, 22, 103–106.
- König, U. and Chol, G. (1968) X-ray and neutron diffraction in ferrites of $Mn_xZn_{1-x}Fe_2O_4$ type. *Journal of Applied Crystallography*, 1, 124–126.
- Korneev, E. V., and Belov, A. F., Khimich, T. A., Belov, V. F. and Kolesnikov, I. M. (1975) Crystallochemical and magnetic properties of manganese-zinc ferrites. *Russian Journal of Physical Chemistry*, 49, 1547–1550.
- Kuno, H. (1960) Notes on rock-forming minerals. (16) Titaniferous pyroxene, spinel and magnetite in hornfels from Sisakazima Islands, Japan. *Journal of the Geological Society of Japan* 66, 626.
- Kwestroo, W. (1959) Spinel phase in the system $MgO-Fe_2O_3-Al_2O_3$. *Journal of Inorganic and Nuclear Chemistry*, 9, 65–70.
- Lindsley, D. H. (1981) Some experiments pertaining to the magnetite-ulvöspinel miscibility gap. *American Mineralogist*, 66, 759–762.
- Lotgering, F. K. (1964) Semiconduction and cation valencies in manganese ferrites. *Journal of Physics and Chemistry of Solids*, 25, 95–103.
- Lotgering, F. K. and Van Diepen, A. M. (1973) Valences of manganese and iron ions in cubic ferrites as observed in paramagnetic Mössbauer spectra. *Journal of Physics and Chemistry of Solids*, 34, 1369–1377.
- Mason, B. (1943) Alpha-vredenburgite: *Geologiska Föreningens i Stockholm, Forhandlingar*, 65, 263–270.
- Mason, B. (1947) Mineralogical aspects of the system $Fe_3O_4-Mn_3O_4-ZnFe_2O_4$. *American Mineralogist*, 32, 426–511.
- McClure, D. S. (1957) The distribution of transition metal cations in spinels. *Journal of Physics and Chemistry of Solids*, 3, 311–317.
- Morrish, A. H. and Clark, P. E. (1975) High-field Mössbauer study of Mn-Zn ferrites. *Physical Review B* 11, 278–286.
- Muan, A., Hauck, J. and Löfall, T. (1972) Equilibrium studies with a bearing on lunar rocks. *Proceedings of the Third Lunar Science Conference (Supplement 3, Geochimica et Cosmochimica Acta)*, 1, 185–196.
- Muir, J. E. and Naldrett, A. J. (1973) A natural occurrence of two-phase chromium-bearing spinels. *Canadian Mineralogist*, 11, 930–939.
- Ono, K., Ueda, T., Ozaki, T., Ueda, Y., Yamaguchi, A. and Moriyama, J. (1971) Thermodynamic study of the iron-manganese-oxygen system. *Journal of the Japan Institute of Metals*, 35, 757–763.
- Palache, C. (1935) The minerals of Franklin and Sterling Hill, Sussex Co., N. J. U. S. Geological Survey Professional Paper, 180, 135 pp.

- Peacor, D. R., Essene, E. J., Simmons, W. B. Jr., and Bigelow, W. C. (1974) Kellyite, a new Mn-Al member of the serpentine group from Bald Knob, N. C. and new data on grovesite. *American Mineralogist*, 59, 1153-1156.
- Pelton, A. D., Schmalzried, H. and Sticher, J. (1979) Thermodynamics of Mn_3O_4 - Co_3O_4 , Fe_3O_4 - Mn_3O_4 , and Fe_3O_4 - Co_3O_4 spinels by phase diagram analysis. *Berichte Bunsengesellschaft für Physikalische Chemie* 83, 241-252.
- Plaksenko, A. N. (1980) On the nature of the non-homogeneity in accessory chromespinelids from ultrabasites of Lowmanonsky differentiated intrusion. *Zapiski Vsesoiuznoe mineralogicheskoe obshchestvo* 114, 91-98.
- Price, G. D. (1981) Subsolidus phase relations in the titanomagnetite solid solution series. *American Mineralogist*, 66, 751-758.
- Ross, C. S. and Kerr, P. F. (1932) The manganese minerals of Bald Knob, N. C. *American Mineralogist*, 17, 1-18.
- Rucklidge, J. C. and Gasparrini, E. L. (1969) Specifications of a complete program for processing electron microprobe data: EMPADR VII. Dept. of Geology, University of Toronto, unpublished circular.
- Sawatzky, G. A., van der Wonde, F., and Morrish, A. H. (1967) Note on cation distribution of $MnFe_2O_4$. *Physics Letters*, A, 25, 147-148.
- Sawatzky, G. A., van der Wonde, F., Morrish, A. H. (1969) Mössbauer study of several ferrimagnetic spinels. *Physical Review*, Series 2, 187, 747-757.
- Shchepetkin, A. A. and Chufarov, G. I. (1972) The dissociation of solid solutions of oxides in M-Fe-O systems under equilibrium conditions. *Russian Journal of Inorganic Chemistry*, 17, 792-794.
- Simmons, W. B., Jr., Peacor, D. R., Essene, E. J. and Winter, G. A. (1981) Manganese minerals of Bald Knob, N. C. *Mineralogical Record*, 167-171.
- Stilwell, F. L. and Edwards, A. B. (1951) Jacobsite from the Tamworth District of New South Wales. *Mineralogical Magazine*, 212, 538-541.
- Strunz, H. (1970) *Mineralogische Tabellen*. Akademische Verlagsgesellschaft, Geest und Portig K.-G. Leipzig.
- Takeda, H., Miyamoto, M. and Reid, A. M. (1974) Crystal-chemical control of element partitioning for coexisting chromite-ulvospinel and pigeonite-augite in lunar rocks. *Proceedings of the Fifth Lunar Science Conference*, 1, 727-741.
- Turnock, A. C. and Eugster, H. P., (1962) Fe-Al oxides: phase relationships below 1000°C. *Journal of Petrology*, 3, 533-565.
- Ulrich, K. H., Bohnenkamp, K. and Engell, H. J. (1966) Equilibrium of magnetite-hausmannite mixed crystals and wüstite-manganese (II) oxide mixed crystals and oxygen and the reduction of magnetite-hausmannite mixed oxides. *Zeitschrift für Physikalische Chemie, Neue Folge*. Frankfurt 51, 35-49.
- Vincent, E. A., Wright, J. B., Chevallier, R. and Mathieu, S. (1957) Heating experiments on some natural titaniferous magnetites. *Mineralogical Magazine*, 31, 624-655.
- Valentino, A. J. and Sclar, C. B. (1982) Experimental study of the magnetite ($FeFe_2O_4$)-franklinite ($ZnFe_2O_4$) solid-solution series. *EOS*, 63, 470.
- Van Hook, H. J. and Keith, M. L. (1958) The system Fe_3O_4 - Mn_3O_4 . *American Mineralogist*, 43, 68-83.
- Verwey, E. J. W. and Heilman, E. L. (1947) Physical properties and cation arrangement of oxides with spinel structure 1. Cation arrangement in spinels. *Journal of Chemical Physics*, 15, 174-180.
- Vogel, R. H., Evans, B. J. and Swartzendruber, L. J. (1976) Intra-site cation ordering and clustering in natural Mn-Zn ferrites. *AIP Conference Proceedings*, 34, 125-127.
- Winter, G. A., Essene, E. J. and Peacor, D. R. (1981) Carbonates and pyroxenoids from the manganese deposit near Bald Knob, N. C. *American Mineralogist*, 66, 278-289.
- Winter, G. A., Essene, E. J. and Peacor, D. R. (1983) Mn-humites from Bald Knob, North Carolina: mineralogy and phase equilibria. *American Mineralogist*, in press.

*Manuscript received, November 9, 1981;
accepted for publication, November 4, 1982.*