

## Structure refinement of calzirtite from Jacupiranga, Brazil

WILLIAM SINCLAIR<sup>1</sup>

Research School of Earth Sciences, Australian National University,  
P.O. Box 4, Canberra, A.C.T. 2600, Australia

RICHARD A. EGGLETON

Department of Geology, Australian National University, P.O. Box 4,  
Canberra, A.C.T. 2600, Australia

GEORGE M. McLAUGHLIN

Research School of Chemistry, Australian National University,  
P.O. Box 4, Canberra, A.C.T. 2600, Australia

### ABSTRACT

The crystal structure of calzirtite,  $\text{Ca}_2\text{Zr}_5(\text{Ti}_{1.5}\text{Nb}_{0.29}\text{Fe}_{0.18})\text{O}_{16}$ ,  $a = 15.094(2)$ ,  $c = 10.043(2)$  Å, space group  $I4_1/acd$ ,  $Z = 8$  has been refined by the method of least-squares using 1327 reflections to an  $R$  index of 0.040 ( $R_w = 0.047$ ). The data were collected on a four-circle diffractometer using graphite-monochromated  $\text{MoK}\alpha$  radiation. The cations occupy fluorite-type positions in the tetragonal cell. They are ordered into planes parallel to (010) and form two layers containing Ti, Ca, and Zr sandwiched between layers of 7- and 8-coordinated Zr. At the 8-coordinate site, Zr shows a statistical displacement off special position 8(b). Corner-linked  $\text{TiO}_6$  octahedra form chains that zig-zag parallel to  $c$ . The results are in agreement with those obtained from a powder refinement of synthetic calzirtite by Rossell (1982, *Acta Crystallographica*, B38, 593–595).

### INTRODUCTION

Calzirtite,  $\text{Ca}_2\text{Zr}_5\text{Ti}_2\text{O}_{16}$ , occurs in several localities in association with zirconolite ( $\text{CaZrTi}_2\text{O}_7$ ), a key compound in the nuclear waste ceramic SYNROC (Ringwood et al., 1979a, 1979b). The first occurrence of calzirtite was reported by Zdorik et al. (1961) in metasomatic calcite-forsterite-magnetite rocks from an alkaline-ultrabasic massif in Eastern Siberia. Pyatenko and Pudovkina (1961) showed the structure to be an anion-deficient superstructure phase closely related to fluorite arrangement. A recent refinement of synthetic calzirtite (Rossell, 1982) using powder diffraction data resulted in a change in the O2 oxygen position and significant cation ordering at the cation positions. The results of Rossell were not available to us at the start of this work.

### CRYSTAL-STRUCTURE ANALYSIS

Chemical analyses of calzirtite from Jacupiranga, Brazil (Melcher, 1966), and Kaiserstuhl, Germany, were done using an energy-dispersive electron-microprobe operating at 15 kV, 3-nA current, and count time of 100 s. Data reduction was done by the method outlined by Ware (1981). The samples from Kaiserstuhl carbonatite contain more Nb than the Jacupiranga samples.

Single-crystal Weissenberg and precession photographs of samples from Brazil showed a tetragonal cell with Laue

symmetry  $4/mmm$ ; the systematic absences  $hkl$ ,  $h + k + l = 2n$ ; for  $hk0$ ,  $h = 2n$ ; for  $h0l$ ,  $l = 2n$ ; and for  $hhl$ ,  $2h + l = 4n$  define the space group uniquely as  $I4_1/acd$ .

The crystal used for data collection was a transparent, pale-orange cube. The crystal was mounted on an automatic Picker FACS-1 four-circle diffractometer, with the  $c$ -axis approximately parallel to the  $\phi$  axis of the machine. Unit-cell dimensions and crystal orientation matrix were obtained by least-squares refinement of the setting angles of twelve centered reflections having  $2\theta$  values close to  $50^\circ$ . Crystal data are given in Table 1.

Intensity data were measured by the  $\theta$ - $2\theta$  continuous-scan technique with a scan speed of  $2^\circ \text{ min}^{-1}$  ( $2\theta$ ) and range from  $0.8^\circ$  below the  $K\alpha_1$  to  $0.8^\circ$  above the  $K\alpha_2$  peak for the reflection concerned. Stationary 10-s background counts were made at each end of the scan range and were assumed to vary linearly between these extremes. Three standard reflections, 600, 060, 004 did not show any significant variations in intensity throughout the course of the experiment. Intensities were collected for 4017 reflections having  $2\theta$  values between  $3$  and  $80^\circ$  for all positive  $hkl$  except those that were absent from the  $I$ -centering condition. The data were corrected for absorption (De Meulenaer and Tompa, 1965), sorted and averaged and reduced to structure amplitudes in the usual way. Reflections for which  $I/\sigma(I) < 3.0$  were classed as unobserved. A total of 1327 unique observed reflections were available for subsequent structural analysis. The statistical discrepancy value for this data set  $R_s (= \sum \sigma/\sum |F_o|)$ , where  $\sigma$  is

<sup>1</sup> Present address: BHP Melbourne Research Laboratories, Melbourne, Australia.

Table 1. Analytical and crystal data for calzirtite

	1	2	Crystal Data
Nb <sub>2</sub> O <sub>5</sub>	8.5	4.4	a 15.094(2) Å
TiO <sub>2</sub>	10.5	13.3	c 10.043(2)
ZrO <sub>2</sub>	67.0	68.2	v 2288(1) Å <sup>3</sup>
*FeO	1.6	1.5	D <sub>c</sub> 5.24 gcm <sup>-3</sup>
CaO	11.5	12.4	Z 8
ε	99.1	99.8	μ 6.79 mm <sup>-1</sup>
Nb	0.59	0.29	Rad/Mon. Mo/Gr.
Ti <sup>4+</sup>	1.20	1.50	Crystal
Fe <sup>2+</sup>	0.18	0.18	Size 0.075mm
ε	1.97	1.97	Space
Zr <sup>4+</sup>	5.03	5.03	Group I4 <sub>1</sub> /acd
Ca <sup>2+</sup>	1.93	2.00	R(final) 0.040
O <sup>2-</sup>	16	16	R <sub>w</sub> (final) 0.049

+ 1: Kaiserstuhl, Germany; 2: Jacupiranga, Brazil; all crystal data for Jacupiranga sample. \* Iron as FeO assumed.

the error contribution to  $|F_o|$  from counting statistics alone) is 0.025. Transmission factors for  $F_o$  calculated by the analytical method of De Meulenaer and Tompa (1965), varied from 0.790 to 0.822.

Computer programs for data reduction and structure solution are part of the ANUCRYS package implemented on the UNIVAC 1100/42 ANU by Drs. P. O. Whimp and D. Taylor.

### STRUCTURE SOLUTION AND REFINEMENT

Scattering factors for neutral atoms were taken from *International Tables for X-ray Crystallography*, volume 4 (1974) and were corrected for both real and imaginary anomalous components. The refinement was carried out

Table 3. Interatomic distances (Å) and O-M-O angles (°) of Jacupiranga calzirtite

M1	-05	2.034(3)	2x	O1 - M2 - O1 <sup>1</sup>	88.4(2)
	05	2.073(3)	2x	O3	98.4(1)
	04	2.247(3)	2x	O3 <sup>1</sup>	88.4(1)
	04	2.704(3)	2x	O4	94.6(1)
Mean		2.265			
M1	-M1	0.539(1)		O1 - M2 - O3	88.4(1)
				O3 <sup>1</sup>	98.4(1)
				O4 <sup>1</sup>	94.6(1)
M2	-01	1.888(2)	2x	O3 - M2 - O4	93.1(1)
	03	1.952(3)	2x	O4 <sup>1</sup>	79.7(1)
	04	1.988(3)	2x		
Mean		1.943			
M3	-02	2.303(3)	2x	O3 - M2 - O4	79.7(1)
	05	2.415(3)	2x	O4 <sup>1</sup>	93.1(1)
	01	2.532(3)	2x		
	03	2.557(3)	2x	O4 - M2 - O4 <sup>1</sup>	82.6(2)
Mean		2.452			
				M2-M2 <sup>1</sup>	3.524(1)
M4	-05	2.056(3)		M4 <sup>1</sup> -M2	3.809(1)
	02	2.086(2)		M2 <sup>1</sup> -M4	3.863(1)
	03	2.142(3)		M4 <sup>1</sup> -M4 <sup>1</sup>	3.867(1)
	04	2.170(3)		M4 <sup>1</sup> -M4 <sup>1</sup>	3.867(1)
	04	2.178(3)		O1-O4, O1-O4 <sup>1</sup>	2.848(4)
	03	2.182(3)		O4-O3, O4 <sup>1</sup> -O3 <sup>1</sup>	2.860(4)
	05	2.183(3)		O1-O3, O1-O3 <sup>1</sup>	2.908(4)
Mean		2.142		O4-O3 <sup>1</sup> , O4 <sup>1</sup> -O3	2.982(4)
				O4-O2, O4 <sup>1</sup> -O2	3.088(4)
				O3-O2, O3 <sup>1</sup> -O2	3.084(4)

Table 2. Atomic coordinates and thermal parameters for Jacupiranga calzirtite

ATOM	SITE	OCCUPANCY	X	Y	Z	Req. (Å <sup>2</sup> )
M(1)	16(f)	0.5 Zr	0.01264(4)	0.01264(4)	1/4	0.93
M(2)	16(f)	0.75Ti+0.1Fe+0.15Nb	0.16809(4)	0.16809(4)	1/4	0.50
M(3)	16(f)	1.0 Ca	0.33281(5)	0.33281(5)	1/4	0.56
M(4)	32(g)	1.0 Zr	0.16152(2)	0.01780(2)	0.48578(4)	0.37
O(1)	16(e)	1.0 Oxy	1/4	0.2130(3)	1/8	0.87
O(2)	16(e)	1.0 Oxy	1/4	0.4303(3)	1/8	0.56
O(3)	32(g)	1.0 Oxy	0.2433(2)	0.0776(2)	0.3309(3)	0.93
O(4)	32(g)	1.0 Oxy	0.1135(2)	0.0827(2)	0.1236(3)	0.95
O(5)	32(g)	1.0 Oxy	0.0655(2)	0.0795(2)	0.6193(3)	0.84
ATOM	U11*	U22	U33	U12	U13	U23
M(1)	0.0140(11)	0.0140(11)	0.0073(6)	-0.0064(12)	0.0011(10)	-0.0011(10)
M(2)	0.0065(5)	0.0065(5)	0.0060(4)	0.0001(6)	-0.0006(5)	0.0006(5)
M(3)	0.0069(6)	0.0069(6)	0.0074(6)	0.0001(8)	-0.0007(7)	0.0007(7)
M(4)	0.0047(12)	0.0041(2)	0.0051(2)	0.0002(5)	0.0010(4)	-0.0001(2)
O(1)	0.008(5)	0.014(2)	0.011(3)	0	0	-0.003(3)
O(2)	0.008(4)	0.008(2)	0.006(2)	0	0	-0.000(2)
O(3)	0.017(10)	0.009(2)	0.010(2)	-0.006(4)	0.001(3)	-0.000(2)
O(4)	0.014(10)	0.011(2)	0.011(2)	-0.002(5)	-0.000(4)	0.000(2)
O(5)	0.017(10)	0.008(2)	0.007(2)	-0.002(4)	-0.001(3)	-0.000(2)

$$*\exp[-2\pi^2(U_{11}h^2a^2+U_{22}k^2b^2+U_{33}l^2c^2+2U_{12}hka^*b+2U_{13}hla^*c+2U_{23}k1b^*c^*)]$$

using the full-matrix least-squares program SFLS (Prewitt, 1966), which minimizes the function  $\sum w(|F_o| - k|F_c|)^2$ , where  $k$  is an overall scale factor and  $w$  is the weight of an observation taken as unity in the initial stages and later as  $w(hkl) = 1/\sigma_2^2$  where  $\sigma_2 = \{\sigma_1^2 + 0.25[0.03(F_o)]^2\}^{1/2}$ .

Refinement using the coordinates and site occupancies of Pyatenko and Pudovkina (1961) was unsuccessful. A second refinement using only the cation positions and occupancies converged to an  $R$  index of 0.25. A three-dimensional difference Fourier map showed that the O2

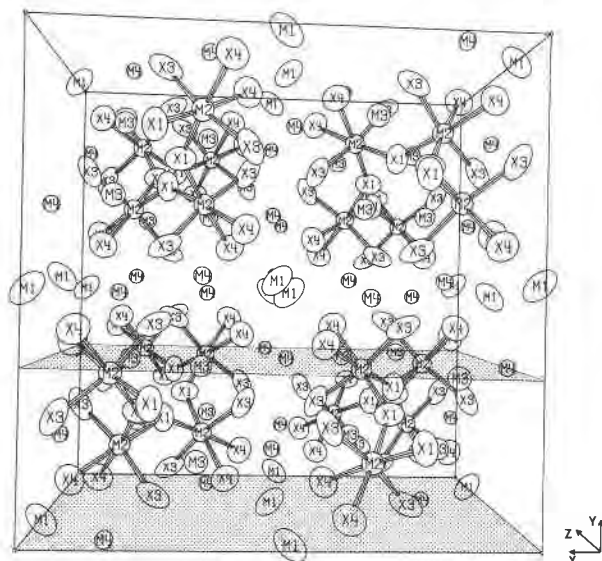


Fig. 1. ORTEP II (Johnson, 1976) drawing of calzirtite showing all metal atoms in the unit cell. The octahedral coordination spheres are also illustrated. Two planes are shaded at  $y = 0$  and  $y = \frac{1}{2}$ . M1 = Zr; M2 = Ti, Fe, Nb; M3 = Ca; M4 = Zr; X1–X5 = oxygen.

oxygen was incorrectly placed by Pyatenko and Pudovkina (1961), the site occupancies were not correct, and there was positional disorder at the M1 site. Adjustment of site-occupancies, splitting of the M1 site and refinement of all variables resulted in an  $R$  index of 0.049 for an isotropic thermal model.

Conversion to anisotropic temperature factors reduced the  $R$  and  $R_w$  indices to 0.040 and 0.049 respectively. A correction for secondary extinction (Zachariasen, 1963) was also included and refined to a final value of  $4.6(2) \times 10^{-4}$ . An analysis of  $w(|F_o| - |F_c|)$  vs.  $F_o$  and  $\sin \theta/\lambda$  showed no systematic trends, indicating an adequate weighting scheme. The standard deviation of an observation of unit weight was 1.76.

A difference Fourier map calculated at this stage showed

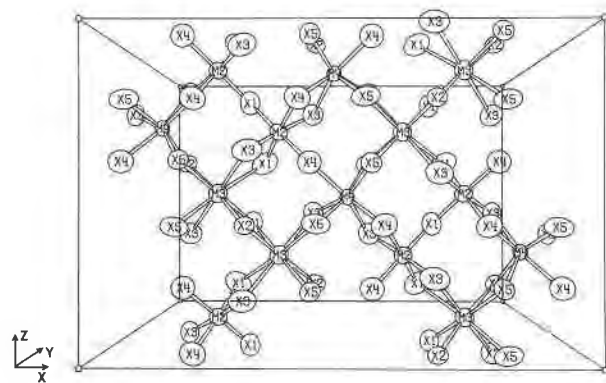


Fig. 2. Diagram of the plane of metal atoms shaded in Fig. 1 at  $y = \frac{1}{2}$ . The completed coordination spheres of the cations have been included.

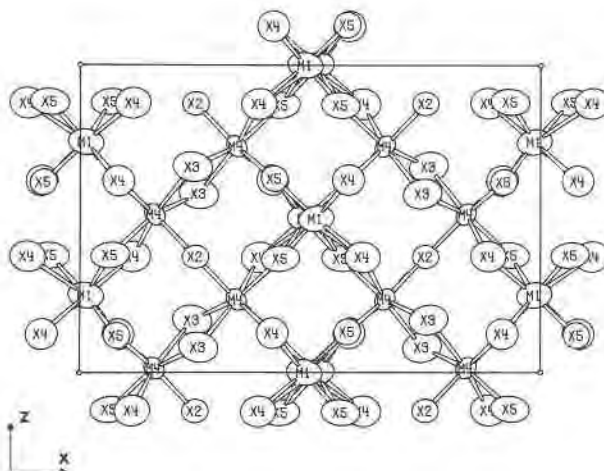


Fig. 3. Drawing of the plane of metal atoms at  $y = 0$  in Fig. 1. The coordination spheres of the cations are also shown.

the largest residual peak to be  $2e \text{ \AA}^{-3}$  at (0.03, 0.03, 0.25). Final atomic parameters are presented in Table 2. Bond lengths and angles are given in Table 3, and structure factors are listed in Table 4.<sup>2</sup>

#### DESCRIPTION OF THE STRUCTURE

This structure is a tetragonal distortion of the fluorite-type structure (Fig. 1). The cations are ordered into planes parallel to (010) and form two layers (at  $y = \frac{1}{4}$  and  $\frac{1}{2}$ ) containing M2, M3, and M4 cations sandwiched between layers of M1 + M4 cations (at  $y = 0$  and  $\frac{1}{2}$ ). Figure 2 shows the coordination scheme of the shaded layer at  $y = \frac{1}{2}$  (Fig. 1). The plane consists of empty and filled M4(Zr) polyhedra in seven-fold coordination with oxygen, alternating with two rows of M2 octahedra and M3 cubes parallel to (001). The interstices in the M2 and M3 rows are also vacant sevenfold polyhedra. Two layers of M2,

<sup>2</sup> To obtain a copy of Table 4 order Document AM-86-304 from the Business Office, Mineralogical Society of America, 1625 I Street, N.W., Suite 414, Washington, D.C. 20006. Please remit \$5.00 in advance for the microfiche.

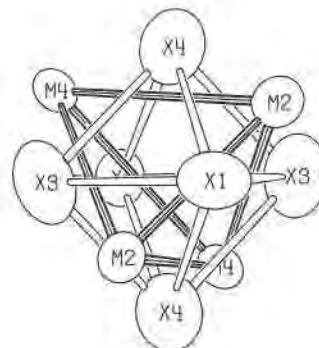


Fig. 4. Illustration of the cation tetrahedron (M2, M4) and anion octahedron (X1, X2, X3, X4) surrounding the vacant anion site at  $(\frac{1}{4}, 0.5833, \frac{1}{2})$ .

M3, and M4 cations combine to form zig-zag strings of M2 octahedra along  $z$  (Fig. 1). In the unit cell, 16 Ti(Nb,Fe) atoms occupy the octahedral M2 sites, 16 Ca atoms occupy the cubic M3 sites, and the seven-cornered diminished cubes (M4) contain 32 Zr atoms. A second type of layer at  $y = 0$  consists of empty and full (M1) cubes containing Zr atoms and vacant and full (M4) sevenfold polyhedra in rows parallel to (001) (Fig. 3).

An unusual feature of calzirtite is the splitting of the M1(Zr) site within a distorted cube of oxygen atoms. Bond-strength calculations by Rossell (1982) showed Zr in triangular prismatic coordination to be significantly underbonded, the two more distant anions of the cube being required to satisfy the bond-strength requirements on Zr. However, the cause of the cation displacement remained unresolved. Using the more precise data of this study, bond-strength sums around Zr show that this cation is underbonded (3.80 valence units) in triangular prismatic (sixfold) coordination and fully bonded in eightfold coordination (4 valence units using the bond-strength parameters of Brown and Wu, 1976).

The metal atoms surrounding the anion vacancy at  $(\frac{1}{4}, 0.5833, \frac{1}{8})$  in calzirtite form a tetrahedron and the oxygen anions form an octahedron (Fig. 4). In the ideal fluorite arrangement for calzirtite, metal-metal and oxygen-oxygen distances would be approximately 3.55 Å. The cation-cation distances of calzirtite (Table 3) are larger by 0.3 Å and the oxygen-oxygen lengths are smaller by 0.5 Å. This type of relaxation is also found in zirconolite (Rossell, 1980) and in many other anion-deficient fluorite-related superstructures (Thornber et al., 1968,  $Zr_3Sc_2O_{13}$ ,  $Zr_3Sc_4O_{12}$ ; Thornber and Bevan, 1970,  $Zr_3Yb_4O_{12}$ ; Allpress et al., 1975,  $CaHf_4O_9$ ; Rossell and Scott, 1975,  $CaHf_7O_{16}$ ; Rossell, 1976; Rossell, 1979,  $Ln_3MO_7$  where  $Ln = REE, Y, \text{ or } Sc$  and  $M = Nb, Sb, \text{ or } Ta$ ).

#### ACKNOWLEDGMENT

We are grateful to Drs. V. M. Oversby and J. Keller for providing the samples of Jacupirangite from Brazil and carbonatite from Kaiserstuhl, respectively.

#### REFERENCES

Allpress, J.G., Rossell, H.J., and Scott, H.G. (1975) Crystal structures of the fluorite-related phases  $CaHf_4O_9$  and  $CaHf_7O_{16}$ . *Journal of Solid State Chemistry*, 14, 264–273.  
Brown, I.D., and Wu, K.K. (1976) Empirical parameters for cal-

culating cation-oxygen bond valences. *Acta Crystallographica*, B32, 1957–1959.  
De Meulenaer, J., and Tompa, H. (1965) The absorption correction in crystal structure analysis. *Acta Crystallographica*, 19, 1014–1018.  
International tables for X-ray crystallography, volume IV. (1974) Kynock Press, Birmingham.  
Johnson, C.K. (1976) ORTEP II A Fortran thermal ellipsoid plot program for crystal structure illustrations. Report ORNL-5138. Oak Ridge National Laboratory, Tennessee.  
Melcher, G.C. (1966) The carbonatites of Jacupiranga, São Paulo, Brazil. In O.F. Tuttle and J. Gittins, Eds. *Carbonatites*, 169–181. Wiley-Interscience, New York.  
Prewitt, C.T. (1966) SFLS report ORNL-TM-305. Oak Ridge National Laboratory, Tennessee.  
Pyatenko, Yu.A., and Pudovkina, Z.V. (1961) The crystal structure of calzirtite: A new derivative structure of  $CaF_2$ - $CeO_2$  type. *Kristallografiya*, 6, 196–199.  
Ringwood, A.E., Kesson, S.E., Ware, N.G., Hibberson, W., and Major, A. (1979a) Immobilization of high level nuclear reactor wastes in SYNROC. *Nature*, 278, 219–223.  
——— (1979b) The SYNROC process: A geochemical approach to nuclear waste immobilization. *Geochemical Journal*, 13, 141–165.  
Rossell, H.J. (1976) Crystal structures of some fluorite-related  $M_2O_{12}$  compounds. *Journal of Solid State Chemistry*, 19, 103–111.  
——— (1979) Fluorite-related phases  $Ln_3MO_7$ ,  $Ln = \text{rare earth, Y or Sc, } M = Nb, Sb \text{ or } Ta$ . II. Structure determination. *Journal of Solid State Chemistry*, 27, 115–122.  
——— (1980) Zirconolite—A fluorite-related superstructure. *Nature*, 283, 282–283.  
——— (1982) Calzirtite—A fluorite-related superstructure. *Acta Crystallographica*, B38, 593–595.  
Rossell, H.J., and Scott, H.G. (1975) The structure of the fluorite-related phases  $Ca_2Hf_7O_{16}$ . *Journal of Solid State Chemistry*, 13, 345–350.  
Thornber, M.R., and Bevan, D.J.M. (1970) Mixed oxides of the type  $MO_2$  (fluorite)- $M_2O_3$ . IV. Crystal structures of the high- and low-temperature forms of  $Zr_3Yb_4O_{12}$ . *Journal of Solid State Chemistry*, 1, 536–544.  
Thornber, M.R., Bevan, D.J.M., and Graham, J. (1968) Mixed oxides of the type  $MO_2$  (fluorite)- $M_2O_3$ . III. Crystal structures of the intermediate phases  $Zr_3Sc_2O_{13}$  and  $Zr_3Sc_4O_{12}$ . *Acta Crystallographica*, B24, 1183–1190.  
Ware, N. (1981) Computer programs and calibration with the PIPS technique for quantitative electron-probe analysis using a Si(Li)-drifted detector. *Computers and Geosciences*, 7, 167–184.  
Zachariasen, W.H. (1963) The secondary extinction correction. *Acta Crystallographica*, 16, 1139–1144.  
Zdorik, T.B., Sidorenko, G.A., and Bykova, A.V. (1961) A new titanozirconate of calcium-calzirtite. *Doklady Akademii Nauk SSSR*, 137, 443–446.

MANUSCRIPT RECEIVED FEBRUARY 22, 1985

MANUSCRIPT ACCEPTED JANUARY 14, 1986