

Raman spectroscopic study of the solubility behavior of H₂ in the system Na₂O-Al₂O₃-SiO₂-H₂

ROBERT W. LUTH, BJORN O. MYSEN, DAVID VIRGO

Geophysical Laboratory, Carnegie Institution of Washington, 2801 Upton Street, N.W., Washington, D.C. 20008, U.S.A.

ABSTRACT

The solubility of hydrogen in liquids quenched at high pressure in the system Na₂O-Al₂O₃-SiO₂-H₂ was studied by Raman spectroscopy. Hydrogen fugacities (f_{H_2}) were controlled with double-capsule techniques with the f_{H_2} buffered by the iron-wüstite (IW) assemblage.

In Raman spectra of H₂-bearing glasses along the joins Na₂O-SiO₂ and NaAlO₂-SiO₂, bands assigned to the stretching vibrations of molecular H₂ (at ~4125 cm⁻¹) and of OH groups (at ~3580 cm⁻¹) are present. The low-frequency region of the Raman spectra of the Na₂O-SiO₂ glasses changes only subtly upon dissolution of H₂. The low-frequency region of the spectra of NaAlO₂-SiO₂-H₂ glasses, however, is identical to spectra of H₂O-bearing glasses of the same composition that were studied by Mysen and Virgo (1986). There were no bands at ~2250 cm⁻¹ attributable to the presence of vibrations from Si-H species, nor at ~1300 cm⁻¹ from Na-H vibrations, although the expected intensity of this band would be very low because of the ionic nature of the Na-H bond. A band at ~1635 cm⁻¹ attributed to bending vibrations of molecular H₂O is detectable in the aluminosilicate glasses quenched from ≥1400°C.

At the f_{H_2} of the IW buffer, Si from the silicate interacts with the Pt container and H₂ to form a Pt-Si alloy and H₂O. The H₂O thereby formed dissolves in the silicate liquid as molecular H₂O and as OH, causing the bands observed at ~1635 cm⁻¹ and at ~3580 cm⁻¹, respectively, in the Raman spectra of the glasses. The formation of Pt-Si alloys at temperatures as low as 1100°C at the f_{H_2} of the IW buffer, as found in this study, indicates that H₂O-free conditions cannot be attained within Pt capsules under such reducing conditions. Consequently, the effects of volatiles such as H₂ or CH₄-H₂ mixtures on phase equilibria determined at reducing conditions must be re-evaluated in light of possible formation of H₂O at the experimental conditions.

INTRODUCTION

The study of the interactions of volatiles with silicate liquids has been an active area of research for many years (e.g., Goranson, 1931; Tuttle and Bowen, 1958; Wasserburg, 1957; Yoder and Tilley, 1962; Luth et al., 1964; Eggler, 1975; Mysen and Boettcher, 1975; Mysen, 1976; Burnham, 1979; Mysen et al., 1980; Stolper, 1982; among many others). This research has concentrated primarily on the effects of H₂O and CO₂ on phase relations in silicate systems and, more recently, on the solution mechanisms of these two volatiles in silicate liquids.

Another volatile, H₂, has been investigated recently for several reasons (Luth and Boettcher, 1986). First, because H₂ is ubiquitous in some high-pressure experimental apparatus, the effects of H₂ on phase equilibria and on the solubility of other volatiles, such as H₂O and CO₂, must be studied to evaluate the significance of the presence of H₂ and the applicability of experimental studies to natural systems. Second, the study of H₂ provides insight into the general problem of the interactions of volatiles with silicate liquids because it has different effects on phase

relations (Luth and Boettcher, 1986) and, potentially, different solubility mechanisms in silicate liquids than do H₂O and CO₂. Third, Arculus et al. (1984) and Haggerty (1986), among others, have suggested that some regions of the mantle of the Earth are relatively reduced, corresponding to oxygen fugacities close to the synthetic iron-wüstite (IW) buffer in f_{O_2} - T space. An O-H vapor in equilibrium with the IW buffer would contain a significant proportion of hydrogen (Fig. 1), varying from ~2% at 25 kbar and 700°C to ~34% at 7.5 kbar and 1600°C.

To investigate further the role of H₂ in silicate liquids, the solubility mechanism of H₂ in liquids in the system Na₂O-Al₂O₃-SiO₂-H₂ has been investigated with Raman spectroscopy. If hydrogen dissolves both as molecular H₂ and by reacting with cation-oxygen bonds in the liquid to form hydroxide and hydride species, Raman spectra of H₂-bearing glasses should contain bands from vibrations involving the resulting hydrogen-containing species. In addition, the low-frequency region (200–1400 cm⁻¹) of the Raman spectra will provide information on the effects of the dissolution of hydrogen on the structure of the silicate network.

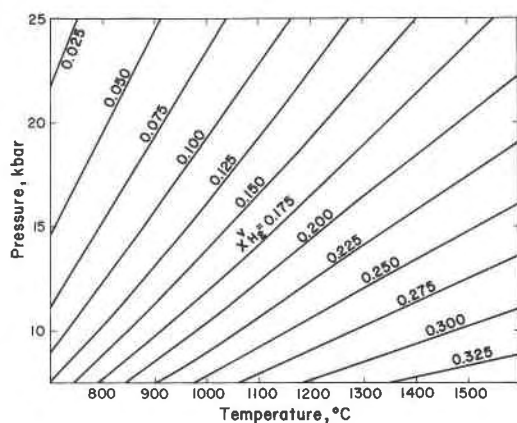


Fig. 1. Composition of O-H vapor in equilibrium with the iron-wüstite buffer assemblage as a function of pressure and temperature. Numbers along the curves are the mole fraction of H₂ in vapor. Vapor composition calculated using modified Redlich-Kwong formulation of Holloway (1977).

EXPERIMENTAL METHODS

Glasses in the system Na₂O-Al₂O₃-SiO₂, synthesized at 1 atm from oxide and carbonate mixes (Table 1), were used as starting materials for experiments in high-pressure, solid-media apparatus (Boyd and England, 1960). Approximately 40 mg of the glass were loaded into an open-ended 3-mm Pt capsule and dried at 400°C for ~16 h. After welding shut, this capsule was sealed into a 5-mm Pt capsule, together with the f_{H₂}-buffer assemblage consisting of iron, wüstite, and H₂O. In some cases, H₂O was replaced with D₂O to obtain further Raman spectral information on hydrogen-bearing species. The double capsule was run vertically in a 19-mm-diameter furnace assembly (Kushiro, 1976), with the temperature monitored by a Pt-Pt₉₀Rh₁₀ thermocouple in contact with the top of the capsule. The piston-out technique, with a -7% friction correction, was used. To ascertain if H₂ was diffusing in from the furnace assembly and if H₂O adsorbed on the starting material was an important source of H₂, samples of glass were synthesized in single Pt capsules at the same pressures and temperatures as the double-capsule experiments, but with the f_{H₂} buffered between NNO (Ni + NiO + H₂O) and HM (Fe₂O₃ + Fe₃O₄ + H₂O) by the furnace assembly.

Raman spectra of the quenched glasses were obtained with the automated Raman system described by Mysen et al. (1982) and Seifert et al. (1982). Small, 2–10-mm³ chips of the glasses were excited by the 488-nm line of a Coherent CR-18 Ar⁺ laser operating at 1.5 to 2.5 W. Other details of the data acquisition and storage, the corrections of instrumental background and of temperature- and frequency-dependent scattering are described by Mysen et al. (1982).

RESULTS

The experimental conditions are listed in Table 2. Analysis of the quenched glasses for the concentration of H₂ dissolved in the liquid was not attempted because of problems that previous workers encountered with diffusion of H₂ out of the glass after the quenching of the experiment. For example, Faile and Roy (1971) reported that approximately half of the H₂ dissolved in a high-silica glass diffused out over ~100 days.

The Raman spectra of the high-frequency (3000–4500

TABLE 1. Compositions of glasses studied

Composition	Na ₂ O	Al ₂ O ₃	SiO ₂
NS2	34.03	0.00	65.97
NS4	20.50	0.00	79.50
NS7	12.84	0.00	87.16
Jd	15.33 (15.16)	25.22 (25.06)	59.45 (59.77)
Ab	11.82 (11.52)	19.44 (19.32)	68.74 (68.95)
A2S	10.60 (10.53)	17.44 (17.65)	71.95 (71.82)

Note: Compositions are given in weight percent. Numbers in parentheses are derived from microprobe analyses; other numbers are nominal compositions.

cm⁻¹) region of the quenched liquids show a sharp, symmetric band at ~4123 cm⁻¹ and a broad, asymmetric band at ~3580 cm⁻¹ (Fig. 2). The band at ~3580 cm⁻¹ is assigned to the stretching vibrations of OH groups, either in molecular H₂O or in OH groups bonded to cations in the silicate network (Scholze, 1960). The topology of this band is similar to that found for H₂O-bearing glasses in the system Na₂O-Al₂O₃-SiO₂ by McMillan and Remmele (1986) and by Mysen and Virgo (1986). In the spectra of the H₂-bearing glasses on the join NaAlO₂-SiO₂, however, there is a small shoulder at ~3313 cm⁻¹ associated with the OH-stretching band (arrow, Fig. 2) that is absent in the spectra of the H₂O-bearing glasses. In the Raman spectra of the aluminosilicate glasses quenched from ≥1400°C, a band at 1630 cm⁻¹, attributed to bending vibrations of molecular H₂O (Herzberg, 1945; McMillan et al., 1983), is present.

Raman spectra of the samples of glass synthesized in single Pt capsules, with the f_{H₂} buffered by the furnace assembly, lacked bands in the 3000–4500-cm⁻¹ region. This contrast indicates that the OH and H₂ bands observed in the spectra of the IW-buffered glasses were not the result of either adsorbed H₂O or H₂ from the furnace assembly.

The sharp band at ~4123 cm⁻¹, attributed to the stretching vibration of the H₂ molecule, occurs at lower frequency in these glasses than in H₂ vapor at 1 atm (4159.4 cm⁻¹; Nakamoto, 1978), and the frequency increases with increasing pressure, temperature, and silica content on both the Na₂O-SiO₂ and NaAlO₂-SiO₂ joins (Fig. 3). Although no bubbles were visible with either the optical or the scanning-electron microscope, it is conceivable that the H₂ is present in submicroscopic bubbles. There is, however, some evidence against this possibility. The Raman spectra of a bubble-rich glass of NS7-H₂O-H₂ composition (Table 2) contains two well-resolved peaks, one at ~4126 cm⁻¹ with a full width at half-maximum peak height (FWHM) of ~14 cm⁻¹, and one at ~4154 cm⁻¹ with a FWHM of ~8 cm⁻¹. The 4154-cm⁻¹ band is interpreted as resulting from vibrations of H₂ molecules contained in the gas bubbles, offset from ~4159 cm⁻¹ by interaction of the H₂ with H₂O molecules, whereas it is suggested that the 4126-cm⁻¹ band would then result from H₂ dissolved in the silicate glass. The difference between the high-frequency spectrum of this

TABLE 2. Summary of experimental conditions and results

Run no.*	Composition	Pressure (kbar)	Temperature (°C)	Duration (min)
142†	NS2	15	1100	30
81	NS2-H ₂	15	1100	30
83	NS2-D ₂	15	1100	30
02	NS4	0.001	1150	90
01	NS4-H ₂	15	1350	30
143	NS4-H ₂	15	1450	20
03	NS4-D ₂	15	1350	30
118	HS4-H ₂	25	1450	30
S.M.‡	NS7	0.001	1460	120
77§	NS7-H ₂	15	1500	10
96†	Ab	15	1400	20
116†	Ab	25	1400	20
89	Ab-H ₂	15	1400	20
108	Ab-H ₂	20	1400	20
126	Ab-H ₂	20	1450	20
109	Ab-H ₂	25	1400	20
120	Ab-D ₂	15	1400	20
119	Ab-D ₂	25	1400	20
124†	Jd	15	1450	20
122	Jd-H ₂	15	1450	20
125	Jd-H ₂	20	1450	20
123	Jd-H ₂	25	1450	20
138†	A2S	20	1500	20
139	A2S-H ₂	15	1500	15
141	A2S-H ₂	20	1475	15
140	A2S-H ₂	20	1500	15

* All high-pressure experiments run with IW buffer except where noted.


† Experiments run under furnace-buffered (f_{H_2} between HM and NNO) conditions.

‡ S.M. = starting material.

§ Inner capsule leaked during experiment; bubble-rich NS7-H₂O-H₂ glass resulted.

sample and the spectra of the other, apparently bubble-free, H₂-containing glasses indicates that the molecular H₂ in the latter is dissolved in the glass.

If the hydroxide groups that cause the ~3580-cm⁻¹ band are generated by the reaction



(X, Y = Na, Al, or Si), then, from charge-balance considerations, hydride groups should be present as well. Van der Steen and van den Boom (1977) attributed a band at ~2250 cm⁻¹ in SiO₂ glass fused in a He-H₂ atmosphere at $P_{total} = 1$ bar to Si-H stretching vibrations. No such band was present in the spectra of the glasses in this study. Another possible hydride is Na-H, which would be characterized by a band at ~1132 cm⁻¹ (Nakamoto, 1978), a region that has strong scattering from Si-O vibrations. Because of this overlap, and because the highly ionic nature of the Na-H bond makes this bond a poor Raman scatterer, the presence of a band at ~1132 cm⁻¹ could not be confirmed.

Alternatively, the formation of a Pt-Si alloy by interaction between the sample container and the silicate sample at the high temperatures and low f_{O_2} of these experiments would explain the presence of OH in these glasses. Chen and Presnall (1975) found such alloys formed in Pt capsules run at 7 kbar, 1665°C for 4 h under furnace-

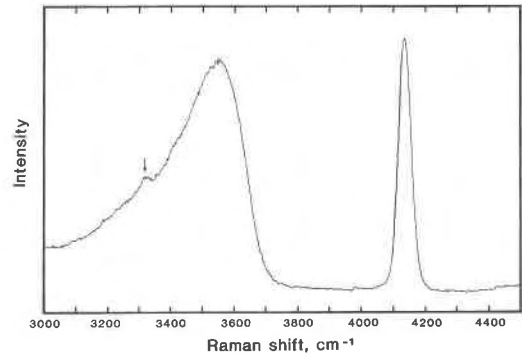


Fig. 2. High-frequency Raman spectrum of Ab-H₂ (run 109). Symmetric band at ~4123 cm⁻¹ from H₂ stretching vibration, asymmetric band at ~3580 cm⁻¹ from OH stretching and bending modes. Arrow indicates the small band that is present in the spectra of H₂-bearing samples. This band is absent in the spectra of H₂O-bearing samples studied by Mysen and Virgo (1986).

buffered conditions. We observed a mosaiclike texture of Pt and Pt-Si alloy, similar to that shown in Figure 6 of Chen and Presnall (1975), in the capsule wall from an experiment that was buffered by IW at 15 kbar and 1450°C for 20 min. Furthermore, ~0.03-mm² areas of homogeneous Pt-Si alloy were observed in the capsule wall of an experiment that was buffered by IW at 15 kbar and 1100°C for 30 min. Analysis of these alloys using energy-dispersive analysis on a JEOL scanning-electron microscope detected only Pt and Si. Formation of this alloy would liberate oxygen that reacts with H₂, diffusing into the capsule from the buffer assemblage to form H₂O. This H₂O could dissolve in the silicate liquid both as molecular H₂O and as OH, resulting in the vibrations that were observed at ~1630 cm⁻¹ and ~3580 cm⁻¹, respectively.

The low-frequency (200–1400 cm⁻¹) region of the Na₂O-SiO₂ glasses (Fig. 4a) changes only subtly with the addition of H₂ (and concomitant H₂O), with a possible new band at ~900 cm⁻¹. In contrast, a new band at ~900 cm⁻¹ is quite obvious in the spectra of glasses along the NaAlO₂-SiO₂ join upon the addition of H₂ and H₂O (Fig. 4b). This band was observed in hydrous albite glass by Mysen et al. (1980) and McMillan et al. (1983) and in hydrous glasses on the NaAlO₂-SiO₂ join by Mysen and Virgo (1986). This band is attributed by Mysen et al. (1980) and Mysen and Virgo (1986) to Si-O vibrations involving nonbridging oxygens generated upon the solution of H₂O in the liquid. McMillan et al. (1983), however, argued that this band results from Si-OH and/or Al-OH stretching vibrations. For this interpretation to be correct, a decrease in the frequency of this band should be observed upon the substitution of D₂O for H₂O. Such a change in frequency was not observed by Mysen and Virgo (1986) or in this study.

When D₂ is substituted for H₂ in these glasses, the O-D vibrations result in an asymmetric band at ~2640 cm⁻¹. In addition, a symmetric band is observed at ~2975 cm⁻¹ from D-D stretching vibrations, along with a smaller, symmetric band at ~3605 cm⁻¹ from H-D vibrations.

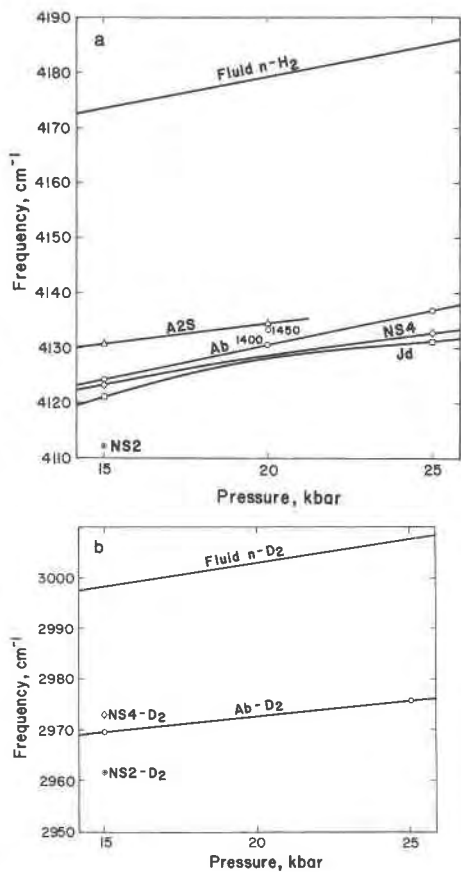


Fig. 3. Dependence of the band from the stretching vibration of H₂ (a) and D₂ (b) on matrix, temperature, and pressure. Data for fluid *n*-H₂ and *n*-D₂ from Sharma et al. (1979) and Sharma et al. (1980), respectively.

The HD molecule is present because the D₂O that was loaded into the buffer capsule contained ~5% H₂O.

The change in frequency of the OH and H₂ bands upon the substitution of D₂ for H₂ may be calculated from

$$\frac{\nu_i}{\nu_j} = \sqrt{\frac{\mu_j}{\mu_i}} \quad (2)$$

(Herzberg, 1950), where ν = the frequency of the vibration, μ = the reduced mass [$= (m_a m_b) / (m_a + m_b)$, where m_a and m_b are the masses of the two entities involved in the vibration], and subscripts i and j represent DD and HH or OD and OH. Equation 2 assumes that the force constant for the vibration is unaffected by the isotopic substitution. The observed values for ν_{OD}/ν_{OH} of ~0.74 and ν_{D_2}/ν_{H_2} of ~0.72 compare well with the values of 0.73 and 0.71 predicted for ν_{OD}/ν_{OH} and ν_{D_2}/ν_{H_2} , respectively, by Equation 2.

DISCUSSION

Before considering the solution mechanisms of H₂, the variation in the frequency of the band from the H-H stretching vibration with pressure, temperature, and composition (Fig. 3a) should be examined. The frequency

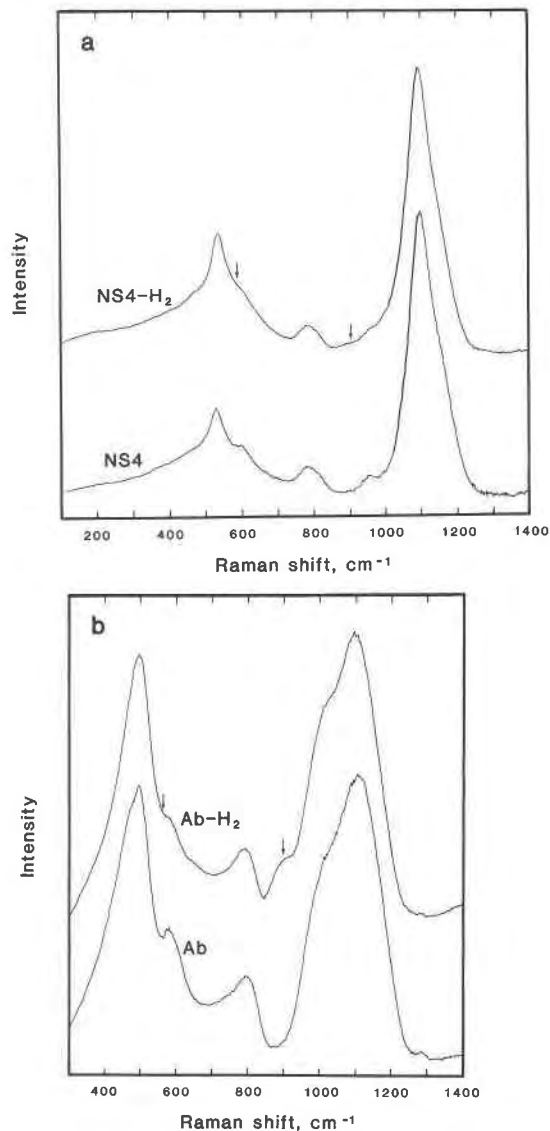


Fig. 4. Temperature- and frequency-corrected Raman spectra. NS4, NS4-H₂, Ab, and Ab-H₂ glasses. Arrows note regions of spectra that change upon the addition of H₂. (a) NS4 (run 02) and NS4-H₂ (run 01). (b) Ab (run 96) and Ab-H₂ (run 109).

of this vibration in the glasses, which is consistently lower by ~50 cm⁻¹ than that in fluid H₂ (Sharma et al., 1979), increases systematically with increasing pressure, temperature, and silica content of the glass on the joins Na₂O-SiO₂ and NaAlO₂-SiO₂. Similar effects are observed for D₂ (Fig. 3b). The ν_{D_2}/ν_{H_2} ratios for the different matrix materials are all 0.719 ± 0.001 , as mentioned above, indicating that the systematic variation in frequency with pressure, temperature, and composition is not a result of scatter in the data. The lower frequency of the H-H stretching vibration in silicate liquids compared with H₂ fluids results from the interactions between the hydrogen dissolved in the silicate glass and the surrounding atoms of the silicate network (Hartwig, 1976). Stone et al. (1984)

interpreted a similar decrease in the frequency of the stretching vibration of N₂ upon dissolution in silica glass as resulting from the interaction of the N₂ molecules with the silica. The systematic decrease in the frequency with decreasing silica content in glasses on the joins Na₂O-SiO₂ and NaAlO₂-SiO₂ (Fig. 3a) would therefore indicate a concomitant increase in the interaction between molecular H₂ and the silicate network with decreasing silica content, perhaps because of greater affinity of molecular H₂ for Al- or Na-containing species in the liquid.

The solution mechanism of H₂ may be expressed by the reaction



The evidence for the presence of molecular H₂ in these glasses has been outlined above. Bands caused by vibrations of hydride species, if present, were too weak to be observed. The presence of bands from vibrations of OH and H₂O result from the reaction of H₂ with O₂ liberated by the silicate when a Pt-Si alloy is formed, and they have nothing to do with the solubility mechanism of H₂ per se. Therefore, unlike H₂O and CO₂, H₂ appears to dissolve in silicate liquids only as a molecular entity.

The formation of a Pt-Si alloy at relatively low temperatures (~1100°C) at the high f_{H_2} of the IW buffer and concomitant generation of H₂O requires re-evaluation of previous experimental work at reducing conditions. In systems containing H₂O, such as those studied by Holloway and Jakobsson (1986) and Luth and Boettcher (1986), the formation of this alloy will decrease slightly the amount of SiO₂ in the bulk composition and increase the H₂O present, although the magnitude of this effect cannot be quantified at present. The separation of the Pt capsule from the sample by a graphite capsule possibly inhibited the formation of the Pt-Si alloy in the experiments of Holloway and Jakobsson (1986); in any case, the coexistence of graphite and vapor at given pressure, temperature, and f_{O_2} in their experiments fixes the vapor composition, and the H₂O generated by reduction of Si⁴⁺ would not affect the composition of the vapor. In the experiments of Luth and Boettcher (1986), where C-bearing phases were not present, the formation of the alloy would make the vapor slightly more H₂O-rich than predicted by the modified Redlich-Kwong equation of state used to calculate vapor compositions. The reduction of Si⁴⁺ and consequent liberation of oxygen will, however, have very significant effects in H₂O-absent systems. For example, the large effect on phase equilibria attributed to CH₄ by Egger and Baker (1982) and to H₂ by Luth and Boettcher (1985) may be a result of the formation of this alloy and concomitant contamination of the experiments with H₂O. Because of the formation of the Pt-Si alloy, H₂O-free conditions cannot be achieved in Pt capsules at elevated temperatures at high f_{H_2} .

ACKNOWLEDGMENTS

Critical reviews by H. S. Yoder, Paul McMillan, and three anonymous reviewers of an earlier version of this manuscript are appreciated. One of

the reviewers pointed out the Chen and Presnall (1975) reference on the formation of Pt-Si alloys, which profoundly affected our interpretation of the mechanism of formation of OH and molecular H₂O in these liquids.

REFERENCES

- Arculus, R.J., Dawson, J.B., Mitchell, R.H., Gust, D.A., and Holmes, R.D. (1984) Oxidation states of the upper mantle recorded by megacryst ilmenite in kimberlite and type A and B spinel lherzolites. *Contributions to Mineralogy and Petrology*, 85, 85–94.
- Boyd, F.R., and England, J.L. (1960) Apparatus for phase equilibrium measurements at pressures up to 50 kilobars and temperatures up to 1750°C. *Journal of Geophysical Research*, 65, 741–748.
- Burnham, C. Wayne. (1979) The importance of volatile constituents. In H.S. Yoder, Jr., Ed., *The evolution of the igneous rocks*, p. 439–482. Princeton University Press, New Jersey.
- Chen, C.-H., and Presnall, D.C. (1975) The system Mg₂SiO₄-SiO₂ at pressures up to 25 kilobars. *American Mineralogist*, 60, 398–406.
- Egger, D.H. (1975) CO₂ as a volatile component of the mantle: The system Mg₂SiO₄-SiO₂-H₂O-CO₂. *Physics and Chemistry of the Earth*, 9, 869–881.
- Egger, D.H., and Baker, D.R. (1982) Reduced volatiles in the system C-O-H: Implications to mantle melting, fluid formation, and diamond genesis. In S. Akimoto and M.H. Manghni, Eds., *High-pressure research in geophysics*, p. 237–250. Reidel, Dordrecht, Holland.
- Faile, S.P., and Roy, D.M. (1971) Dissolution of hydrogen in fused silica. *American Ceramic Society Journal*, 54, 533–534.
- Goranson, R.W. (1931) The solubility of water in granite magmas. *American Journal of Science*, 22, 481–502.
- Haggerty, S.E. (1986) Diamond genesis in a multiply-constrained model. *Nature*, 320, 34–38.
- Hartwig, C.M. (1976) Raman scattering from hydrogen and deuterium dissolved in silica as a function of pressure. *Journal of Applied Physics*, 47, 956–959.
- Herzberg, Gerhard. (1945) *Molecular spectra and molecular structure. II. Infrared and Raman spectra of polyatomic molecules*. Van Nostrand, New York.
- (1950) *Molecular spectra and molecular structure. I. Spectra of diatomic molecules* (2nd edition). Van Nostrand, New York.
- Holloway, J.R. (1977) Fugacity and activity of molecular species in supercritical fluids. In D.G. Fraser, Ed., *Thermodynamics in geology*, p. 161–182. Reidel, Dordrecht, Holland.
- Holloway, J.R., and Jakobsson, Sigurdur. (1986) Volatile solubilities in magmas: Transport of volatiles from mantles to planet surfaces. *Proceedings of the Sixteenth Lunar and Planetary Science Conference, Part 2*. *Journal of Geophysical Research*, 91, D505–D508.
- Kushiro, Ikuo. (1976) Changes in viscosity and structure of melt of NaAlSi₃O₈ composition at high pressures. *Journal of Geophysical Research*, 81, 6347–6350.
- Luth, R.W., and Boettcher, Art. (1985) Hydrogen and the melting of albite and diopside (abs.). *EOS*, 66, 1130.
- (1986) Hydrogen and the melting of silicates. *American Mineralogist*, 71, 264–276.
- Luth, W.C., Jahns, R.H., and Tuttle, O.F. (1964) The granite system at pressures of 4 to 10 kilobars. *Journal of Geophysical Research*, 69, 759–773.
- McMillan, P.F., and Remmele, R.L., Jr. (1986) Hydroxyl sites in SiO₂ glass: A note of infrared and Raman spectra. *American Mineralogist*, 71, 772–778.
- McMillan, P.F., Jakobsson, Sigurdur, Holloway, J.R., and Silver, L.A. (1983) A note on the Raman spectra of water-bearing albite glass. *Geochimica et Cosmochimica Acta*, 47, 1937–1943.
- Mysen, B.O. (1976) The role of volatiles in silicate melts: Solubility of carbon dioxide and water in feldspar, pyroxene, and feldspathoid melts to 30 kb and 1625°C. *American Journal of Science*, 276, 969–996.
- Mysen, B.O., and Boettcher, A.L. (1975) Melting of a hydrous mantle: I. Phase relations of natural peridotite at high pressures and temperatures with controlled activities of water, carbon dioxide, and hydrogen. *Journal of Petrology*, 16, 520–548.
- Mysen, B.O., and Virgo, David. (1986) Volatiles in silicate melts at high pressure and temperature, 2. Water in melts along the join NaAlO₂-

- SiO₂ and a comparison of solubility mechanisms of water and fluorine. *Chemical Geology*, 57, 333–358.
- Mysen, B.O., Finger, L.W., Seifert, F.A., and Virgo, David. (1982) Curve-fitting of Raman spectra of amorphous materials. *American Mineralogist*, 67, 686–696.
- Mysen, B.O., Virgo, David, Harrison, W.J., and Scarfe, C.M. (1980) Solubility mechanisms of H₂O in silicate melts at high pressures and temperatures: A Raman spectroscopic study. *American Mineralogist*, 65, 900–914.
- Nakamoto, Kazuo. (1978) *Infrared and Raman spectra of inorganic and coordination compounds* (3rd edition). Wiley-Interscience, New York.
- Scholze, H. (1960) Zur Frage der Unterscheidung zwischen H₂O-Molekulan und OH-Gruppen in Gläsern und Mineralen. *Naturwissenschaften*, 47, 226–227.
- Seifert, F.A., Mysen, B.O., and Virgo, David. (1982) Three-dimensional network structure in the systems SiO₂-NaAlO₂, SiO₂-CaAl₂O₄, and SiO₂-MgAl₂O₄. *American Mineralogist*, 67, 696–718.
- Sharma, S.K., Mao, H.K., and Bell, P.M. (1979) Raman study of *n*-H₂ under very high pressures at room temperature. *Carnegie Institution of Washington Year Book* 78, 645–649.
- (1980) Raman measurements of deuterium in the pressure range 8–537 kbar at room temperature. *Carnegie Institution of Washington Year Book* 79, 358–364.
- Stolper, Edward. (1982) The speciation of water in silicate melts. *Geochimica et Cosmochimica Acta*, 46, 2609–2620.
- Stone, J., Chraplyvy, A.R., and Burrus, C.A. (1984) Observation of Raman scattering from N₂ in a silica optical fiber. *Journal of Non-Crystalline Solids*, 69, 145–147.
- Tuttle, O.F., and Bowen, N.L. (1958) Origin of granite in the light of experimental studies in the system NaAlSi₃O₈-KAlSi₃O₈-SiO₂-H₂O. *Geological Society of America Memoir* 74.
- van der Steen, G.H.A.M., and van den Boom, H. (1977) Raman spectroscopic study of hydrogen-containing vitreous silica. *Journal of Non-Crystalline Solids*, 23, 279–286.
- Wasserburg, G.J. (1957) The effect of H₂O in silicate systems. *Journal of Geology*, 65, 15–23.
- Yoder, H.S., Jr., and Tilley, C.E. (1962) Origin of basalt magmas: An experimental study of natural and synthetic rock systems. *Journal of Petrology*, 3, 342–532.

MANUSCRIPT RECEIVED JUNE 19, 1986

MANUSCRIPT ACCEPTED FEBRUARY 13, 1987