

Characterization of some biogenic carbonates with Raman spectroscopy

J. URMOS, S. K. SHARMA, F. T. MACKENZIE

Department of Oceanography and Hawaii Institute of Geophysics, University of Hawaii, Honolulu, Hawaii 96822, U.S.A.

ABSTRACT

Raman spectra are reported for biogenic carbonates from a scleractinian coral (*Porites* sp.), pink pigmented (*Corallium regale*) and unpigmented (*Corallium secundum*) precious corals, and natural and cultured pearls. Spectra of aragonitic *Porites* coral and pearls show Raman bands typical of aragonite; however, the bands of the natural pearl are slightly sharper than the corresponding bands from *Porites* and cultured pearl spectra. The broadening of the Raman bands of *Porites* is indicative of either small crystallite size or crystal structure disorder.

Spectra of the deep-sea, precious corals closely resemble Raman spectra of magnesian calcite, with the exception of the pink coral, which shows seven additional bands in the spectral region of 1020–3758 cm^{-1} . These extra bands arise from a carotenoid pigment that is responsible for the pink coloration of the coral skeleton. Lattice modes for these corals are much broader than the corresponding pure calcite bands but are similar to those of synthetic 9.9 mol% magnesian calcite. These increased halfwidths are attributed mainly to static positional disorder of the carbonate ion in the calcite. This static rotation of carbonate ions out of the basal plane results from the substitution of 10 mol% Mg^{2+} for Ca^{2+} in the calcite. The positional disordering of carbonate ions in biogenic magnesian calcite seems to be characteristic of these biominerals, irrespective of their source, and may affect the relative stabilities of these carbonates as they undergo diagenesis.

INTRODUCTION

To date, nearly 60 different types of biogenic minerals have been recognized, but only a few of these biominerals have been examined in detail (Lowenstam and Weiner, 1989). Of this diverse assemblage of biominerals, the carbonates are the most important in terms of abundance, accounting for approximately 30% of the Phanerozoic sedimentary rock record after diagenesis (Chave, 1984; Lowenstam and Weiner, 1989; Morse and Mackenzie, 1990). These phases exert a major influence on the chemistry of sea water, the composition of sediments accumulating in the oceans, and the nature of diagenesis. In order to understand quantitatively the fate of these carbonates in sedimentary and diagenetic environments, information about their microstructures and chemical heterogeneities is essential.

Bischoff et al. (1985) used Raman spectroscopy to show that positional disordering of the carbonate ions is greater for biogenic magnesian calcites than for synthetic magnesian calcites with similar compositions. This disorder is an important factor affecting the thermodynamic stability of these biogenic phases. In the present study, Raman spectroscopy has been used to investigate the structures of biogenic aragonite and additional biogenic calcite. The results confirm previous findings (Bischoff et al., 1985) of carbonate ion positional disorder in biogenic calcites. Furthermore, our results show that the differences observed between biogenic and synthetic aragonite Raman

spectra are much smaller than those of the magnesian calcite and that these differences may originate more from small crystallite size than crystal structure disorder.

EXPERIMENTAL METHODS

The Raman spectra were recorded at room temperature with a Spex 1402 double monochromator and a computerized data acquisition system. The carbonate samples were excited with the 488.0-nm line of an Ar^+ ion laser. The biogenic calcite and aragonite samples were studied directly with no pretreatment, and the synthetic calcite and aragonite samples were powdered and placed in capillary tubes. Scattered radiation from the samples was measured in a 90° scattering geometry. The Raman spectra were obtained at intervals of 1 cm^{-1} (100–1800 cm^{-1}) and 3 cm^{-1} (2000–4000 cm^{-1}) and slit widths of 2 or 3 cm^{-1} . Selected anti-Stokes Raman spectra were recorded for calibration purposes and only Stokes Raman spectra are illustrated. Raman spectra of pink coral samples were also recorded with the 514.5-nm line of an Ar^+ ion laser to distinguish between Raman and fluorescence bands. Compositions of the magnesian calcite samples were determined using electron microprobe and X-ray diffraction analyses.

STRUCTURE AND BAND ASSIGNMENTS

Calcite and aragonite are the two major polymorphs of calcium carbonate that have been identified as geologi-

cally important biominerals. Aragonite is the thermodynamically favored phase at high pressure.

Calcite

Calcite has rhombohedral space group $D_{3d}^6 (R\bar{3}c)$ with $Z = 2$. Cations have C_{3i} site symmetries, and C atoms occupy sites with D_3 symmetry. Factor-group analysis predicts that 27 optical modes will be distributed among the following symmetry species (Bhagavantam and Venkatarayudu, 1939; Wilkinson, 1973; White, 1974):

lattice modes

$$\Gamma_{\text{rot}} = A_{2g}(\text{i.a.}) + E_g(\text{R}) + A_{2u}(\text{IR}) + E_u(\text{IR})$$

$$\Gamma_{\text{trans}} = A_{2g}(\text{i.a.}) + E_g(\text{R}) + A_{1u}(\text{i.a.}) + A_{2u}(\text{IR}) + 2E_u(\text{IR})$$

internal modes

$$\Gamma_{\text{int}} = A_{1g}(\text{R}) + A_{2g}(\text{i.a.}) + 2E_g(\text{R}) + A_{1u}(\text{i.a.}) + A_{2u}(\text{IR}) + 2E_u(\text{IR})$$

where Γ_{rot} and Γ_{trans} refer to the rotational and translational lattice modes, and R, IR, and i.a. refer to Raman-active, infrared-active, and inactive modes, respectively. In the Raman spectrum of calcite, a total of five fundamental vibration modes, two lattice modes and three internal modes, are expected to be active (White, 1974). The first overtone of the infrared-active $2 \times \nu_2$ mode at $1740\text{--}1750\text{ cm}^{-1}$ is also allowed in the Raman spectrum.

Aragonite

Aragonite has orthorhombic space group $D_{2h}^6 (Pnma)$ with $Z = 4$. In calcite, C in the carbonate anions occupies sites with D_3 symmetry, but in aragonite C has C_s symmetry. Factor-group analysis predicts that 57 optical modes in aragonite will be distributed among the following symmetry species (Couture, 1947; Yamamoto et al., 1974):

lattice modes

$$\Gamma_{\text{rot}} = A_{1g}(\text{R}) + 2B_{1g}(\text{R}) + 2B_{2g}(\text{R}) + B_{3g}(\text{R}) + 2A_{1u}(\text{i.a.}) + B_{1u}(\text{IR}) + B_{2u}(\text{IR}) + 2B_{3u}(\text{IR})$$

$$\Gamma_{\text{trans}} = 4A_{1g}(\text{R}) + 2B_{1g}(\text{R}) + 2B_{2g}(\text{R}) + 4B_{3g}(\text{R}) + 2A_{1u}(\text{i.a.}) + 3B_{1u}(\text{IR}) + 3B_{2u}(\text{IR}) + B_{3u}(\text{IR})$$

internal modes

$$\Gamma_{\text{int}} = 4A_{1g}(\text{R}) + 2B_{1g}(\text{R}) + 2B_{2g}(\text{R}) + 4B_{3g}(\text{R}) + 2A_{1u}(\text{i.a.}) + 4B_{1u}(\text{IR}) + 4B_{2u}(\text{IR}) + 2B_{3u}(\text{IR}).$$

In the Raman spectrum of aragonite, 30 fundamental vibration modes are expected to be active. The rotational and translational lattice modes appear in the low-frequency region ($100\text{--}350\text{ cm}^{-1}$), whereas the internal fundamental modes of vibration of the carbonate ions appear in the high-frequency region ($600\text{--}1800\text{ cm}^{-1}$).

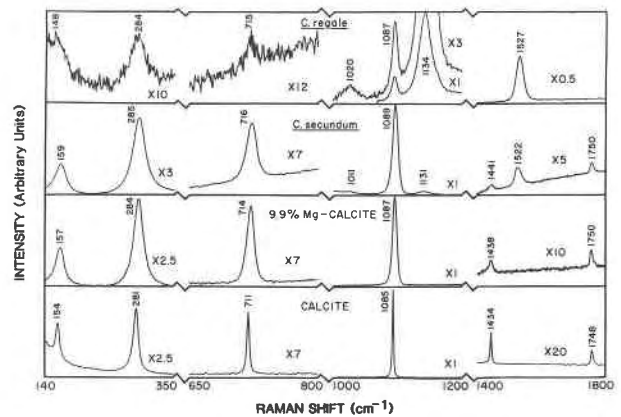


Fig. 1. Portions of the Raman spectra for pink (*C. regale*) and white (*C. secundum*) precious corals, synthetic magnesiumian calcite (9.9 mol% MgCO_3), and calcite over the region of $140\text{--}1800\text{ cm}^{-1}$. Scaling factors for the various intervals are relative to the ν_1 mode ($\sim 1085\text{ cm}^{-1}$) of each sample.

RESULTS AND DISCUSSION

Biogenic calcite

Selected portions of the region from $140\text{--}1800\text{ cm}^{-1}$ of the Raman spectra of deep-sea corals, calcite, and magnesiumian calcite with 9.9% Mg are shown in Figure 1. Additional high-frequency Raman spectra in the interval of $2000\text{--}4000\text{ cm}^{-1}$ for pink (*Corallium regale*) and white (*Corallium secundum*) precious corals are shown in Figure 2.

The five fundamental bands and the overtone band at $1740\text{--}1750\text{ cm}^{-1}$ predicted from the group theory analysis of calcite are observed in the synthetic and biogenic calcite spectra. The bands at 154 cm^{-1} and 281 cm^{-1} in the calcite spectrum have been assigned to translational (E_g) and rotational (E_g) modes, respectively (Bischoff et al., 1985). It should, however, be emphasized that a considerable degree of mixing occurs between the translational and rotational lattice modes of calcite (Rousseau et al., 1968). The weak bands at 711 cm^{-1} and 1434 cm^{-1} are internal E_g modes corresponding to in-plane bending (ν_4) and antisymmetric stretching (ν_3) modes of carbonate ions. The strongest band, at 1085 cm^{-1} , is an A_g internal mode that derives from the symmetric stretching mode (ν_1) of the carbonate ion.

The general features of the Raman spectra of the pink and white corals closely resemble the spectra of calcite and synthetic magnesiumian calcite with 9.9% Mg, even though the pink coral spectrum has a low signal-to-noise ratio because of the strong fluorescence background. In addition to the expected calcite bands, Raman bands were also observed at 1011 , 1131 , and 1522 cm^{-1} in the spectrum of white coral and at 1020 , 1134 , and 1527 cm^{-1} in the spectrum of pink coral. The band at 1134 cm^{-1} for pink coral is nearly three times stronger than the 1087 cm^{-1} (A_{1g}) mode of the carbonate ion that dominates the other calcite spectra. Raman spectra of biogenic carbon-

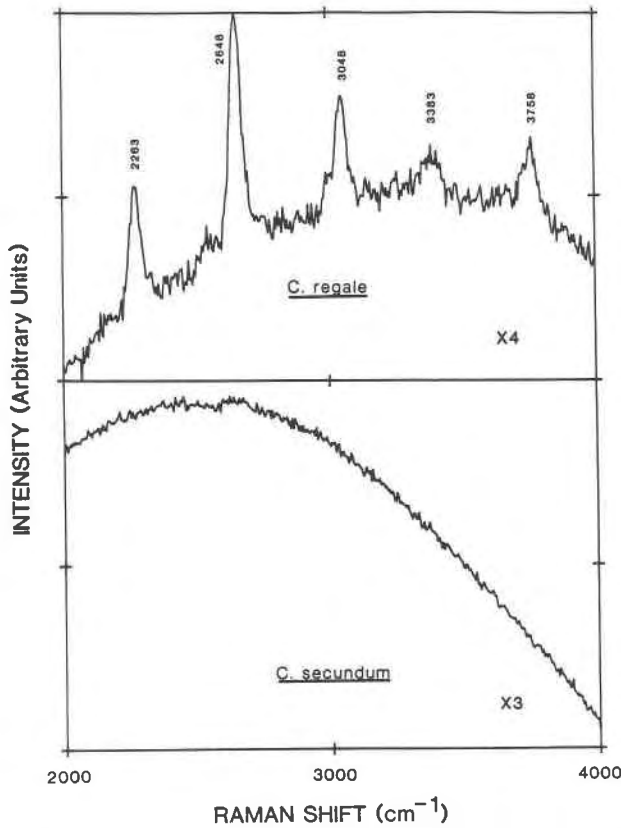


Fig. 2. Raman spectra in the region of 2000–4000 cm^{-1} of pink *C. regale* and white *C. secundum* precious corals showing the characteristic combination and overtone bands of the carotenoid pigment in the *C. regale* spectrum.

ates usually contain a weak band near 1014 cm^{-1} that has been attributed to bicarbonate ion (HCO_3^-) (Bischoff et al., 1985), which occurs in biogenic carbonates as a possible charge balance for an equivalent amount of Na^+ (White, 1975; Veizer, 1983; Bischoff et al., 1983). The Raman band at 1011 cm^{-1} in the *C. secundum* spectrum can be assigned to bicarbonate ion. The origins of those bands that are not assignable to vibrations of carbonate and bicarbonate ions in calcite will be discussed in the following section.

Bischoff et al. (1985) evaluated in detail some of the possible mechanisms for interpreting the variations in half

width (full width at the half-maximum peak height) and band positions in Raman spectra of magnesian calcite; only a brief summary is given here. The systematic variations in the Raman spectra of magnesian calcite may be potentially explained by changes in unit-cell dimensions because of the random substitution of Mg^{2+} for Ca^{2+} in the magnesian calcite solid-solution series, heterogeneities in the distribution of Mg^{2+} in the biogenic calcite, or the presence of trace constituents, such as SO_4^{2-} , Na^+ , and OH^- (Busenberg and Plummer, 1985), in the biogenic samples. Bischoff et al. (1985) evaluated these potential mechanisms and showed that they are either not plausible on the basis of other observations or are not sufficiently significant to account for the differences observed between the half widths of synthetic and biogenic magnesian calcite samples having similar Mg^{2+} contents. Instead, they proposed that the static positional disorder of carbonate ions in the calcite structure can provide a mechanism to explain the variations in the Raman spectra of the biogenic calcite. This disorder is physically manifested as a tilting of the planar carbonate groups out of the basal plane toward the *c* axis in order to accommodate the shorter Mg-O bonds in the crystal structure. This mechanism is supported by measurements of the *c/a* axial ratios for magnesian calcite, which shows positive deviations of the ratio from the ideal behavior (Bischoff et al., 1983; Mackenzie et al., 1983). Thus, although other factors may in part account for the increases in half width and changes in band positions in Raman spectra of biogenic magnesian calcite, the static positional disordering of the carbonate groups in the calcite crystal structure largely accounts for this behavior (Bischoff et al., 1985).

Observed half widths and positions of prominent Raman bands for the calcite samples are summarized in Table 1. The half widths and positions of the Raman bands in the pink and white coral spectra are found to be significantly different from the corresponding bands of the synthetic calcite, and to more closely resemble those of the synthetic 9.9 mol% magnesian calcite spectrum (Fig. 1). The spectra for the pink coral in the low frequency region are much degraded in comparison to the other calcite spectra in Figure 1. Biogenic magnesian calcite typically yields noisy spectra because of fluorescence from trace impurities (Bischoff et al., 1985), and the reduced precision in data for these spectra may, in part, be responsible for some scatter in the trends of spectral

TABLE 1. Raman frequencies and half widths (cm^{-1}) for synthetic and biogenic calcites

Sample	T	L	ν_4	ν_1	ν_3	$2 \times \nu_2$
Calcite	154 (6.7)	281 (9.5)	711 (4.5)	1085 (2.5)	1434 (5.5)	1748 (8.0)
9.9 mol% Magnesian calcite	157 (14.7)	284 (18.3)	714 (9.7)	1087 (7.6)	1438 (14)	1750 (10.8)
White coral	159 (19.4)	285 (23.1)	716 (13.4)	1089 (9.4)	1441 (13.9)	1750 (13.9)
(<i>C. secundum</i>)			nm	nm	nm	nm
Pink coral	148	284	715	1020	1087	1134
(<i>C. regale</i>)	nm	(26)	nm	(22.9)	(9.0)	(21.4)
						1522 (25.9)

Note: Half widths given in parentheses. The abbreviation nm = not measured. T = translational mode; L = librational mode.

properties obtained from biogenic carbonates. The skeletal pigment in the pink coral skeleton is the most likely cause for the degraded signal-to-noise ratio in the low-frequency region of this sample. The large half widths for the lattice modes (140–350 cm^{-1} region in Fig. 1) of the precious corals are similar in magnitude to half widths measured for other biogenic magnesian calcite (Bischoff et al., 1985) and are primarily attributed to the static positional disordering of the carbonate ion in the calcite crystal structure. This disordering results from the presence of 10 mol% Mg^{2+} in these biogenic samples as determined by electron microprobe and X-ray diffraction analyses. For a given mol% of Mg^{2+} , the biogenic calcites also show slightly greater half widths than the compositionally equivalent synthetic calcites (Bischoff et al., 1985), which suggests the possibility of greater positional disorder along with greater compositional heterogeneities in the biogenic magnesian calcite.

Calcite pigments

The most prominent bands in the Raman spectrum of the pink precious coral *C. regale* are a number of bands that are not attributable to the carbonate skeleton of the coral (Figs. 1, 2). The dominant Raman bands, between 1020 and 1527 cm^{-1} , are characteristic of resonance Raman spectra from *trans* conjugated carotenoid pigments (Rimai et al., 1973; Hoskins and Alexander, 1977). The intensities of the carotenoid Raman bands are much enhanced over the bands of the calcite matrix owing to the resonant coupling of the vibrational and electronic transitions with the laser source. Thus Raman spectra of carotenoids may be obtained at very low in situ pigment concentrations.

The characteristic vibrational modes of the carotenoid pigment are assigned as follows (Saito and Tasumi, 1983; Merlin, 1985; Merlin and Delé-Dubois, 1986). The fundamental Raman bands are at 1527 cm^{-1} (ν_1), which is produced by the stretching vibrations of $-\text{C}=\text{C}-$ double bonds, and at 1134 cm^{-1} (ν_2) because of the stretching of $-\text{C}-\text{C}-$ single bonds. The low intensity band at 1020 cm^{-1} (ν_3) is attributable to the rocking mode of the $-\text{CH}_3$ functional group. The other Raman bands of the carotenoid are combinations or overtones of the fundamental modes: 2263 $\text{cm}^{-1} = 2\nu_2$; 2648 $\text{cm}^{-1} = \nu_1 + \nu_2$; 3048 $\text{cm}^{-1} = 2\nu_1$ or $3\nu_3$; 3383 $\text{cm}^{-1} = 3\nu_2$; and 3758 $\text{cm}^{-1} = \nu_1 + 2\nu_2$.

As part of a wide-ranging Raman spectroscopic investigation of a variety of natural pigments in mollusc shells and corals, Merlin and Delé (1983) and Merlin and Delé-Dubois (1986) examined the pigments of a sample of the precious coral *Corallium rubrum*, which has a deep red coloration, both in situ and in solution extracts. Previous attempts to characterize the nature of the pigmentation of *C. rubrum* using chemical techniques were unsuccessful because the pigment could not be extracted from the skeleton (Fox, 1972). By using Raman spectroscopy, Merlin and Delé (1983) successfully identified a carotenoid as the type of pigment responsible for the coloration of this coral. Based on a comparison with the Raman

spectra of other carotenoids, a *trans* configured carotenoid with a $\text{ROOC}-(\text{CH}=\text{CH})_n-\text{COOR}'$ ($n = 11 \pm 1$) structure was proposed for the pigment in *C. rubrum* (Merlin, 1985; Merlin and Delé-Dubois, 1986).

A comparison of our Raman spectra from *C. regale* with the spectra from *C. rubrum* (Merlin and Delé-Dubois, 1986) reveals that the spectra are essentially identical, and the band positions differ by only 2–3 cm^{-1} for the fundamental carotenoid modes. The intensities of the carotenoid bands relative to the carbonate bands are significantly greater for *C. rubrum* than for the *C. regale* bands in our spectra. The ν_1 calcite peak at 1087 cm^{-1} is a separate and distinct peak in the Raman spectrum for *C. regale* (Fig. 1), but the same ν_1 calcite band is barely discernible as a shoulder on the much more intense ν_2 carotenoid band of *C. rubrum* (Merlin and Delé-Dubois, 1986). These intensity differences are attributable to corresponding differences in the relative concentrations of the same carotenoid pigment; the pink coloration of *C. regale* results from a lower concentration of carotenoid in the calcite skeleton than in the deep red colored *C. rubrum*.

Further support for the contention that a carotenoid is responsible for coloration of the coral is obtained from examination of white parts of the same coral skeleton (Merlin and Delé-Dubois, 1986) and a white member of the same genus (*C. secundum*). Our Raman spectra for *C. secundum* do not exhibit the intense bands characteristic of the carotenoid pigment found in the *C. regale* spectra. The weak bands in the *C. secundum* spectrum at 1131 cm^{-1} and 1522 cm^{-1} (Fig. 1) are presumably due to trace amounts of pigment in the skeletal matrix, although none of the characteristic combination or overtone bands were observed at higher frequencies because of their very low intensities (Fig. 2). The resonance Raman scattering of carotenoids can serve as a useful non-destructive and diagnostic technique for identifying this class of pigment in biogenic minerals.

Biogenic aragonite

Portions of Raman spectra in the 140–1800 cm^{-1} region for aragonite of the reef-building coral *Porites*, of cultured and natural pearl, and of synthetic aragonite are shown in Figure 3. Only 14 bands out of the 30 predicted Raman-active modes were detected in the Raman spectra of the polycrystalline aragonite samples. The lower-than-predicted number of observed bands may be attributed to a number of factors, such as low intensities, accidental degeneracies, or very small displacements of the trigonal anions to give a near-trigonal symmetry [D_{3d}^3 ($P\bar{3}m1$) and $Z = 2$] (Ismail et al., 1982) that yields a simpler spectrum than expected for crystals with the aragonite structure. The positions of the observed Raman bands are in agreement with those reported by Couture (1947) for the polarized Raman spectrum of aragonite. The most intense band near 1085 cm^{-1} (A_{1g}) in the aragonite spectra corresponds to the ν_1 symmetric stretching mode of the carbonate ion. The low to medium intensity bands in

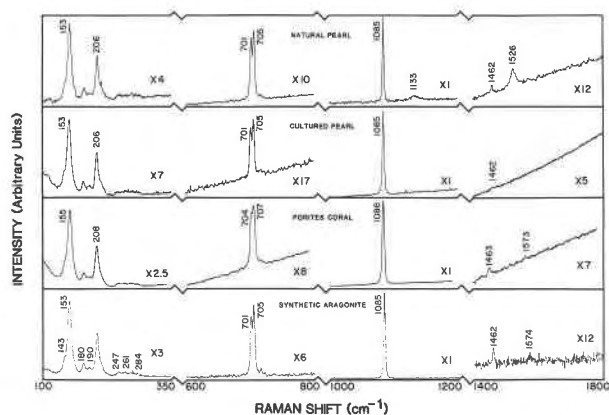


Fig. 3. Selected portions of the Raman spectra in the interval of 100–1800 cm^{-1} for natural and cultured pearls, the scleractinian coral *Porites* sp., and synthetic aragonite. The scaling factors are relative to the ν_1 mode ($\sim 1085 \text{ cm}^{-1}$) for each sample. The ν_2 band of the carbonate ion in the region of 800–850 cm^{-1} is very weak and is not shown in the figure.

the region of 100–300 cm^{-1} of the aragonite spectra arise from translational and rotational modes of lattice vibration. The ν_4 in-plane bending mode of the carbonate ion in aragonite occurs as a doublet consisting of bands at $\sim 701 \text{ cm}^{-1}$ (B_{1g}) and $\sim 705 \text{ cm}^{-1}$ (A_{1g}) (Fig. 3, Table 2), which is in contrast to the single band at $\sim 711 \text{ cm}^{-1}$ found in the calcite spectra (Fig. 1, Table 1). We were able to observe only a single band at 1462 cm^{-1} in the ν_3 region, rather than a doublet (1464 and 1466 cm^{-1}) as reported by Couture (1947). We also detected a very weak ν_2 band at $\sim 852 \text{ cm}^{-1}$ (Table 2); this vibrational mode is permitted for the aragonite crystal structure but is not allowed in the Raman spectra of crystals with a calcite structure. An additional weak band at $\sim 1574 \text{ cm}^{-1}$ was observed in some of the aragonite spectra (Fig. 3, Table 2). The $\sim 1574\text{-cm}^{-1}$ band probably arises from a combination mode.

The Raman spectrum measured for the natural pearl sample contains two bands at 1133 cm^{-1} and 1526 cm^{-1} that are not observed in the cultured pearl spectrum (Fig. 3, Table 2) and that are not assignable to vibrations of the carbonate ions in the aragonite crystal. These respective bands originate from the vibrations of single and

double C bonds. Such bands may result from a diffuse matrix of protein that pervades the carbonate matrix of the natural pearl (Alexander, 1940). Although no coloration of the sample was noticed, these bands might also be caused by the type of carotenoid pigment discussed in the previous section, particularly as in the case of the white *C. secundum* coral. The intensity ratio of the two bands in the natural pearl ($I_{1526}/I_{1133} = 1.1$) is identical to the ratio of the equivalent peaks of the carotenoid pigment in the pink coral carbonate. This evidence indicates that trace amounts of carotenoid are likely present in the aragonite matrix of the natural pearl, and one might predict that for pearls with some coloration, the pigmentation may originate from a carotenoid.

The Raman spectra for the synthetic and biogenic aragonite samples are all very similar (Table 2, Fig. 3) and the biogenic aragonite spectra are not as variable as the spectra of biogenic magnesian calcite. The positions of the Raman bands are all similar, and the only differences are found in the peak half widths. The lattice modes of the natural pearl have half widths that are narrower than in the synthetic aragonite (Table 2). The half widths for some lattice modes and the ν_1 symmetric stretching band of the carbonate ions in the *Porites* coral sample are greater than for the synthetic and other biogenic aragonite. The slight broadening of the *Porites* bands may possibly be attributed to a difference in the aragonite crystal size and habit. For a typical scleractinian coral, the skeletal matrix is made up of small acicular aragonite crystals on the order of 1–4 μm in diameter (Constantz, 1986). Although such aragonite crystals are sufficiently small to cause line broadening, the *Porites* band positions are, however, shifted to higher frequencies, which is opposite to the shift expected from reduced particle sizes (Sharma and Urmos, 1987). Variability in the Raman spectra of biogenic aragonite may, perhaps, be attributed more to variations in crystallite size or other factors than to crystal structure disorder, which, if it occurs in aragonite, is certainly not as pronounced as the disorder found in magnesian calcite.

SUMMARY AND CONCLUSIONS

The Raman spectroscopic results presented in this paper and previously by Bischoff et al. (1985) reveal that carbonate ion positional disordering is ubiquitous in both biogenic and synthetic magnesian calcite. An important

TABLE 2. Raman frequencies and half widths (cm^{-1}) for synthetic and biogenic aragonite

Sample	Lattice modes							ν_4	ν_2	ν_1	ν_3				
Aragonite (synthetic)	143	153	180	190	206	247	261	284	701	705	853	1085	1462	1574	
		(8.7)	(7.4)		(7.4)							(2.1)	(6.0)		
<i>Porites</i> coral	145	155	182	192	208	249	264	286	704	707	nm	1086	1463	1573	
		(9.6)	(7.4)		(8.1)							(4)	(10)		
Cultured pearl	144	153	180	190	206	246	261	283	701	705	nm	1085	1462		
		(8.7)	(6.0)		(7.4)							(2.2)	(6.5)		
Natural pearl	143	153	180	190	206	248	259	284	701	705	852	1085	1133	1462	1526
		(7.4)	(5.6)		(6.8)							(2.1)		(5.0)	(19.9)

Note: Half widths given in parentheses. The abbreviation nm = not measured.

aspect of these observations is that biogenic magnesian calcite phases exhibit greater positional disorder of the carbonate ion than does synthetic magnesian calcite with the same Mg^{2+} content (Fig. 1). A significant geological consequence of these different degrees of disordering is that these differences are, in part, responsible for different relative chemical reactivities of these phases during diagenesis. Disorder and other physical and chemical factors affecting the relative stabilities of various carbonate phases have been used by Bischoff et al. (in preparation) to propose a number of different possible reaction pathways for the diagenetic stabilization of magnesian calcite to more stable carbonates containing smaller concentrations of trace element impurities and less structural disorder.

As might be predicted from the typically low degree of trace element substitution in aragonite, which at most is ~1% for Sr^{2+} (Veizer, 1983), the Raman spectra for the biogenic aragonite samples do not show evidence of the type of carbonate ion positional disordering that typifies biogenic magnesian calcite. Thus other factors, such as crystallite size, may need to be considered when assessing the chemical reactivities of aragonite undergoing diagenesis.

Raman spectroscopy is a valuable tool for characterizing the microstructure of biogenic and synthetic carbonates. This method can also detect organic material, such as carotenoid pigment, that is closely associated with the mineral matrix of biogenic carbonate. Variations in the positions and half widths of the Raman-active modes provide evidence of the presence of rotational disordering of the carbonate ion in carbonates. This rotational disorder is evident in calcite, but not in aragonite, owing to the presence of solid solution between Ca^{2+} and Mg^{2+} and the greater concentration of trace impurities in calcite. Raman studies of biogenic magnesian calcite show that it typically has some degree of disorder that is greater than that in the equivalent synthetic materials. This disordering in biogenic materials has not been a widely recognized phenomenon. Such disordering in biogenic carbonates may play an important role in influencing the diagenetic behavior of these minerals.

ACKNOWLEDGMENTS

The critical reviews of R.J. Reeder and A.M. Hofmeister are gratefully acknowledged. The constructive suggestions of M.A. Bertram are appreciated. Some of the precious coral samples were generously provided by R. Grigg and K. Chave. We thank T. Hulsebosch for the microprobe analyses. Financial support was provided through NSF grants EAR-8508971 (S.K.S.) and EAR-8915536 (F.T.M.). School of Ocean and Earth Science and Technology Contribution No. 2400.

REFERENCES CITED

- Alexander, A.E. (1940) An X-ray study of aragonite in natural and cultured pearl. *American Journal of Science*, 238, 366–371.
- Bhagavantam, S., and Venkatarayudu, T. (1939) Raman effect in relation to crystallographic structure. *Proceedings of the Indian Academy of Sciences*, A13, 543–563.
- Bischoff, W.D., Bishop, F.C., and Mackenzie, F.T. (1983) Biogenically produced magnesian calcites: Inhomogeneities in chemical and physical properties; comparison with synthetic phases. *American Mineralogist*, 68, 1183–1188.
- Bischoff, W.D., Sharma, S.K., and Mackenzie, F.T. (1985) Carbonate ion disorder in synthetic and biogenic magnesian calcites: A Raman spectral study. *American Mineralogist*, 70, 581–589.
- Busenberg, E., and Plummer, L.N. (1985) Kinetic and thermodynamic factors controlling the distribution of SO_4^{2-} and Na^+ in calcites and selected aragonites. *Geochimica et Cosmochimica Acta*, 49, 713–725.
- Chave, K.E. (1984) Physics and chemistry of biomineralization. *Annual Review of Earth and Planetary Sciences*, 12, 293–305.
- Constantz, B.R. (1986) The primary surface area of corals and variations in their susceptibility to diagenesis. In J.H. Schroeder and B.H. Purser, Eds., *Reef Diagenesis*, p. 53–76. Springer-Verlag, New York.
- Couture, L. (1947) Étude des spectres de vibrations de monocristaux ioniques. *Annales de Physique*, 2, série 12, 5–94.
- Fox, D.L. (1972) Pigmented calcareous skeletons of some corals. *Comparative Biochemistry and Physiology*, 43B, 919–927.
- Hoskins, L.C., and Alexander, V. (1977) Determination of carotenoid concentrations in marine phytoplankton by resonance Raman spectrometry. *Analytical Chemistry*, 49, 695–697.
- Ismail, M.A., Jayasooriya, V.A., and Kettle, S.F.A. (1982) Spectral intensities of the internal vibrational modes of species with the aragonite crystal structure. *Journal of Molecular Structure*, 79, 349–351.
- Lowenstam, H.A., and Weiner, S. (1989) *On biomineralization*, 324 p. Oxford University Press, New York.
- Mackenzie, F.T., Bischoff, W.D., Bishop, F.C., Loijens, M., Schoonmaker, J., and Wollast, R. (1983) Magnesian calcites: Low-temperature occurrence, solubility and solid-solution behavior. In *Mineralogical Society of America Reviews in Mineralogy*, 11, 97–144.
- Merlin, J.C. (1985) Resonance Raman spectroscopy of carotenoids and carotenoid-containing systems. *Pure and Applied Chemistry*, 57, 758–792.
- Merlin, J.C., and Delé, M.L. (1983) Étude par spectroscopie Raman de résonance de la pigmentation des squelettes calcaires de certains coraux. *Bulletin de la Société Zoologique de France*, 108, 289–301.
- Merlin, J.C., and Delé-Dubois, M.L. (1986) Resonance Raman characterization of polyacetylenic pigments in the calcareous skeleton. *Comparative Biochemistry and Physiology*, 84B, 97–103.
- Morse, J., and Mackenzie, F.T. (1990) *Geochemistry of sedimentary carbonates*, 707 p. Elsevier, New York.
- Rimai, L., Heyde, M.E., and Giu, D. (1973) Vibrational spectra of some carotenoids and related linear polyenes. A Raman spectroscopic study. *Journal of the American Chemical Society*, 95, 4493–4501.
- Rousseau, D.L., Miller, R.F., and Leroi, G.E. (1968) Raman spectrum of crystalline sodium nitrate. *Journal of Chemical Physics*, 48, 3409–3413.
- Saito, S., and Tasumi, M. (1983) Normal coordinate analysis of β -carotene isomers and assignments of the Raman and infrared bands. *Journal of Raman Spectroscopy*, 14, 310–321.
- Sharma, S.K., and Urmos, J.P. (1987) Micro-Raman spectroscopic studies of materials at ambient and high pressures with CW and pulsed lasers. In R.H. Geiss, Ed., *Microbeam analysis—1987*, p. 133–136. San Francisco Press, San Francisco.
- Veizer, J. (1983) Trace elements and isotopes in sedimentary carbonates. In *Mineralogical Society of America Reviews in Mineralogy*, 11, 265–300.
- White, A.F. (1975) Sodium and potassium coprecipitation in calcium carbonate. Ph.D. dissertation, Northwestern University, Evanston, Illinois.
- White, W.B. (1974) The carbonate minerals. In V.C. Farmer, Ed., *The infrared spectra of minerals*. Mineralogical Society Monograph 4, p. 227–284. Mineralogical Society, London.
- Wilkinson, G.R. (1973) Raman spectra of ionic, covalent, and metallic crystals. In A. Anderson, Ed., *The Raman effect*, vol. 2: Applications, p. 811–893. Dekker, New York.
- Yamamoto, A., Shiro, Y., and Murata, H. (1974) Optically-active vibrations and elastic constants of calcite and aragonite. *Bulletin of the Chemical Society of Japan*, 47, 265–273.

MANUSCRIPT RECEIVED MAY 21, 1990

MANUSCRIPT ACCEPTED JANUARY 7, 1991