

Dehydration mechanism of clinoptilolite and heulandite: Single-crystal X-ray study of Na-poor, Ca-, K-, Mg-rich clinoptilolite at 100 K

THOMAS ARMBRUSTER

Laboratorium für chemische und mineralogische Kristallographie, Universität Bern, Freiestrasse 3, CH-3012 Bern, Switzerland

ABSTRACT

The crystal structure of clinoptilolite from Weitendorf, Styria, Austria [$a = 17.622(2)$, $b = 17.895(2)$, $c = 7.399(1)$ Å, $\beta = 116.45(2)^\circ$, space group $C2/m$], $(Mg_{0.9}Ca_{1.4}Sr_{0.1}Ba_{0.3}K_{1.2}Na_{0.4})Al_7Si_{29}O_{72} \cdot 25H_2O$, was studied by single-crystal X-ray diffraction. The structures of a fully hydrated form (25 H₂O) and three partially dehydrated forms with 7–5 H₂O were refined at 100 K. The dehydration is accompanied by cation diffusion within the channel system. Four cation positions (Na1, Ca2, K3, Mg4) were found in the channels of the highly hydrated form. With loss of H₂O, cations migrate preferentially to site K3 at the center of a distorted eight-membered ring of tetrahedra, forming channels parallel to *a*. In the 5H₂O variant [$a = 17.61(1)$, $b = 17.456(7)$, $c = 7.360(7)$ Å, $\beta = 116.77(4)^\circ$], H₂O is strongly disordered, but the framework remains expanded. With progressing dehydration, disorder in the tetrahedral framework is reflected in increasing atomic displacement parameters and decreased T-O distances.

The thermal stiffness of the heulandite-clinoptilolite framework is related to the Al concentration on T2, which governs the bond strength between O1 and Ca2. A small Al concentration on T2 enables cation diffusion to occur from Ca2 to K3 upon heating. High occupancies of large cations on K3 prevent the structure from collapsing.

INTRODUCTION

Clinoptilolite and heulandite are monoclinic zeolite minerals characterized by large, intersecting open channels of ten- and eight-membered tetrahedral rings. The large ten-membered A ring and the smaller eight-membered B ring confine channels parallel to *c*. Type C channels parallel to *a* are also formed by eight-membered rings and connect A and B channels (Merkle and Slaughter, 1968). The channels are occupied by cations and H₂O.

It is well known that zeolites of the heulandite-clinoptilolite group react differently upon heating depending on their chemical composition (e.g., Alietti et al., 1974; Alberti and Vezzalini, 1983; Bish, 1984, 1988). This difference has even been used to distinguish clinoptilolite from heulandite (Mumpton, 1960; Boles, 1972). Bish (1984) reviewed the literature on dehydration of this mineral group and suggested that especially the low-temperature dehydration behavior is of interest because clinoptilolite-bearing tuffs at Yucca Mountain, Nevada, were being investigated as a potential repository for high-level radioactive wastes (Smyth, 1982). The Na, K, and Ca content of clinoptilolite-heulandite varies significantly in many deposits; thus dehydration must be investigated within the composition range of the natural material. Low-temperature dehydration was monitored in most previous experiments with X-ray powder diffraction, differential thermogravimetry (DTG), and differential thermoanaly-

sis (DTA) techniques; thus only the change of cell dimension with H₂O loss was determined, and the exact mechanism of dehydration remains unclear.

In a previous single-crystal X-ray dehydration study (Armbruster and Gunter, 1991) clinoptilolite-heulandite, $Ca_{2.1}Mg_{0.3}Na_{2.5}K_{0.28}Al_{8.0}Si_{28.2}O_{72} \cdot 25.5H_2O$, was stepwise dehydrated in a dry N₂ atmosphere, and the structure was subsequently studied at 100 K. Annealing 1 h at 448 K in a dry atmosphere was sufficient to expel most of the H₂O and to produce a heat-collapsed structure with identical tetrahedral framework topology, but strongly altered T-O-T angles and decreased cell volume (1864 vs. 2097 Å³).

Koyama and Takéuchi (1977) suggested that K in K-rich clinoptilolite is positioned almost in the center of the C channel, thereby inhibiting collapse of the framework structure. This was confirmed by Galli et al. (1983), who studied a K-exchanged heulandite sample with single-crystal data up to 593 K and observed only a slight contraction of the framework structure [cell volume before heating: 2132(1) Å³; after heating excursion: 2012(2) Å³]. However, the population of channel cations in this exchanged sample is much higher than those of most natural samples, which could also influence the stability of the expanded cavities. In the present study, clinoptilolite with a complex cation composition within the structural cavities was selected. The aim of this investigation is to understand the dehydration mechanism and the accompanying structural distortions.

TABLE 1. Data measurement and refinement parameters for clinoptilolite from Weitendorf, Styria, at 100 K

	Natural	Dehyd1	Dehyd2	Dehyd3
Composition: (Mg _{0.9} Ca _{1.4} Sr _{0.1} Ba _{0.3} K _{1.2} Na _{0.4})Al ₇ Si ₂₉ O ₇₂ · nH ₂ O				
Crystal size: 0.15 × 0.15 × 0.15 mm				
Space group: C2/m				
Radiation: MoK α				
Scan type: ω				
Scan width (°)	1.5	1.5	2.5	2.5
a (Å)	17.622(2)	17.588(2)	17.619(6)	17.61(1)
b (Å)	17.895(2)	17.572(4)	17.503(4)	17.456(7)
c (Å)	7.399(1)	7.389(2)	7.371(3)	7.360(7)
β (°)	116.45(2)	116.77(2)	116.71(4)	116.77(4)
Max. θ (°)	30	30	30	30
Measured reflections	2333	2008	2003	2014
Observed unique reflections >3 σ (I)	1560	1463	1293	1225
No. of parameters	209	184	178	178
R (%)	3.33	3.97	4.29	4.31
R _w (%)	4.64	5.79	5.42	5.31

Note: $R = \frac{\sum |F_{\text{obs}}| - |F_{\text{calc}}|}{\sum |F_{\text{obs}}|}$. $R_w = \left[\frac{\sum w(|F_{\text{obs}}| - |F_{\text{calc}}|)^2}{\sum w|F_{\text{obs}}|^2} \right]^{1/2}$.

EXPERIMENTAL PROCEDURE

The clinoptilolite sample is from the basalt at Weitendorf, Styria, Austria (Armbruster et al., 1991). The composition, (Mg_{0.9}Ca_{1.4}Sr_{0.1}Ba_{0.3}K_{1.2}Na_{0.4})Al₇Si₂₉O₇₂ · 25H₂O, was determined with an ARL-EMX-SM electron microprobe operating at 15 kV and 20 nA with a defocused beam (20 μ m). With Na + K (1.6) > Ca (1.4) and Si/Al = 4.14, the sample fulfills both definitions of a clinoptilolite (Mason and Sand, 1960; Boles, 1972). The H₂O content was estimated from structure refinements described below.

Single-crystal data collection

Single-crystal X-ray data were obtained at 100 K with an Enraf-Nonius CAD-4 diffractometer (graphite-monochromatized MoK α radiation) using a conventional liquid-N₂ cooling device. Experimental details were described by Armbruster and Gunter (1991) and are summarized in Table 1. The natural crystal was immersed in H₂O for several weeks and subsequently quenched to 100 K on the diffractometer (sample: natural). After data measurement the same crystal was kept on the diffractometer, flushed for 2.5 h with dry N₂ at 373 K and quenched to 100 K for data measurement (sample: dehyd1). This procedure was repeated after flushing 4 h at 413 K (sample: dehyd2) and 1 h at 473 K (sample: dehyd3). Cell dimensions were determined for all samples with reflections 15° > θ > 10°. With progressive dehydration the X-ray reflections became streaked along the ω direction, and the scan angle had to be varied within the various data sets (Table 1). Absorption was tested by ψ scans, but the effect was considered insignificant, and the correction was not applied. The program SHELX76 (Sheldrick, 1976) was used for structure refinement with a 1/ σ^2 weighting scheme. The populations of the channel cation sites Na1, Ca2, K3, and Mg4 were refined with Na, Ca, K, and Mg scattering factors. In addition, all Ba found by electron microprobe analyses was constrained to occupy K3. For estimates of site oc-

cupancies of various species, it was assumed that Ca and K have about twice and Sr four times as many electrons as Na. Resulting T-O distances were used to estimate Si/(Al + Si) for each site, using the same method as Koyama and Takéuchi (1977). Corresponding Si,Al scattering factors were introduced for the tetrahedral cations in the subsequent refinement cycles. For additional details and nomenclature of atomic sites see Armbruster and Gunter (1991). Final difference Fourier maps of all samples showed maximum peaks and minima of about ± 0.7 e/Å³.

RESULTS

Dehydration was accompanied by a change in cell dimensions, which is most pronounced along **b** (Table 1). Based on site-occupancy refinements, H₂O in the natural sample amounts to 25 H₂O pfu. Flushing the crystal with dry N₂ at 373 K reduced the H₂O content to 7 H₂O (dehyd1), and in dehyd3 only 5 H₂O pfu were detected (Fig. 1). The dehydration within the investigated temperature range does not lead to formation of a heat-collapsed phase (e.g., Armbruster and Gunter, 1991). Observed and calculated structure factors for all structures are given in Table 2¹; positional parameters and occupancies are summarized in Table 3; and anisotropic displacement parameters are listed in Table 4. Table 5 shows T-O distances, T-O-T angles, and M-O distances for channel cations.

Natural sample

In agreement with Koyama and Takéuchi (1977) and Armbruster and Gunter (1991), four cation sites (Na1, Ca2, K3, Mg4) were resolved in the fully hydrated sample within the channel system (Fig. 1). Na1 is 2.08 Å from K3 and 2.25 Å from Mg4; thus these sites are too close to one another to be occupied simultaneously. Na1 oc-

¹ A copy of Tables 2, 3, 4, and 5 may be ordered as Document AM-93-517 from the Business Office, Mineralogical Society of America, 1130 Seventeenth Street NW, Suite 330, Washington, DC 20036, U.S.A. Please remit \$5.00 in advance for the microfiche.

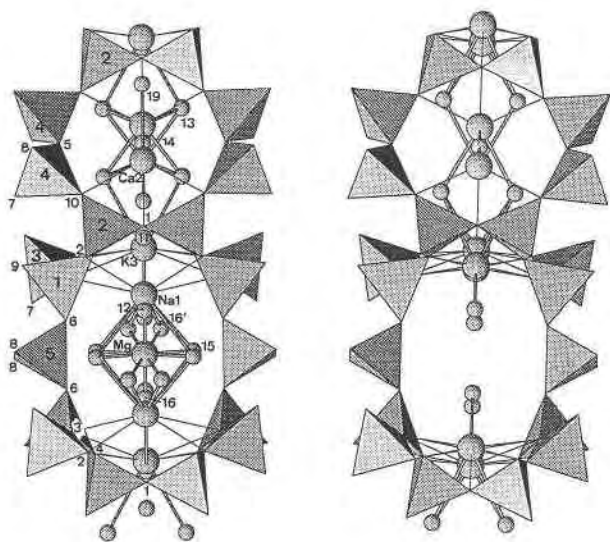


Fig. 1. Projection along [001], displaying the large A channel confined by ten tetrahedra and the B channel by eight-membered rings. Thin lines connect channel cations with coordinating framework O, thick bonds are drawn between channel cations and H₂O. (Left) sample natural; (right) sample dehyd3.

cupancy 0.1 Na and 0.19 K) is coordinated by $2 \times O2$ (2.83 Å) and $2 \times O3$ (3.10 Å) of the tetrahedral framework and five H₂O molecules [O16' (2.48 Å), O11 (2.74 Å), and $2 \times O15$ (2.91, 3.00 Å)]. O16' and O15 were highly disordered and refined as split positions. Assignment of additional K to the Na1 position is justified by the refined population (greater than the analyzed Na content) and by the long Na1-O distances. The maximum occupancy of Ca2 is 0.5 because its symmetry-equivalent at $-x, -y, -z$ is too close to permit occupancy of both sites. Ca2 (occupancy 0.35 Ca and 0.04 K) is eightfold-coordinated with $2 \times O10$ (2.75 Å), $1 \times O1$ (2.55 Å) of the framework, and five H₂O molecules [$4 \times O13$ ($2 \times 2.42, 2 \times 2.57$ Å)], and $1 \times O14$ (3.07 Å)]. K3 (occupancy 0.08 Ba, 0.07 K, 0.03 Sr) is coordinated by six framework O atoms [$2 \times O2$ (3.18 Å), $2 \times O3$ (2.98 Å), $2 \times O4$ (3.07 Å)]. The coordination is completed by two H₂O molecules at O13 (3.08 Å). Mg4 (occupancy 0.36 Mg) is not bonded to any framework O but the coordination can be described as a disordered octahedral [Mg(H₂O)₆]²⁺ ion [$2 \times O15$ (1.91 Å), $2 \times O12$ (2.03 Å), $2 \times O16'$ (2.16 Å)] centered in the ten-membered ring of tetrahedra defining the A channels. The disorder is caused by the split character of O15 and O16'. The above assignments leave O16 and O19 as H₂O molecules that are not coordinated by cations. The refined position O12, which has large and strongly anisotropic displacement parameters (Table 4), is a mixture of the H₂O sites O12 and O12'. These positions are only 0.7 Å apart (Hambley and Taylor, 1984). O12 is coordinated to K3 and Mg4, whereas O12' is a H₂O molecule not bonded to channel cations. The contribution of O12' is lost upon dehydration, and the displacement parameters become

more isotropic. The disordered character of O12 is also responsible for the short Na1-O12 and K3-O12 distances.

Sample dehyd1 (2.5 h at 373 K)

O16 and O19 became vacant, and the populations of all other H₂O positions decreased significantly. Position Na1 approached site K3 (Fig. 1). The distance Na1-K3 decreased to 1.3 Å. The electron density at Na1 decreased significantly, with Na1-O distances becoming shorter, suggesting that K diffused from Na1 to K3 (K3 increased in population). The new Na1 site (occupancy 0.10 Na and 0.09 K) is coordinated by $2 \times O2$ (2.58 Å), $2 \times O3$ (2.76 Å), and H₂O on O12 (2.47 Å). Cations on Ca2 moved preferentially to K3; in turn the electron density at Ca2 was reduced by 50%, leading to a Ca population of 0.22. The Ca2-O distances became significantly shorter compared with those of the fully hydrated sample. As a consequence of the Ca2 → K3 diffusion, the population of K3 increased [0.33(K,Ca)] but its position and O coordination were unchanged. K3 became coordinated by two satellite positions (K3₁ and K3₂) with small populations. K3₁ has two distances to framework O4 of about 1.97 Å and one of 1.93 Å to H₂O at O18. It is very likely that Mg moved to K3, because the electron density at Mg4 was no longer detectable. K3₂ has four distances to framework O of about 2.7 Å and is also coordinated by O12 (2.33 Å) and O18 (2.80 Å). The low population and characteristic distances thus suggest that this site is mainly occupied by Sr.

Samples dehyd2 and dehyd3

Both samples are very similar and therefore are discussed together. The populations of O atoms related to H₂O agree within 3σ for both samples, which both contain approximately 5 H₂O pfu. However, displacement parameters are significantly greater for dehyd3. The populations of Na1 and Ca2 further had decreased, and those for K3 increased. Satellite position K3₁ could no longer be resolved. Residual H₂O on O13 (occupancy 0.37) is significantly disordered and coordinates K3. The high displacement parameter U_{22} indicating that this O13 is a mixture of O13 (general position) and O13' (on the mirror plane), as refined by Hambley and Taylor (1984) and Armbruster and Gunter (1991), is striking. Splitting into two sites was not considered for this sample because of low occupancy. Ca2 possesses sixfold coordination [$2 \times O13$ (2.79 Å), $1 \times O14$ (2.10 Å), $2 \times O10$ (2.61 Å), and $1 \times O1$ (2.20 Å)]. The largest changes in corresponding T-O-T angles between the fully hydrated sample and dehyd3 were observed for T1-O3-T3, which decreased 6.5°, and T4-O5-T4, which increased 5.4° with dehydration.

DISCUSSION

Dehydration of the Weitendorf sample leads to an apparent decrease of T-O distances (up to 0.03 Å). This decrease cannot be related to changes in T-O-T angles

(e.g., Hill and Gibbs, 1979). As an example, T4-O5-T4 increases because of dehydration from $143.9(3)^\circ$ to $149.3(6)^\circ$; however, T4-O5 distances become shorter by 0.03 \AA (corresponding to 10σ). The influence of broken H bridges as a consequence of dehydration cannot also be responsible for shortened T-O distances. H14, bonded to O14 (fully occupied in the natural sample), was localized by Hambley and Taylor (1984) by neutron diffraction for natural heulandite. Judging from bond valence calculations for O5, which has a $O5 \cdots H14$ distance of ca. 2.3 \AA , this H bond is by far too weak to cause the observed T4-O5 change. The influence of channel cations must also be ruled out because O5 has none in its neighborhood. However, from sample natural to dehyd3, B_{eq} of O1 and O5 increased by factors of 3.1 and 3.3, respectively, indicating that rigid rotational disorder of TO_4 units is largely responsible for T-O shortening. There is a general and continuous increase of B_{eq} for framework atoms with dehydration reflecting this increasing disorder. A similar but less pronounced increase of B_{eq} was observed for partially dehydrated (dehyd3) Succor clinoptilolite-heulandite (Armbruster and Gunter, 1991). With additional dehydration, displacement parameters of various critical O positions (e.g., O1) even decreased in the heat-collapsed Succor structure (dehyd4). This suggests that Succor dehyd3 and Weitendorf dehyd3 represent strongly strained structures where heat-collapsed domains may already exist. This is also confirmed by the anisotropy of O1 displacement parameters, for which the largest increase was parallel to a upon dehydration (the heat-collapsed structure is characterized by a large shift of O1 along a). The increase of R values (Table 1) from the natural sample to dehyd3 indicates that a harmonic vibrational model is not sufficient to simulate this disorder. Additional dehydration (dehyd4) of the Succor sample (Armbruster and Gunter, 1991) led to release of strain due to formation of a heat-collapsed variant, whereas in the Weitendorf sample the strained variant persists.

The dehydration conditions of clinoptilolite-heulandite from Succor Creek, $Ca_{2.1}Mg_{0.3}Na_{2.5}K_{0.28}Al_{8.0}Si_{28.2}O_{72} \cdot nH_2O$ (Armbruster and Gunter, 1991), leading to sample dehyd3 were almost identical to those yielding dehyd1 in this study (373 K, dry N_2). However, in the Succor sample (dehyd3) 14 H_2O pfu were found, whereas only 7 H_2O were localized in the corresponding Weitendorf sample. Also similar to these investigations are the neutron diffraction experiments by Hambley and Taylor (1984), who studied a sample with the composition $Ba_{0.1}Sr_{0.1}Ca_{2.2}Na_{1.4}Al_{7.9}Si_{28.5}O_{72} \cdot nH_2O$ from Coonabarabran in its natural state and after treatment in vacuum at 343 K. After these moderate dehydration conditions, the H_2O content is mainly related to the Ca concentration. This is also in agreement with the high enthalpy of hydration (-1580 kJ/mol) known for Ca (Barrow, 1973). The higher Ca content of the Succor and Coonabarabran sample maintains higher O13 and O14 (coordinated to site Ca2) populations at this dehydration level, whereas reduced pop-

ulations are observed in this study for a sample with smaller Ca content.

At first glance it may appear surprising that, in spite of its high K content, a low K3 occupancy was found for the natural Weitendorf sample. However, framework O2 and O3 are coordinated similarly to both K3 and Na1. In the fully hydrated sample, K prefers a large H_2O coordination number, which is available at Na1. Only depletion of H_2O forces K to move to K3. The partial dehydration of K is promoted by its low enthalpy of hydration of -320 kJ/mol (Barrow, 1973). In contrast, the K-rich clinoptilolite studied by Koyama and Takéuchi (1977) was also rich in Na; thus the Na1 site was preferred by Na, and all K was placed in K3.

These new data support the conclusions summarized by Hambley and Taylor (1984); channel occupation of various cations and substitution of Al for Si play an interrelated role in determining the thermal stability of these zeolites. In all minerals of the heulandite-clinoptilolite group, T2 is preferentially occupied by Al, as T2-O are the longest T-O distances within the structure (e.g., Koyama and Takéuchi, 1977; Alberti, 1975; Hambley and Taylor, 1984; Smyth et al., 1990; Armbruster and Gunter, 1991). A key to understanding the thermal stability of this mineral group is in the manner in which O1 links the two T2 tetrahedra. Considering only the framework structure, O1 is underbonded, owing to relatively large Al content on T2 (30% in the Weitendorf sample). In addition, O1 is coordinated to the channel site Ca2. Thus the bond strength between Ca2 and O1 will be dependent on the Al population on T2. In heulandite samples with high Al contents Ca2 will be situated in the neighborhood of O1 (Hambley and Taylor, 1984; Armbruster and Gunter, 1991). As an example, the population of Ca2 of Succor sample dehyd3 was only slightly smaller (occupancy 0.33) than that of the fully hydrated sample (occupancy 0.37). In Al-poor clinoptilolite, cations on Ca2 may easily diffuse to other channel positions, such as K3, as observed in the present investigation. Koyama and Takéuchi (1977) suggested that large cations on K3 plug the C channel (Fig. 2), which prevents the structure from collapsing. This also explains why the framework structure of the K-poor, Al-rich Succor sample collapsed during heating to 448 K, whereas the K-rich, Al-poor Weitendorf sample did not collapse on heating to 473 K.

Based on the above observations of complex natural samples, the dehydration experiments of Alietti et al. (1974) on cation-exchanged (Na,K,Ca) clinoptilolite (their no. 23) and heulandite (their no. 24) can be better understood. For both framework compositions, the K-exchanged variants did not collapse with heating up to 1073 K. Galli et al. (1983) showed for a K-exchanged heulandite (9.3 Al pfu) that three types of K channel positions exist: (1) a ten-membered ring site, (2) a channel wall site (corresponding to K3), and (3) an eight-membered ring site (corresponding to Ca2). At 573 K the site in the eight-membered ring (bonded to O1) was 65% occupied by K; the site at the channel wall (K3) had a K occupancy of

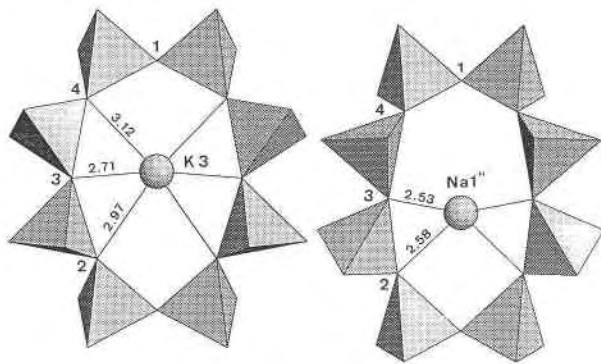


Fig. 2. Projection along [100] displaying type-C channels confined by eight-membered rings, which are plugged by cations. (Left) sample Weitendorf dehyd3; (right) heat-collapsed structure dehyd4 from Succor (Armbuster and Gunter, 1991).

70%. Thus both criteria are fulfilled, O1 (underbonded because of significant Al on T2) is coordinated to K, and occupancy of K3 is large, preventing the structure from collapsing (Fig. 2). In addition, the K position in the ten-membered ring has K-O distances to framework O4 and O6 of 2.8–3.1 Å, which reduces compression. Structural data for K-exchanged clinoptilolite do not exist, but we may assume from these experiments and those of Koyama and Takéuchi (1977) that with increasing dehydration, K moves to K3, which keeps the channels expanded (Fig. 2). In contrast to heulandite, the small Al population of T2 allows very low occupancies of Ca2.

Both Na exchanged heulandite and clinoptilolite collapse below 473 K (Alietti et al., 1974). In both minerals cation sites Na1 and Ca2 are occupied by Na. In heulandite site Ca2 is expected to be preferred by Na because of the coordination to the underbonded O1 atom. With progressive dehydration Na will migrate from Na1 to a site closer to the channel wall position (K3). However, Na is too small to maintain expansion of the channels (Fig. 2), and the structure must collapse.

Ca-exchanged clinoptilolite and heulandite collapse (Alietti et al., 1974). The concentration of divalent Ca is only half those of Na or K for a given Al substitution in the framework. Ca in heulandite is concentrated at Ca2 neighboring O1. Excess Ca is located at Na1. Ca is too small to keep the channels open even if it diffuses to K3. Furthermore, occupation of K3' (Armbuster and Gunter, 1991) in the center of the ten-membered ring (at 000) of a collapsed cavity is a preferred site for Ca, with 4 (K3'-O) of 2.15 Å. The collapse of the Ca-exchanged clinoptilolite (no. 23) of Alietti et al. (1974) is much more pronounced than that of Ca-exchanged clinoptilolite from Castle Creek, Idaho, of Bish (1984), which is related to the higher stabilizing (not exchanged) K content of the latter sample.

The complex dehydration behavior of natural clinoptilolite and heulandite depends on the concentration of large cations, such as K, Cs, and Ba, and the Al concentration in the framework, which governs the Ca2 population.

REFERENCES CITED

- Alberti, A. (1975) The crystal structures of two clinoptilolites. *Tschermaks mineralogische und petrographische Mitteilungen*, 22, 25–37.
- Alberti, A., and Vezzalini, G. (1983) The thermal behaviour of heulandites: A structural study of the dehydration of the Nadap heulandite. *Tschermaks mineralogische und petrographische Mitteilungen*, 31, 259–270.
- Alietti, A., Gottardi, G., and Poppi, L. (1974) The heat behavior of the cation exchanged zeolites with heulandite structure. *Tschermaks mineralogische und petrographische Mitteilungen*, 19, 291–298.
- Armbuster, Th., and Gunter, M.E. (1991) Stepwise dehydration of a heulandite-clinoptilolite from Succor Creek, Oregon, U.S.A.: A single-crystal X-ray study at 100 K. *American Mineralogist*, 76, 1872–1883.
- Armbuster, Th., Wenger, M., and Kohler, Th. (1991) Mischkristalle von Klinoptilolith-Heulandit und Harmotom-Phillipsit aus dem Basalt von Weitendorf, Steiermark. *Mitteilungen der Abteilung für Mineralogie des Landesmuseum Joanneum*, 59, 13–18.
- Barrow, G.M. (1973) *Physical chemistry*, 646 p. McGraw-Hill, New York.
- Bish, D.L. (1984) Effects of exchangeable cation composition on the thermal expansion/contraction of clinoptilolite. *Clays and Clay Minerals*, 32, 444–452.
- (1988) Effects of composition on the dehydration behavior of clinoptilolite and heulandite. In D. Kallo and H.S. Sherry, Eds., *Occurrence, properties, and utilization of natural zeolites*, p. 565–576. Akademiai Kiado, Budapest.
- Boles, J.R. (1972) Composition, optical properties, cell dimensions, and thermal stability of some heulandite group zeolites. *American Mineralogist*, 57, 1463–1493.
- Galli, E., Gottardi, G., Mayer, H., Preisinger, A., and Passaglia, E. (1983) The structure of a potassium-exchanged heulandite at 293, 373 and 593 K. *Acta Crystallographica*, 39B, 189–197.
- Hambley, T.W., and Taylor, J.C. (1984) Neutron diffraction studies on natural heulandite and partially dehydrated heulandite. *Journal of Solid State Chemistry*, 54, 1–9.
- Hill, R.J., and Gibbs, G.V. (1979) Variation in $d(T-O)$, $d(T\cdots T)$ and TOT in silica and silicate minerals, phosphates and aluminates. *Acta Crystallographica*, 35B, 25–30.
- Koyama, K., and Takéuchi, Y. (1977) Clinoptilolite: The distribution of potassium atoms and its role in thermal stability. *Zeitschrift für Kristallographie*, 145, 216–239.
- Mason, B., and Sand, L.B. (1960) Clinoptilolite from Patagonia: The relationship between clinoptilolite and heulandite. *American Mineralogist*, 45, 341–350.
- Merkle, A.B., and Slaughter, M. (1968) Determination and refinement of the structure of heulandite. *American Mineralogist*, 53, 1120–1138.
- Mumpton, F.A. (1960) Clinoptilolite redefined. *American Mineralogist*, 45, 351–369.
- Sheldrick, G.M. (1976) SHELX76. Program for crystal structure determination. University of Cambridge, Cambridge, England.
- Smyth, J.R. (1982) Zeolite stability constraints on radioactive waste isolation in zeolite-bearing volcanic rocks. *Journal of Geology*, 90, 195–201.
- Smyth, J.R., Spaid, A.T., and Bish, D.L. (1990) Crystal structures of a natural and a Cs-exchanged clinoptilolite. *American Mineralogist*, 75, 522–528.