

EPR-determined site distributions of low concentrations of transition-metal ions in minerals: Review and predictions

AGLAIA B. VASSILIKOU-DOVA

Department of Physics, University of Athens, Panepistimiopolis, GR 15784 Zografos, Greece

ABSTRACT

Data for distribution of small concentrations (up to 1% per site) of Mn^{2+} , Fe^{3+} , Cr^{3+} , and V^{4+} among different sites in minerals determined by electron paramagnetic resonance are reviewed. In some cases a decision between controversial site assignments can be made. In cases where only one site is occupied, the results enable one to state qualitative rules for site preferences. Kinetic factors, rather than equilibrium relations, are found to be important in certain cases, but considerably more systematic study is required to allow correlation with the growth conditions or thermal history of a mineral.

INTRODUCTION

In an interesting review (Hawthorne, 1983), electron paramagnetic resonance (EPR) is listed among the less-developed methods for quantitative determination of site occupancies. However, for most transition metals and for rare earth ions that are present only in small amounts (up to about 1% per site), it still is the most powerful method. That is because this method gives unambiguous information about the valence state and site symmetry, and, at least for some ions, it enables precise determination of geometries (distortions of their first coordination spheres) from characteristics of their EPR spectra. Thus, occasionally, controversial site assignments can be unambiguously determined, provided the crystal structure of the pure host compound is known with sufficient accuracy.

Three areas of increasing complexity are of interest in connection with site distributions of transition-metal ions in minerals: (1) distribution ratios and their variability for minerals from different geochemical environments and with different growth and thermal histories, (2) factors controlling these distributions, namely equilibrium or kinetic factors during crystal growth or changes thereafter, and (3) determination of differences in site distribution energy (in the case of equilibrium distributions or of activation energies), kinetic control during crystal growth, and elucidation of the underlying causes.

The present study concentrated on ions for which sufficient data are available in the literature, namely, Cr^{3+} , Mn^{2+} , Fe^{3+} , and V^{4+} . Preference for occupancy of a special site by these ions depends mainly on their nature and surroundings, and it can be constrained in connection with the following considerations.

SITE PREFERENCE ENERGY

Evidently, the site preference energy (or ligand field stabilization energy, $\Delta LFSE$) for Cr^{3+} (Fig. 1) is so large that it can substitute only in sites of octahedral symmetry. The absence of any site preference energy for the isoelec-

tronic d^3 ions, Mn^{2+} and Fe^{3+} , in sixfold- or fourfold-coordinated sites suggests that substitution of them is affected by other factors.

The site preference energy of Cr^{3+} favors occupation of Al sixfold-coordinated sites, e.g., in spinels, garnets, and topaz (Burns, 1970; Petrov et al., 1977), as has been known for a long time. Almost exclusive occupation of Al sixfold-coordinated interstitial sites by this ion in berlinite may be ascribed to the same cause. The intrasite partition coefficient K between sixfold- and fourfold-coordinated sites is greater than 100 in favor of interstitial sixfold sites (Henning et al., 1967). Although no EPR spectra were detected for Cr^{3+} for the distorted interstitial octahedral sites, most likely because they were broadened beyond detection by static disorder, the optical absorption spectra can be used for precise site assignment.

In andalusite two crystallographically nonequivalent Al sites are present with sixfold- and fivefold-coordination according to Burnham and Buerger (1961). However, a more recent investigation (Papendick et al., 1988) proposes fourfold- instead of the fivefold-coordination. Since EPR spectra of Cr^{3+} from only one center were observed (Vinokurov et al., 1962; Holuj et al., 1966), Cr^{3+} can be assigned unambiguously to the sixfold-coordinated site, although the differences between distortion from superposition model analysis (SPM) and zero field splitting patterns (ZFS) indicate a pronounced local relaxation around this ion (Buscher et al., 1987). The same combination of Al sites is found in sillimanite (Winter and Ghose, 1979). Again only the sixfold-coordinated site was found to be occupied by Cr^{3+} (Le Marshall et al., 1971).

Mn^{2+} was found to occupy the interstitial sixfold-coordinated sites in berlinite (Behner et al., 1986). Only the central transition of this ion could be observed, indicating a high static disorder, as in the case of Cr^{3+} . In addition, the ^{55}Mn hyperfine splitting resolved at Q-band frequencies led to the site assignment. Similar results were obtained for Mn^{2+} in quartz (Rao et al., 1989); exclusive occupancy of the Al sixfold-coordinated interstitial site

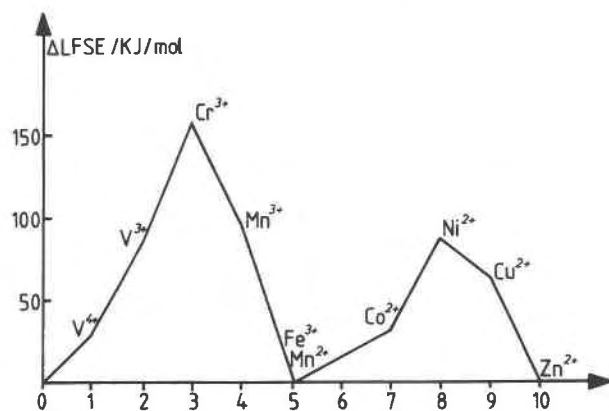


Fig. 1. Site preference energies for octahedral coordination of transition-metal d^n ions with O as ligand.

could be explained in terms of kinetic factors relating to the coordination of Mn^{2+} in the growth medium, even though the large difference in ionic radii of Al and Mn does not favor incorporation into the tetrahedral sites in quartz.

Fe^{3+} is found in both tetrahedral and interstitial sites in quartz (Stegger and Lehmann, 1989). Although substitution in tetrahedral sites is always dominant in amethyst, synthetic crystals with exclusive occupancy of Fe^{3+} in interstitial sites have been hydrothermally grown using seed crystals flattened on [001] with preferential growth along the c axis. Thus, seed orientation (or growth plane) seems to be an important kinetic factor. Although an overwhelming body of evidence in favor of occupancy of the interstitial sites has accumulated (Stegger and Lehmann, 1989), this relation is still disputed, and a substitutional center without local charge compensation has been proposed instead (Mombourquette and Weil, 1987; Mombourquette et al., 1989; Minge et al., 1989a, 1989b, 1990; Choi and Weil, 1970).

For Fe^{3+} in berlinite, the same kind of interstitial incorporation was postulated on the basis of an SPM analysis (Heming and Lehmann, 1987) of its ZFS pattern, which implies an axis of compression along the threefold screw axis, like the interstitial center in quartz (Behner et al., 1986). The fourfold- and sixfold-coordinated sites in sillimanite were both indicated, as in the case of andalusite (Holuj and Jesmanowicz, 1978), to be occupied by Fe^{3+} (Le Marshall et al., 1971).

THE SIZE MISMATCH

For ions occupying sites of smaller host ions, the largest site is preferentially occupied, and thus the size mismatch is minimized. This principle appears to hold in numerous cases, e.g., for Fe^{3+} and Cr^{3+} in Al sites, as shown by SPM analyses (Newman and Urban, 1975) of ZFS data (Buscher et al., 1987).

Cr^{3+} preferentially occupies (Barry and Troup, 1970; Troup et al., 1982) the larger M1 of the two sixfold-co-

ordinated sites in chrysoberyl (Farbell et al., 1963), whereas in synthetic crystals grown from the melt, an intrasite partition coefficient higher than 3 (Forbes, 1983) was determined in favor of the same site. In zoisite, exclusive occupancy of the larger Al1 site by Cr^{3+} (Hutton, 1971) is not surprising, in view of the large difference in average bond lengths of 0.08 Å (Dollase, 1968) between Al1 and Al2 sites.

Like Cr^{3+} , Fe^{3+} shows preference for the larger sites in chrysoberyl and zoisite. However, exclusive occupancy of the slightly larger Al1 site ($\Delta R = 0.01$ Å) in cordierite (Gibbs, 1966) is indeed surprising (Hedgecock and Chakravarty, 1966). No site assignment was proposed initially by Hedgecock and Chakravarty (1966), since both Al sites have the same symmetry and thus cannot be distinguished by their site splittings, but the SPM analysis allows a precise assignment (Buscher et al., 1987). The single center of Fe^{3+} detected in scolecite (Hutton and Scala, 1976) was assigned to the larger Al1 site using SPM analysis, although an even smaller difference in size than in the case of cordierite (only 0.003 Å) is reported for the two Al1, Al2 fourfold-coordinated sites (Falth and Hansen, 1979).

Mn^{2+} almost exclusively occupies the larger M2 site (Fujino et al., 1981) in forsterite (Michoulier et al., 1969). In synthetic willemite an intrasite partition coefficient of 2 in favor of the larger Zn site was observed, irrespective of the temperature of crystal growth, which varied between 773 and 1793 K (Perkins and Sienko, 1967; Howling, 1969).

Exclusive occupancy of the Ca sites by Gd^{3+} and Eu^{2+} in minerals also possessing Mg or Al sites (Morris, 1975) is in accordance with this principle of minimization of size mismatch, which is valid for smaller host sites. The results for occupancy of smaller host sites are presented in Table 1.

Data for distribution of transition-metal ions among larger host sites are much scarcer. Fe^{3+} preferentially occupies the larger M2 site in synthetic forsterite (Niebuhr, 1975). A difference in intrasite partition coefficients between two samples with different total Fe contents (0.2 and 0.006 wt%), favors the first sample by a factor of about 50 and cannot represent equilibrium distributions. Exclusive occupancy of Mg sites by Fe^{3+} in dolomite (Prissok and Lehmann, 1986) cannot be considered as proof of a site preference because this ion may have been formed by ionizing radiation after growth, as a result of the initial presence of Fe^{2+} . A single center of Fe^{3+} was also detected and assigned to the Mg site in diopside (Gaite and Michoulier, 1973). Again, since no indication of local charge compensation was observed, it may also have been formed from Fe^{2+} by exposure to ionizing radiation.

Mn^{2+} in apatite prefers the Ca site, which is ninefold-coordinated by O, over the site coordinated by six O atoms and two monovalent ions (Warren, 1970). Because of their different coordination numbers and ligands, it is not easy to evaluate precisely the relative sizes of these sites.

TABLE 1. Site distributions for smaller host ions

Mineral	Host site	c.n.	ΔR^* (Å)	K^{**} Fe ³⁺	K Cr ³⁺	K Mn ²⁺	References
Zoisite	A11	6	0.78	>20	>20		Hutton (1971)
	A12	6					
Chrysoberyl	A11	6	0.47	>20	3.6 + 0.6		Barry and Troup (1970) Forbes (1983)
	A12	6					
Cordierite	A11	4	0.10	>20			Hedgecock and Chakravarty (1966)
	A12	4					
Scolecite	A11	4	0.03	>20			Hutton and Scala (1976)
	A12	4					
Tremolite	M1	6	-0.02			>9†	McGavin et al. (1982)
	M2	6	0.01			>9	
	M3	6					
Forsterite	M1	6	0.38	>2‡	<1	>20	Niebuhr (1975), Rager (1977) Michoulier et al. (1969)
	M2	6					
Willemite	M1	4	0.12			2	Perkins and Sienko (1967) Howling (1969)
	M2	4					

* ΔR is the difference in average bond lengths.

** K is the ratio of intrasite coefficients for the smaller over that of the larger site.

† The low occupancy ratio of Mg2 may be due to large differences in individual bond lengths of 1.2 Å. No distinction between Mg2 and Mg3 is possible from superposition model analysis.

‡ The distribution coefficients for two synthetic crystals differ by a factor of 50.

The slight preference of Cr³⁺ for the smaller M1 site (Rager, 1977) in forsterite was explained by the larger ligand field stabilization energy for this site caused by the greater distortion.

PREFERENCE OF Mn²⁺ AMONG Mg AND Ca SITES

The ionic radius of Mn²⁺ ranges between those of Mg²⁺ and Ca²⁺ (Shannon, 1976). With few exceptions, the Mg sites are preferentially occupied when both Ca and Mg sites are present (see Table 2).

The largest body of experimental data for structures with both Ca and Mg sites has been accumulated for dolomite, for which huge variations in the Mg/Ca distribution ratios were observed. If equilibrium distributions are established, the intrasite partition coefficient should approach unity at high temperatures. However, in one case (Angus et al., 1984), increases in intrasite partition coefficients with increasing temperature were reported, and the large value of 115 J/(mol·K) for the entropy difference calculated from them is not acceptable: it should be close to zero. The value of 9 J/(mol·K) calculated from results of another study (Lloyd et al., 1985) appears to be reasonable. In addition, the variation of a factor of about 200 among samples in a third study (Prissok and Lehmann, 1986) was shown to be too large to be compatible with equilibrium distributions. A second group of dolomite samples was found by Lloyd et al. (1985) to exhibit no correlation between intrasite partition coefficients and temperature.

For tremolite, three Mg sites (M1–M3) and one Ca site (M4) are available (Hawthorne and Grundy, 1976). Earlier studies (Bershov et al., 1966; Manoogian, 1968; Golding et al., 1972) had detected only a single center of Mn²⁺, but additional weaker spectra were observed in a more recent investigation (McGavin et al., 1982); the most intense of those was assigned to the Ca site. However, this result is questionable, since the small size of the ⁵⁵Mn

hyperfine splitting constant (isotropic value of $-74.8 \times 10^{-4} \text{ cm}^{-1}$) suggests occupancy of a Mg site (Simanek and Muller, 1970), whereas the value that is 15% higher than that reported for the less intense centers is in the range expected for Ca sites. As shown in Figure 2, occupancy of the M1, M3 (Mg), and M4 (Ca) sites is compatible with results of SPM analyses for the most intense center. Since M1 has a larger average bond distance than M3, it should be the one that is preferentially occupied, according to the principle of size mismatch. A possible cause for the low occupancy of the M2 site (despite its having even larger average bond distance than M1) may be the variation of the individual O bond lengths for this site, although they are not very large (0.09 and 0.02 Å for M3 and M2, respectively).

In monticellite, exclusive occupancy of the Mg site (Onken, 1965) by Mn²⁺ was observed (Danilov and Manoogian, 1968).

For diopside, different intrasite partition coefficients have been reported, with some data showing preferential occupancy of the Mg site (Gaité, 1975) and other data implying nearly equal occupancy of Ca and Mg sites (Vinokurov et al., 1964). The results of an SPM analysis (Lehmann, 1982) and the sizes of the hyperfine splittings led to reversal of the site assignment proposed initially

TABLE 2. Distribution of Mn²⁺ between Mg and Ca sites

Mineral	$K = \text{Mg/Ca}$	References
Dolomite	2.7 ~ 500	Angus et al. (1984)
		Lloyd et al. (1985)
		Prissok and Lehmann (1986)
Diopside*	<1**	Vinokurov et al. (1964)
		Gaité (1975)
Monticellite	>50	Danilov and Manoogian (1968)
Tremolite*	>9	McGavin et al. (1982)

* Site assignments still controversial.

** The value of 1/ K slightly larger than 1.

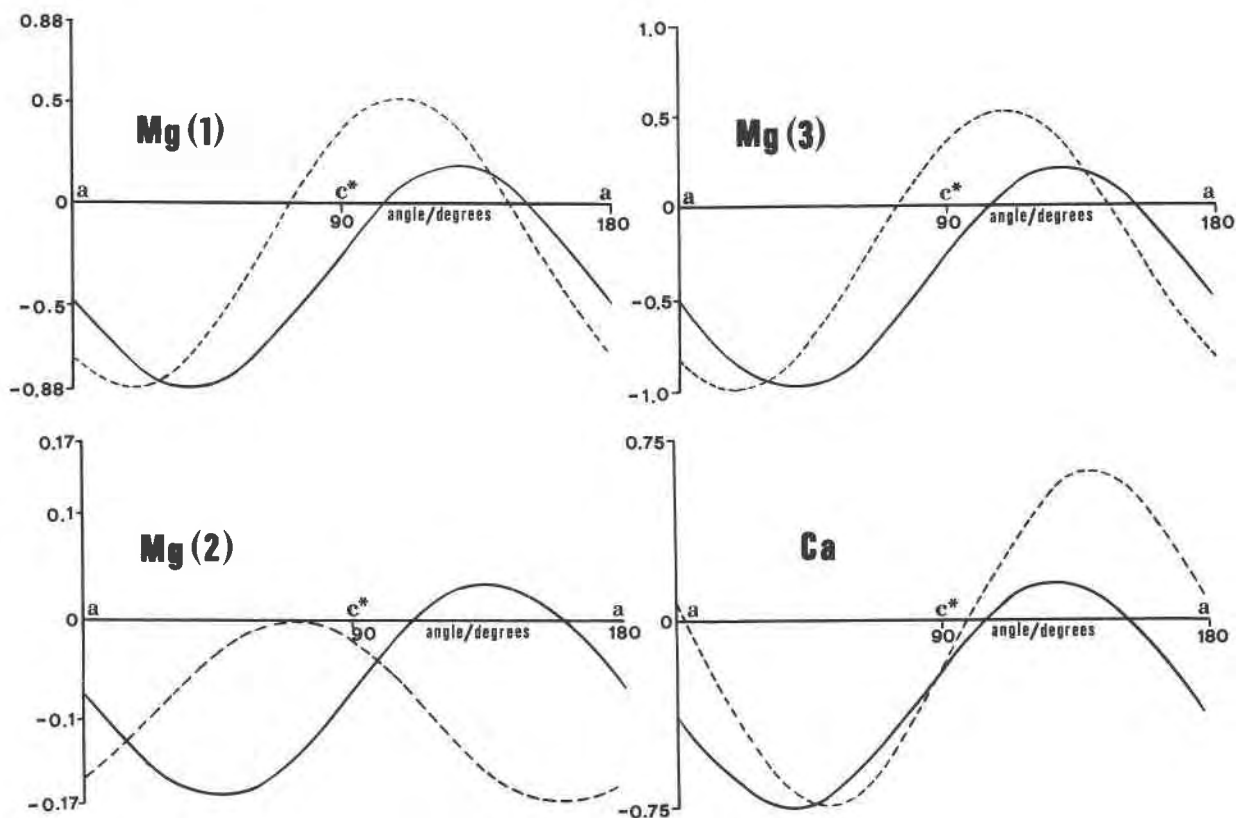


Fig. 2. Comparison of the zero field splitting pattern of the most intense spectrum of Mn^{2+} in tremolite for rotation around the **b** axis (solid lines) with the distortion patterns of the four sites of divalent cations calculated from the crystal structure data (dashed lines). Both quantities are drawn as dimensionless distortions (=effective fractions of a ligand at normal bond distance; see Heming and Lehmann, 1987). Clearly the ZFS pattern is almost equally compatible with occupation of the Mg1, Mg3, and Ca sites.

for this mineral by Gaité (1975). Table 2 summarizes the results for distribution of Mn^{2+} among Mg and Ca sites.

TENDENCY OF V^{4+} FOR FORMATION OF A SHORT V-O BOND

This ion has a strong tendency to form a very short V-O bond, which results in one very large principal value of the ^{51}V hyperfine splitting constant, A_{zz} , the other two principal values A_{yy} , A_{xx} are normally about three times smaller and of similar magnitude (see Table 3). A_{zz} is approximately aligned along the V-O bond direction, which defines the O atom involved in the V-O bond. The observed inequality $g_{\parallel} < g_{\perp}$ is characteristic of a VO^{2+} molecular ion because in a tetragonally compressed octahedron the b_{2g} (d_{xy}) level is lowest.

In most cases it is advantageous to consider the coupled substitution of V and O^{2+} in the host compound. So far, such coupled substitutions with perfect local charge compensation have been observed for three cations, Ti, Al, and Ca, in combination with different ligands, namely Ti-O and Al-OH or Al-F and Ca- H_2O .

VO^{2+} was detected by EPR in titanite from different localities. Evidently, those samples all contain V in concentrations up to 0.3 mol% (Taborsky, 1976). In all cases,

the spectra from a single center were observed (Bershov and Marfunin, 1965; Marfunin et al., 1966; Vassilikou-Dova and Lehmann, 1988a). As determined from the EPR data, the V-O bond is parallel to the Ti-O1 direction with a very short bond distance of 1.7 Å (Speer and Gibbs, 1976), as expected from the energetic preference for formation of a short V-O bond. The existence of a longer distance (by 0.2 Å) for the next shortest Ti-O bond explains why only one such center is observed. The presence of V^{4+} in Si sites cannot, however, be excluded, since in such fourfold-coordination it can normally be detected only at or below 77 K (Grunin, 1971; Manoharan et al., 1968; Havlicek and Novak, 1974; De Biasi, 1980; Di Gregorio et al., 1982). The two EPR studies of Marfunin et al. (1966) and Vassilikou-Dova and Lehmann (1988a) were performed at room temperature.

In wavellite, two crystallographically nonequivalent Al sites each have two OH groups in their first coordination spheres (Araki and Zoltai, 1968). The EPR spectrum of a prominent center of VO^{2+} with the z axis almost coincident with the c axis was obtained (Vassilikou-Dova et al., 1988), indicating substitution of axial symmetry, i.e., with local charge compensation. The direction of the V-O bond, as shown by the strongly absorbing center, clearly

TABLE 3. Spin-Hamiltonian parameters (A in 10^{-4} cm $^{-1}$) and mode of substitution for VO^{2+} in minerals

Mineral	g_1 g_{zz}	g_1^* g_{yy}, g_{xx}	A_1 A_{zz}	A_1^* A_{yy}, A_{xx}	Host atoms	Site symmetry	References	
Titanite	1.943	1.958	174.3	54.8	Ti-O1	1	Marfunin et al. (1966) Vassilikou-Dova and Lehmann (1988a)	
Apophyllite	1.933	1.974	180.2	60.6	Ca-H ₂ O	1	Marfunin et al. (1966)	
	1.948	1.96	166.2	59	K-H ₂ O	1	Vassilikou-Dova and Lehmann (1988b)	
Wavellite	1.932	1.948	171.8	54.7	Al1-H1	m	Vassilikou-Dova et al. (1988)	
	1.944		151		Al1-O2 or Al1-H ₂ O1	m 1		
Zoisite	1.948	1.955	163.4	51.2	Al1-OH	1	Hutton (1971)	
	1.938	1.936	161.7	48.8	Al3-O8	m		
	1.876	1.981	155.5	61.6		m**		
	1.934	1.944	163.7	52.9		m**		
Topaz	1.946	1.974	148.1	109.8	43.4	Si3-O6	1	Petrov (personal communication)
	1.939	1.969	164.8	100.2	56.1	Al-F	1	
Vanadinite	1.903	1.987	175.9	106.8	66.8	V-O1	m	Vassilikou-Dova and Lehmann (1989)

* Average of g_{xx} and g_{yy} or A_{zz} and A_{xx} values; they are usually alike.

** Visible at or below 77 K only.

indicates that substitution of Al1-OH1 by VO^{2+} occurs. Not unexpectedly, this is the shortest of all the four Al-OH bonds, but it also involves the Al site with the smallest average bond length (1.8 Å compared with 1.9 Å for Al12). Thus, the principle of size mismatch seems to be of little significance in the formation of the molecular ion VO^{2+} , perhaps because of the considerable rearrangements of the coordinating ions in order to create a short V-O bond of approximately 1.6 Å in length. The spectra of two additional VO^{2+} centers with absorbing peaks of much lower intensity (about 4% of that of the prominent absorption peaks) were also observed. These centers may be due to the substitution of VO^{2+} for Al1-O2, corresponding to the shortest of all the Al-O or Al1-H₂O1 bonds. In both cases, coupled substitution of an Al-O-P group by V-O would occur. Local charge compensation would thus require coupled substitution.

In zoisite, only one Al-OH group is present (Dollase, 1968), but four centers of VO^{2+} were detected (Hutton, 1971). The spectra of the center of higher intensity imply site symmetry $\bar{1}$. The z axis very nearly coincides with that of the Al1-OH bond direction, indicating the same substitution as in the prominent center in wavellite. The agreement in orientation is much better than with the Al1-O4 bond direction that was originally proposed by Hutton (1971), although the latter bond is the shortest of the Al1 site; thus, it cannot be excluded. However, in contrast to the substitution for the Al-OH group, an additional charge-compensating substitution would be required. The spectra of the second center observable at room temperature have site symmetry 2. The center was attributed by Hutton (1971) to substitution for Al3-O8, which has the shortest Al-O bond to Al3. This conclusion is therefore plausible, despite the lack of any indication of local charge compensation. Spectra of lower intensity from two additional centers could only be detected at 77 K, so they most likely arise from substitution for Si.

The presence of VO^{2+} in topaz in two different sites was reported in two papers (Dickinson and Moore, 1967; Petrov, 1983); however, only in the latter were spin-

Hamiltonian parameters and orientations of the principal axes reported, which allow assignment of peaks to a specific site. The orientation of the z axis of one center indicates coupled substitution of the shorter Al-F by VO^{2+} , which is analogous to the centers with the most intense peaks in wavellite and zoisite. The z axis of the second center of VO^{2+} is close to the Al-O3 bond direction, again the shortest of all Al-O bonds (Rippe and Gibbs, 1971). Thus, as in zoisite and wavellite, peaks from a center requiring additional charge compensation are also present. However, the reported values of A_{xx} and A_{yy} for these centers are unusually large compared with the ones reported for all other VO^{2+} centers in minerals. Corrected values of the spin-Hamiltonian parameters of VO^{2+} in topaz are reported in Table 3 (Petrov, personal communication).

For apophyllite, spectra with peaks arising from two VO^{2+} centers were recorded (Marfunin et al., 1966; Vassilikou-Dova and Lehmann, 1988b). Substitution of Ca-H₂O is undoubtedly responsible for the creation of the most prominent center, since in certain orientations a clear additional doublet hyperfine splitting due to interaction with a neighboring F⁻ ion was observed (Ca is coordinated by four O atoms, two H₂O molecules, and one F atom; Colville and Anderson, 1971). The less intense center was tentatively assigned to substitution of K⁺ (coordinated by eight H₂O molecules), since no additional ligand hyperfine splitting was observed, but substitution for Si also cannot be excluded. While substitution of M-H₂O by V-H₂O has been reported for numerous synthetic crystals (Jain and Venkateswarlu, 1980; Jain et al., 1984), apophyllite is the only known example of a mineral in which such substitution occurs.

The rule that the shortest bond is involved in the formation of the V-O molecular ion, verified in all the above cases, does not apply in a vanadinite sample from Turkey in which V⁴⁺ was detected by EPR at room temperature (Vassilikou-Dova and Lehmann, 1989). The tetravalent ion evidently occupies a V³⁺ site. The large distortion of this fourfold-coordinated site most likely causes an in-

crease in the spin lattice relaxation time sufficient to be detected at room temperature. The direction of the z axis indicates that the V-O1 with the longer bond distance (1.76 Å) compared with the other two bonds (V-O3 = 1.72 Å) (Trotter and Barnes, 1958) corresponds to the short V-O bond. Since a shortening of more than 0.1 Å must take place after the formation of the double bond, differences in the dynamic properties of these bonds may be decisive. It is most likely that this ion forms as a result of low f_{O_2} during crystal growth and not as a radiation defect.

CONCLUSIONS

Existing data allow the formulation of qualitative rules for site preferences of transition-metal impurities: (1) the differences in ligand field stabilization energy for distribution among sites of sixfold- and fourfold-coordination controls substitutions by Cr^{3+} . However, the incorporation of Mn^{2+} and Fe^{3+} in interstitial sites of sixfold-coordination in minerals that normally have only fourfold-coordinated sites cannot be explained accordingly. (2) Where two or more sites of different size occur, occupancy of the larger site is preferred. (3) The choice of the shortest M-L bond (L = O, OH, F, or H_2O) for incorporation of a VO^{2+} molecular ion has been verified in all cases, even if the principle of minimization of size mismatch is violated. The formation of a short V-O bond must be controlled by equilibria. Dynamic properties of bonds in addition to static differences must be of some influence. (4) A preference of Mn^{2+} among Mg and Ca sites for the Mg site is normally observed. The large spread of distribution ratios in some systems, e.g., in dolomite, must be considered in connection with different geochemical environments and thermal histories. Contradictions among existing results show that other factors, such as initial Mg-Ca disorder at high temperatures or a different supply of Ca^{2+} and Mg^{2+} during crystal growth, must be considered.

ACKNOWLEDGMENT

Supply of the distortion and zero field splitting patterns for tremolite (Fig. 2) by K.P. Such is gratefully acknowledged. Many thanks are expressed to Glenn Waychunas for his critical reading of the manuscript and his helpful comments and suggestions.

REFERENCES CITED

- Angus, J.G., Beveridge, D., and Raynor, J.B. (1984) Dolomite thermometry by electron spin resonance spectroscopy. *Chemical Geology*, 43, 331-346.
- Araki, T., and Zoltai, T. (1968) The crystal structure of wavellite. *Zeitschrift für Kristallographie*, 27, 21-33.
- Barry, G.R., and Troup, G.J. (1970) Electron paramagnetic resonance in natural chrysoberyl. *Physica Status Solidi*, 38, 229-234.
- Behner, T., Elbers, G., Remme, S., Prissok, F., Stegger, P., and Lehmann, G. (1986) Interstitial transition metal impurities as a possible cause of enhanced reactivities. *Berichte der Bunsen Gesellschaft für physikalische Chemie*, 90, 698-702.
- Bershov, L.V., and Marfunin, A.S. (1965) Vanadyl ion in minerals; Features of electron paramagnetic resonance of initial elements. *Izvestia Akademii Nauk, SSSR, Seriya Geologicheskaya*, 9, 45-52.
- Bershov, L.V., Marfunin, A.S., and Mineeva, R.M. (1966) EPR of Mn^{2+} in tremolite. *Geochimica*, 4, 464-466.
- Burnham, C.W., and Buerger, M.J. (1961) Refinement of the crystal structure of andalusite. *Zeitschrift für Kristallographie*, 115, 269-290.
- Burns, R.G. (1970) Mineralogical applications of crystal field theory. Cambridge University Press, Cambridge, United Kingdom.
- Buscher, R., Such, K.P., and Lehmann, G. (1987) Local relaxation around Fe^{3+} and Cr^{3+} in minerals. *Physics and Chemistry of Minerals*, 14, 553-559.
- Choi, D., and Weil, J.A. (1970) EPR study of Fe^{3+} in α -quartz: Further lithium-compensated centers. *Physical Review B*, 42 (16), 9759-9765.
- Colville, A.A., and Anderson, C.P. (1971) Refinement of the crystal structure of apophyllite. I. X-ray diffraction and physical properties. *American Mineralogist*, 56, 1222-1233.
- Danilov, A.G., and Manoogian, A. (1968) Electron spin resonance of Mn^{2+} impurities in monticellite. *Canadian Journal of Physics*, 47, 839-846.
- De Biasi, R.S. (1980) ESP of V^{4+} in α -cristobalite $AlPO_4$. *Journal of Physics C*, 13, 6235-6238.
- Dickinson, A.C., and Moore, W.J. (1967) Paramagnetic resonance of metal ions and defect centers in topaz. *Journal of Physical Chemistry*, 71, 231-240.
- Di Gregorio, G., Greenblatt, M., Pifer, J.H., and Sturge, M.D. (1982) An ESR and optical study of V^{4+} in zircon-type crystals. *Journal of Chemical Physics*, 76, 2931-2937.
- Dollase, W.A. (1968) Refinement and comparison of the structures of zoisite and clinozoisite. *American Mineralogist*, 53, 1883-1898.
- Falsh, L., and Hansen, S. (1979) Structure of scolecite from Poona, India. *Acta Crystallographica*, 35B, 1877-1880.
- Farbell, E.F., Fang, J.H., and Newman, R.E. (1963) Refinement of the chrysoberyl structure. *American Mineralogist*, 48, 804-810.
- Forbes, C.E. (1983) Analysis of the spin Hamiltonian parameters for Cr^{3+} in mirror and inversion sites of alexandrite (Al_2CrBeO_4). Determination of the relative site occupancy. *Journal of Chemical Physics*, 79, 2590-2595.
- Fujino, K., Sasaki, S., Takéuchi, Y., and Sadanaga, R. (1981) X-ray determination of electron distributions in forsterite, fayalite and tephroite. *Acta Crystallographica*, 37B, 513-518.
- Gaite, J.M. (1975) EPR study of Mn^{2+} in diopside. *Journal of Physics C*, 8, 3887-3895.
- Gaite, J.M., and Michoulier, J. (1973) Electron paramagnetic resonance of Fe^{3+} in diopside and spodumene. *Journal of Chemical Physics*, 59, 488-494.
- Gibbs, G.V. (1966) The polymorphism of cordierite. I. The crystal structure of low cordierite. *American Mineralogist*, 51, 1068-1087.
- Golding, R.M., Newman, R.H., Rae, A.D., and Tennant, W.G. (1972) Single crystal ESR study of Mn^{2+} in natural tremolite. *Journal of Chemical Physics*, 54, 1912-1918.
- Grunin, V.S. (1971) EPR of V^{4+} in cristobalite. *Soviet Physics, Solid State*, 12, 1785-1788.
- Havlicek, V., and Novak, P. (1974) EPR linewidths and intensity of V^{4+} ion $NaCa_2Mg_2V_3O_{12}$ garnet. *Czechoslovakian Journal of Physics*, 24B, 188-202.
- Hawthorne, F.C. (1983) Quantitative characterization of site-occupancies in minerals. *American Mineralogist*, 68, 287-306.
- Hawthorne, F.C., and Grundy, H.D. (1976) The crystal chemistry of the amphiboles. IV. X-ray and neutron refinements of the crystal structure of tremolite. *Canadian Mineralogist*, 14, 334-345.
- Hedgecock, M.E., and Chakravarty, S.C. (1966) EPR of Fe^{3+} ions in chrysoberyl. *Canadian Journal of Physics*, 44, 2749-2755.
- Heming, M., and Lehmann, G. (1987) Superposition model for the zero-field splitting of 3d-ion EPR: Experimental tests, theoretical calculations and applications. In J.A. Weil, Ed., *Electronic magnetic resonance of the solid state*, p. 163-174. Canadian Chemical Society, Ottawa.
- Henning, J.C.M., Liebertz, J., and Van Staple, R.P. (1967) Evidence for Cr^{3+} in four-coordination: ESR and optical investigations of Cr-doped $AlPO_4$ crystals. *Journal of Physics and Chemistry of Solids*, 28, 1109-1114.
- Holuj, F., and Jesmanowicz, A. (1978) EPR of Fe^{3+} in andalusite and kyanite at V-band and the pair spectra. *Physica Status Solidi*, 48A, 191-198.

- Holuj, F., Thyer, J.R., and Hedgecock, M.E. (1966) ESR spectra of Fe^{3+} in single crystals of andalusite. *Canadian Journal of Physics*, 44, 509–523.
- Howling, D.R. (1969) Crystal field axes of manganese sites in single-crystal willemite. *Journal of Magnetic Resonance*, 1, 339–355.
- Hutton, D.R. (1971) Paramagnetic resonance of VO^{2+} , Cr^{3+} and Fe^{3+} in zoisite. *Journal of Physics C*, 4, 1251–1257.
- Hutton, D.R., and Scala, C.M. (1976) An EPR study of Fe^{3+} in scolecite. *Physica Status Solidi*, 75B, K167–K168.
- Jain, V.K., and Venkateswarlu, P. (1980) Electron paramagnetic resonance of VO^{2+} in hydrated crystals. *Journal of Chemical Physics*, 73, 30–35.
- Jain, V.K., Seth, V.P., and Malhotra, R.K. (1984) Electron paramagnetic resonance of vanadyl ion impurities in crystalline solids. *Journal of Physics and Chemistry of Solids*, 45, 529–545.
- Lehmann, G. (1982) Spectroscopy of minerals. *Berichte der Bunsen Gesellschaft für physikalische Chemie*, 86, 985–994.
- Le Marshall, J., Hutton, D.R., Troup, G.J., and Thyer, J.R.W. (1971) A paramagnetic resonance study of Fe^{3+} in sillimanite. *Physica Status Solidi*, 5A, 769–773.
- Lloyd, R.V., Lumsden, D.N., and Gregg, J.M. (1985) Relationship between paleotemperatures of metamorphic dolomites and ESR determined Mn(II) partition ratios. *Geochimica et Cosmochimica Acta*, 49, 2565–2568.
- Manoharan, N., Kikuchi, C., and Viehmann, H. (1968) Spin resonance properties of scheelites. I. Vanadium in CaWO_4 . *Journal of Chemical Physics*, 48, 1097–1102.
- Manoogian, A. (1968) Intensity of allowed and forbidden electron spin resonance lines of Mn^{2+} in tremolite. *Canadian Journal of Physics*, 46, 1029–1033.
- Marfunin, A.S., Bershov, L.V., and Mineeva, R.M. (1966) La résonance paramagnétique électronique de l'ion VO^{2+} dans le sphène et l'apophyllite et de l'ion Mn^{2+} dans la trémolite, l'apophyllite et la scheelite. *Bulletin de la Société française de Minéralogie et de Cristallographie*, 89, 177–189.
- McGavin, D.G., Palmer, R.A., Tennant, C.W., and Devine, S.D. (1982) Use of ultrasonically modulated electron resonance to study S-state ions in mineral crystals: Mn^{2+} , Fe^{3+} in tremolite. *Physics and Chemistry of Minerals*, 8, 200–205.
- Michoulier, J., Gaite, J.M., and Maffeo, B. (1969) Résonance paramagnétique électronique de l'ion Mn^{2+} dans un monocristal de forsterite. *Comptes Rendues de l'Académie des Sciences de Paris*, 269, 535–538.
- Minge, J., Mombourquette, M.J., and Weil, J.A. (1989a) Dynamic interchange between $(\text{FeO}/\text{Na})^+$ configurations in α -quartz. *Physical Review B*, 40 (10), 6523–6528.
- Minge, J., Weil, J.A., and McGavin, D.G. (1989b) EPR study of Fe^{3+} in α -quartz: Characterization of a new type of cation-compensated center. *Physical Review B*, 40 (10), 6490–6498.
- Minge, J., Mombourquette, M.J., and Weil, J.A. (1990) EPR study of Fe^{3+} in α -quartz: The sodium-compensated center. *Physical Review B*, 42, 33–36.
- Mombourquette, M.J., and Weil, J.A. (1987) Modelling Fe^{3+} in quasi tetrahedral surroundings using the Newman superposition model. *Journal of Chemical Physics*, 87, 3385–3391.
- Mombourquette, M.J., Minge, J., Hantehzadeh, M.R., Weil, J.A., and Halliburton, L.E. (1989) Electron paramagnetic resonance study of Fe^{3+} in α -quartz: Hydrogen-compensated center. *Physical Review B*, 39 (7), 4004–4008.
- Morris, R.V. (1975) Electron paramagnetic resonance study of the site preferences of Gd^{3+} and Eu^{2+} in polycrystalline silicate and aluminate minerals. *Geochimica et Cosmochimica Acta*, 39, 621–634.
- Newman, D.J., and Urban, W. (1975) Interpretation of S-state ion EPR spectra. *Advanced Physics*, 24, 793–844.
- Niebuhr, H.H. (1975) Electron spin resonance of ferric iron in forsterite. *Acta Crystallographica*, 31A, 5274.
- Onken, H. (1965) Verfeinerung der Kristallstruktur von Monticellit. *Tschermaks mineralogische und petrologische Mitteilungen*, 10, 34–44.
- Papendick, M., Eberhard, E., and Ruscher, C. (1988) Neue Aspekte der Kristallstruktur von Andalusit. *Zeitschrift für Kristallographie*, 182, 203–204.
- Perkins, H.H., and Sienko, M.J. (1967) ESR study of Mn-doped α -zinc silicate crystals. *Journal of Chemical Physics*, 46, 2398–2401.
- Petrov, I. (1983) Paramagnetische Zentren in Topas-kristallchemische Klassifikation natürlicher Topase durch Korrelation ihrer optischen Absorptions-, ESR- und TL-Spektren. Ph.D. thesis, University of Heidelberg, Germany.
- Petrov, I., Schmetzer, K., and Eysel, H.H. (1977) Absorptionsspektren von Chrom in Topas. *Neues Jahrbuch für Mineralogie Monatshefte*, 8, 365–372.
- Prissok, F., and Lehmann, G. (1986) An EPR study of Mn^{2+} and Fe^{3+} in dolomites. *Physics and Chemistry of Minerals*, 13, 331–336.
- Rager, H. (1977) Electron spin resonance of trivalent chromium in forsterite, Mg_2SiO_4 . *Physics and Chemistry of Minerals*, 1, 371–378.
- Rao, P.S., Weil, J.A., and Williams, J.A.S. (1989) EPR investigations of carbonaceous natural quartz. *Canadian Mineralogist*, 27, 219–224.
- Ribbe, P.H., and Gibbs, G.V. (1971) The crystal structure of topaz and its relation to physical properties. *American Mineralogist*, 56, 24–30.
- Shannon, R.D. (1976) Revised effective ionic radii and systematic studies of interatomic distances in halides and chalcogenides. *Acta Crystallographica*, 32A, 751–767.
- Simanek, E., and Muller, K.A. (1970) Covalency and hyperfine structure constant A of iron group impurities in crystals. *Journal of Physics and Chemistry of Solids*, 31, 1027–1040.
- Speer, J.A., and Gibbs, G.V. (1976) The crystal structure of synthetic titanite, CaTiOSiO_4 , and the domain textures of natural titanites. *American Mineralogist*, 61, 238–247.
- Stegger, P., and Lehmann, G. (1989) The structures of three centers of trivalent iron in α -quartz. *Physics and Chemistry of Minerals*, 16, 401–407.
- Taborsky, F.K. (1976) Die Geochemie der Titanite. Habilitationsschrift, University of Freiburg, Freiburg, Germany.
- Trotter, J., and Barnes, W.H. (1958) The structure of vanadinite. *Canadian Mineralogist*, 6, 161–173.
- Troup, G.J., Edgar, A., Hutton, D.R., and Phakey, P.P. (1982) 8 mm wavelength EPR spectra of Cr^{3+} in laser quality alexandrite. *Physica Status Solidi*, 71A, K29–K31.
- Vassilikou-Dova, A.B., and Lehmann, G. (1988a) EPR of V^{4+} and Fe^{3+} in titanites. *Physics and Chemistry of Minerals*, 15, 559–563.
- (1988b) EPR of V^{4+} in apophyllite. *Physica Status Solidi*, 147B, 691–697.
- (1989) Four-valent vanadium in vanadinite. *American Mineralogist*, 74, 1182–1185.
- Vassilikou-Dova, A.B., Landrath, K.D., and Lehmann, G. (1988) EPR of VO^{2+} in the mineral wavellite $\text{Al}_3(\text{OH})_3(\text{PO}_4)_2 \cdot 5\text{H}_2\text{O}$. *Zeitschrift für Naturforschung*, 43a, 309–313.
- Vinokurov, V.M., Zaripov, M.M., Stepanov, V.G., Pol Skii, Y.E., Cherkin, G.K., and Shekun, L.Y. (1962) EPR of trivalent chromium in andalusite. *Soviet Physics, Solid State*, 3, 1797–1800.
- Vinokurov, V.M., Zaripov, M.M., and Stepanov, V.G. (1964) Paramagnetic resonance of Mn^{2+} in diopside. *Soviet Physics Solid State*, 6, 870–875.
- Warren, R.W. (1970) EPR of Mn^{2+} in calcium fluorophosphate. I. The Ca(II) site. *Physical Review B*, 2, 4383–4388.
- Winter, J.K., and Ghose, S. (1979) Thermal expansion and high-temperature crystal chemistry of Al_2SiO_5 polymorphs. *American Mineralogist*, 64, 573–586.