

## Barberite, $\text{NH}_4\text{BF}_4$ , a new mineral from Vulcano, Aeolian Islands, Italy

ANNA GARAVELLI, FILIPPO VURRO

Dipartimento Geomineralogico, Campus Universitario, Via E. Orabona 4, I-70125 Bari, Italy

### ABSTRACT

Barberite, ammonium tetrafluoroborate, occurs as a fumarolic encrustation at Fossa crater on Vulcano, Aeolian Islands, Italy. Associated minerals are sulfur, malladrite, realgar, salammoniac, cannizzarite, galenobismutite, and bismuthinite. The mineral is orthorhombic and occurs as minute crystals tabular to platy on {001} and sometimes elongated [010] or [100], forming globular aggregates (average diameter 1–2 mm). It is admixed with sulfur and sometimes with malladrite, salammoniac, and realgar. The very thin crystals (about 1  $\mu\text{m}$  in thickness) range from about 50 to 300  $\mu\text{m}$  in length and are very unstable in air. The mineral is colorless, transparent to translucent, nonfluorescent, with a vitreous luster and a white streak.  $\text{VHN}_{25} = 14.2 \text{ kg/mm}^2$  (range: 13.0–15.4), cleavage {100} perfect, {010} and {001} good, fracture not observed.  $D_{\text{calc}} = 1.90$ ,  $D_{\text{meas}} = 1.89(3) \text{ g/cm}^3$ . Barberite is biaxial,  $2V_{\text{meas}} = 90 \pm 2^\circ$ ; the mean  $n$ , calculated from the Gladstone-Dale relationship, is 1.308. It has  $a = 9.0615(7)$ ,  $b = 5.6727(6)$ ,  $c = 7.2672(6) \text{ \AA}$ ,  $V = 373.5(1) \text{ \AA}^3$ ,  $a:b:c = 1.5974:1:1.2811$ ,  $Z = 4$ , space group  $Pnma$ . The strongest six lines in the X-ray powder diffraction pattern are [ $d$  in ångströms ( $I/I_0$ )  $hkl$ ]: 3.183(100)211, 3.540(90)210, 2.8982(80)112, 4.472(75)011, 2.1631(70)113, 2.5362(65)121. On the basis of chemical analysis, IR spectroscopy, and X-ray data, barberite corresponds to the synthetic compound  $\text{NH}_4\text{BF}_4$ . The mineral is named after Franco Barberi, professor of volcanology at Pisa University.

### INTRODUCTION

The island of Vulcano is part of the Aeolian Archipelago and lies off the northern coast of Sicily. It has been shaped by various volcanoes and in recent times its geological, volcanic, and structural features have been the subject of many detailed investigations (e.g., Barberi et al., 1974; Keller, 1980; Frazzetta et al., 1983). The Fossa crater, one of the most recent volcanoes of Vulcano, is a 391-m cone, with a base diameter of 1 km (Fig. 1). Since the last explosive eruption, which occurred at the Fossa crater from 1888 to 1890 (Mercalli and Silvestri, 1890), Vulcano has been in a dormant state characterized by fumarolic activity of varying intensity. After a peak value of 615  $^\circ\text{C}$ , recorded in 1924 (Sicardi, 1973), the average temperatures have been below 400  $^\circ\text{C}$ . Since 1987 there has been a progressive increase in activity at the Fossa crater, where the maximum temperature of the fumaroles has increased from 330 to 700  $^\circ\text{C}$  (October 1992).

In order to contribute to the understanding of the genesis and evolution both of fluids and depositional environments of sublimates at Vulcano, since 1988 we have been studying the fumarolic products and encrustations at La Fossa crater from a mineralogical, chemical, and morphological point of view, carrying out two to three field studies each year.

In 1988 sulfur, salammoniac, and sassolite were found to be present throughout the fumarolic area of the Fossa cone. Since 1990, as well as the above-mentioned minerals, some sulfides and sulfosalts were also found (Di

Chio et al., 1991) around the hottest fumaroles (FF and FA in Fig. 1). In October 1992, when the maximum temperature of the crater fumaroles increased to 700  $^\circ\text{C}$ , we found barberite on the ground around the FF and FA vents. The mineral was recognized as a new species on the basis of its powder pattern and cell parameters, which closely resembled those for synthetic  $\text{NH}_4\text{BF}_4$  (JCPDS 15-745). Chemical analyses, IR spectroscopy, and density confirm the identity of barberite with the synthetic compound.

The mineral  $\text{NH}_4\text{BF}_4$  has been named barberite after Franco Barberi, professor of volcanology at the University of Pisa, who, as president of the Gruppo Nazionale per la Vulcanologia (National Group for Volcanology, Italy), has promoted volcanological, geochemical, and mineralogical research on the island of Vulcano. Both the mineral and the name have been approved by the Commission on New Minerals and Mineral Names, IMA. The holotype is deposited in the mineralogical museum of Bari University (N. 4/nm).

### OCCURRENCE AND PARAGENESIS

The Fossa volcano, for which documentation is available dating back to about 500 B.C., is characterized by eruptions, generally lasting a few years, interspaced by a few decades of calm, with intensive fumarolic activity. The last eruption began at the Fossa crater in 1888 and ended in 1890; since then the volcano has remained in a fumarolic stage.

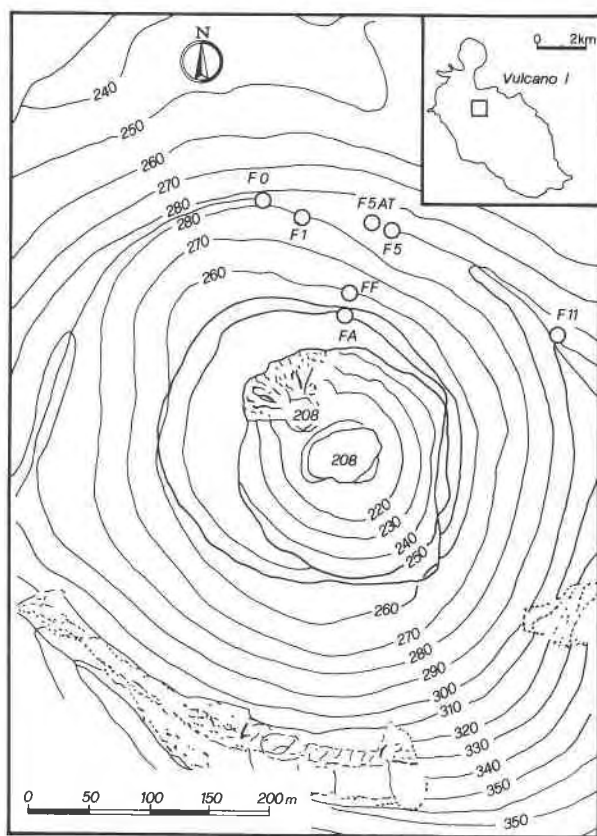


Fig. 1. Location of the Fossa crater fumaroles at Vulcano (redrawn from Gruppo Nazionale per la Vulcanologia, 1988).

In 1987, when the maximum temperature of the fumaroles was below 400 °C, sulfur, salammoniac, and sassolite were the only phases present in the fumarolic area of the Fossa cone. Since 1990, when the maximum temperature of the hottest fumaroles (FF and FA in Fig. 1), situated on the inner slope of the crater, increased to 607 °C, bismuthinite ( $\text{Bi}_2\text{S}_3$ ), cannizzarite ( $\text{Pb}_4\text{Bi}_{5+3}\text{S}_{11.5+1.5}$ ), galenobismutite ( $\text{PbBi}_2\text{S}_4$ ), and sphalerite ( $\text{ZnS}$ ) have been collected, in addition to the minerals mentioned above. These phases were also observed in 1991 and 1992; in 1992 barberite was collected. Other associated minerals are malladrite ( $\text{Na}_2\text{SiF}_6$ ) and realgar ( $\text{AsS}$ ). The ground temperature where we collected barberite ranged from 200 to 600 °C.

Barberite occurs as globular aggregates (average diameter 1–2 mm) admixed with sulfur; salammoniac (where the temperature of the ground is below 300 °C), malladrite, and realgar are admixed as well. Very thin crystals of barberite (about 1  $\mu\text{m}$  in thickness) range from about 50 to 300  $\mu\text{m}$  in length (Fig. 2).

Tetrafluoroborate ions can be formed only in a strongly acid solution containing more F than B (see references in Onishi, 1969). Barberite can be formed by the reaction between boron trifluoride and ammonium fluoride, according to Berzelius (in Mellor, 1924).

Barberite in the sampling area reacts with HCl present

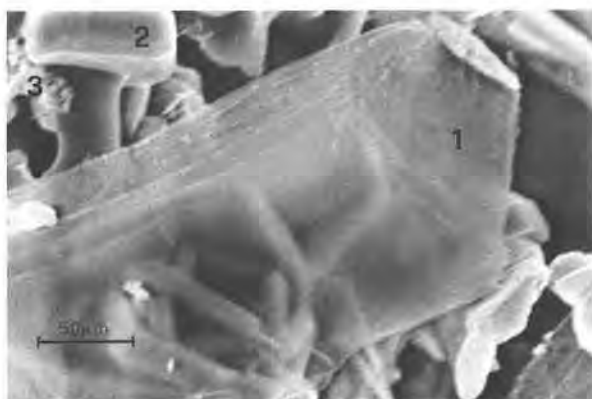


Fig. 2. Scanning electron photomicrograph of a platy and very thin crystal of barberite (1) on malladrite (2) and realgar (3). Scale bar = 5.0  $\mu\text{m}$ .

in fumarolic fluids (about 0.5 vol%) to form  $\text{NH}_4\text{Cl}$ ,  $\text{BF}_3$ , and HF; in damp air, as the synthetic  $\text{NH}_4\text{BF}_4$ , it decomposes partially, yielding perhaps  $\text{NH}_3\text{BF}_3\text{OH}$  and HF (Pascal, 1961; Bonadeo and Silberman, 1969), and so we conserve the mineral in a covered filter weighing bottle made of a transparent plastic material.

#### CHEMISTRY

Barberite is very soluble in  $\text{H}_2\text{O}$ ; 100 parts of  $\text{H}_2\text{O}$  at 16 and 100 °C dissolve 25 and 95–98 parts of  $\text{NH}_4\text{BF}_4$ , respectively (Stolba, 1870; Mellor, 1924). A preliminary qualitative analysis was made by atomic absorption spectroscopy for B and by the Nessler method for  $\text{NH}_4$ . Since no electron probe analysis was possible because of the chemical composition of the mineral, quantitative analyses of barberite were carried out by wet methods. Because of the small amounts of the collected mineral available, analytical methods were tested many times on synthetic 99.99%  $\text{NH}_4\text{BF}_4$  from Aldrich Chemical Co.

A small amount of purified material, dissolved in deionized  $\text{H}_2\text{O}$ , was analyzed by means of a Dionex ion chromatograph. For the cations, column CS 10 was used with 25 mM of HCl and 0.25 mM of 2–3 diamino propionic acid monohydrochloride as eluents. For the anions, column AS 5A-5  $\mu\text{m}$  was used with 2 mM of  $\text{Na}_2\text{CO}_3$ , 1 mM of NaOH, and 1 mM of p-cyanophenol as eluents. The analytical results (in weight percent) are Na = 0.4, K = 2.2,  $\text{NH}_4$  = 16.6, F = 0.3, Cl = 0.6, Br = 0.1,  $\text{BF}_4$  = 79.8, total = 100.0. The F, Cl, and Br and an appropriate amount of  $\text{NH}_4$  were deducted as admixed salammoniac. The empirical formula (based on  $\text{BF}_4 = 1$ ) is  $[(\text{NH}_4)_{0.96}\text{K}_{0.06}\text{Na}_{0.02}]_{\Sigma=1.04}\text{BF}_{4.00}$ . The simplified formula can be written as  $\text{NH}_4\text{BF}_4$  and requires  $\text{NH}_4 = 17.21$ ,  $\text{BF}_4 = 82.79$ , total 100.00 wt%.

#### X-RAY CRYSTALLOGRAPHY

An X-ray single-crystal study would have been desirable but proved impossible owing to the very platy habit of the crystals and the unstable nature of the mineral. In

**TABLE 1.** X-ray powder pattern for barberiite and synthetic NH<sub>4</sub>BF<sub>4</sub>

hkl	Barberiite			Synthetic NH <sub>4</sub> BF <sub>4</sub>		JCPDS 15-745	
	<i>d</i> <sub>calc</sub>	<i>d</i> <sub>obs</sub>	// <i>l</i> <sub>0</sub>	<i>d</i> <sub>obs</sub>	// <i>l</i> <sub>0</sub>	<i>d</i> <sub>obs</sub>	// <i>l</i> <sub>0</sub>
101	5.6693	5.669	25	5.677	22	5.668	30
200	4.5308	4.531	30	4.534	40	4.528	60
011	4.4717	4.472	75	4.480	75	4.482	100
201	3.8448	3.843	50	3.850	40	3.844	50
002	3.6337	3.634	45	3.639	50	3.635	50
210	3.5402	3.540	90	3.544	100	3.542	85
102	3.3726	3.374	10	3.377	10	3.376	12
211	3.1826	3.183	100	3.187	80	3.186	85
112	2.8989	2.8982	80	2.9033	50	2.902	60
202	2.8346	2.8346	50	2.8372	30	2.839	35
301	—	—	—	2.7936	2	2.792	4
121	2.5366	2.5362	65	2.5394	35	2.541	45
311	2.5030	2.5030	20	2.5047	12	2.505	12
220	2.4041	2.4037	20	2.4074	12	2.409	12
103	2.3403	2.3404	55	2.3433	18	2.341	25
302	—	—	—	—	—	2.324	35
221	2.2825	2.2822	65	2.2855	35	2.286	35
400	2.2654	2.2651	15	2.2662	6	2.266	10
022	2.2358	2.2358	40	2.2397	13	2.238	18
013	2.2278	2.2275	17	2.2304	13	2.232	18
122	2.1707	2.1716	40	2.1746	35	2.176	45
113	2.1634	2.1631	70	—	—	2.165	45
312	2.1496	2.1493	30	2.1525	12	2.151	12
203	2.1363	2.1358	10	2.1384	4	2.138	6
410	2.1038	2.1037	20	2.1054	14	2.104	12
411	2.0208	2.0207	4	2.0230	2	2.022	4
222	2.0050	2.0043	5	2.0069	2	2.008	4
303	1.8898	1.8900	4	1.8921	2	1.891	2
031	—	—	—	—	—	1.834	2
412	1.8207	1.8209	12	1.8233	4	1.821	6
123	1.8051	1.8054	15	1.8079	7	1.808	8
104	—	—	—	—	—	1.782	2
501	—	—	—	—	—	1.759	<1
230	—	—	—	—	—	1.749	<1
421	1.7198	1.7201	12	1.7216	5	1.721	6
223	—	—	—	—	—	1.708	2
114	—	—	—	—	—	1.701	<1
511	—	—	—	1.6815	3	1.680	4
132	—	—	—	1.6513	12	1.653	20
502	—	—	—	1.6235	2	1.622	4
a = 9.0615(7) Å			a = 9.0701(8) Å			a = 9.063 Å	
b = 5.6727(6) Å			b = 5.6803(7) Å			b = 5.686 Å	
c = 7.2672(6) Å			c = 7.2776(9) Å			c = 7.272 Å	

fact, the crystals of barberiite used for the experiment liquefy after 1–2 d under the combined effects of radiation and high room moisture. On the other hand, attempts to coat the crystalline materials were unsuccessful because they decompose when in contact with cellulose acetate. Finally, the rotation photograph spots obtained on a sample introduced into a Lindemann capillary tube are very broad, and so only one cell parameter could be determined, and that with poor precision [ $c = 7.30(3)$  Å]. On the other hand, the structure of synthetic NH<sub>4</sub>BF<sub>4</sub> is well known (Hoard and Blair, 1935; Clark and Lynton, 1969; Caron and Ragle, 1971). It is orthorhombic, space group *Pnma*;  $Z = 4$ .

Instead, X-ray powder diffraction patterns were obtained separately for barberiite and for the synthetic compound (Table 1). A PW 1800 Philips diffractometer (CuK $\alpha$  radiation,  $\frac{1}{4}^\circ$   $2\theta$ /min) was used. The examined samples were spread on the support surface of pure, powdered, and compressed NaF, allowing the NaF surface to remain exposed between sample grains. With this preparation technique, the NaF may also be used as an internal standard (Garavelli and Mazzi, 1957). Indexing was performed on the basis of lattice parameters obtained from the references above.

In Table 2 chemical, physical, and crystallographic data of barberiite are compared with those of the two other tetrafluoroborate minerals: avogadrite, (K,Cs)BF<sub>4</sub> (Zambonini, 1926), and ferrucite, NaBF<sub>4</sub> (Carobbi, 1933).

#### PHYSICAL AND OPTICAL PROPERTIES

Minute crystals of barberiite appear tabular to platy on {001}, pseudo-hexagonal, commonly elongated [010] or [100]. The observed forms are rhombic bipyramid; no twinning was observed. The very thin crystals (about 1  $\mu$ m in thickness and 50–300  $\mu$ m in length, Fig. 2), are colorless, with a vitreous luster and a white streak. They are transparent to translucent and nonfluorescent. A density of 1.89(3) g/cm<sup>3</sup> was measured by flotation in a benzene-bromofom mixture. The calculated density for the

**TABLE 2.** Relationship of barberiite with other tetrafluoroborates

	Avogadrite	Ferrucite	Barberiite
Chemical formula	(K,Cs)BF <sub>4</sub>	NaBF <sub>4</sub>	NH <sub>4</sub> BF <sub>4</sub>
System crystal	orthorhombic	orthorhombic	orthorhombic
Space group	<i>Pnma</i>	<i>Cmcm</i>	<i>Pnma</i>
Unit-cell parameters	a = 8.664 Å b = 5.480 Å c = 7.02 Å V = 333.3 Å <sup>3</sup>	a = 6.32 Å b = 6.25 Å c = 6.77 Å V = 267.4 Å <sup>3</sup>	a = 9.0615(7) Å b = 5.6727(6) Å c = 7.2672(6) Å V = 373.5(1) Å <sup>3</sup>
Strongest lines	3.41 Å (100) 3.26 Å (80) 3.06 Å (75)	3.39 Å (100) 3.41 Å (85) 2.31 Å (40)	3.183 Å (100) 3.540 Å (90) 2.898 Å (80)
Optical data	biaxial (–) 2V very large $\alpha = 1.3239$ $\beta = 1.3245$ $\gamma = 1.3247$	biaxial (+) 2V = 11°25' $\alpha = 1.301$ $\beta = 1.3012_{\text{calc}}$ $\gamma = 1.3068$	biaxial ( $\pm$ ) 2V = 90 $\pm$ 2° $n_{\text{calc}} = 1.3081$

Note: data for avogadrite and ferrucite from JCPDS 16-378 and 11-671, respectively; optical data from Palache et al. (1951); barberiite lattice parameters refined from powder data.

ideal formula is  $1.90 \text{ g/cm}^3$ . The microindentation hardness with a 25-g load ( $\text{VHN}_{25}$ ) is  $14.2 \text{ kg/mm}^2$  (range: 13.0–15.4).

Crystals of barberite are biaxial. The value of  $2V$ , measured in air with a universal stage, is  $90 \pm 2^\circ$ . No indices of refraction are obtainable using the Becke line method because barberite decomposes when in contact with the immersion medium. The mean index of refraction calculated from the Gladstone-Dale relationship, using the ideal formula and the constants given by Mandarino (1976), is 1.308.

The infrared spectra of barberite and synthetic  $\text{NH}_4\text{BF}_4$  are identical. The spectra show a broad band at  $3250\text{--}3159 \text{ cm}^{-1}$ , caused by  $\text{NH}$  stretching, and a sharp peak at  $1400 \text{ cm}^{-1}$ , caused by  $\text{NH}_2$  deformation. Three bands at about  $1300$ ,  $1750$ , and  $2150 \text{ cm}^{-1}$ , two peaks at  $1000$  and  $1100 \text{ cm}^{-1}$ , a weak peak at  $770 \text{ cm}^{-1}$ , and a doublet at  $535$  and  $525 \text{ cm}^{-1}$  constitute the vibrational spectrum of the  $\text{BF}_4^-$  ion, according to the data reported by Bonadeo and Silberman (1970).

#### ACKNOWLEDGMENTS

The authors thank G. Ferraris (University of Turin) for his helpful advice and suggestions; L. Leoni and M. Cavallaro for their collaboration on the microindentation hardness analysis at Earth Science Department, Pisa University; F. Scordari (Geomineralogical Department, Bari University) for his helpful suggestions and for barberite X-ray single-crystal analysis; and M. Salamida (ENEL laboratory, Bari) for his assistance in ion chromatographic analyses. Thanks are also due to R. Erd for his conscientious and very useful reviews.

This research was carried out with the financial support of the National Group for Volcanology, Italy. SEM investigations were performed at the Dipartimento Geomineralogico (Bari University, Italy) using equipment from the C.N.R. Centro Chimica dei Plasmi.

#### REFERENCES CITED

- Barberi, F., Ferrara, G., Keller, J., Innocenti, F., and Villari, L. (1974) Evolution of the Aeolian arc volcanism. *Earth and Planetary Science Letters*, 21, 269–276.
- Bonadeo, H., and Silberman, E. (1969) Infrared studies on  $\text{BF}_4^-$  in alkali halide solid solutions. *Journal of Molecular Spectroscopy*, 32, 214–221.
- Bonadeo, H.A., and Silberman, E. (1970) The vibrational spectra of sodium, potassium and ammonium fluoroborates. *Spectrochimica Acta*, 26A, 2337–2343.
- Carobbi, G. (1933) Sulla presenza di un nuovo minerale fra i prodotti dell'attività fumarolica del Vesuvio. *Periodico di Mineralogia*, 4, 410–421.
- Caron, A.P., and Ragle, J.L. (1971) Refinement of the structure of orthorhombic ammonium tetrafluoroborate,  $\text{NH}_4\text{BF}_4$ . *Acta Crystallographica*, B27, 1102–1107.
- Clark, M.J.R., and Lynton, H. (1969) Crystal structures of potassium, ammonium, rubidium and cesium tetrafluoroborates. *Canadian Journal of Chemistry*, 47, 2579–2586.
- Di Chio, F., Garavelli, A., Laviano, R., and Vurro, F. (1991) Fumarolic sublimates from the Fossa Grande Crater at Vulcano (Aeolian Islands), p. 36. International Conference on Active Volcanoes and Risk Mitigation, 27 August–1 September, 1991, Naples, Italy.
- Frazzetta, G., La Volpe, L., and Sheridan, M.F. (1983) Evolution of the Fossa Cone, Vulcano. *Journal of Volcanology and Geothermal Research*, 17, 329–360.
- Garavelli, C.L., and Mazzi, F. (1957) Un metodo per l'esecuzione di diffratogrammi a raggi X su campioni dell'ordine del centigrammo. *Atti della Fondazione "Giorgio Ronchi"*, Anno XII, 6, 1–13.
- Gruppo Nazionale per la Vulcanologia (1988) Intervento straordinario a Vulcano: Estate 1988, p. 15. Rapporto CNR, Roma.
- Hoard, J.L., and Blair, V. (1935) The crystal structures of rubidium and ammonium fluoroborates. *Journal of American Chemical Society*, 57, 1985–1988.
- Keller, J. (1980) The island of Vulcano. *Rendiconti della Società Italiana di Mineralogia e Petrologia*, 36, 369–414.
- Mandarino, J.A., (1976) The Gladstone-Dale relationship. I. derivation of new constants. *Canadian Mineralogist*, 14, 498–502.
- Mellor, J.W. (1924) A comprehensive treatise on inorganic and theoretical chemistry, vol. 5, p. 127. Longman, New York.
- Mercalli, G., and Silvestri, O. (1890) Le eruzioni dell'Isola di Vulcano incominciate il 3 agosto 1888 e terminate il 22 marzo 1890, relazione scientifica. *Annali dell'Ufficio Centrale Meteorologico e Geodinamico Italiano*, 10, 1–23.
- Onishi, T. (1969) On the presence of tetrafluoroborate ions in natural waters. *Bulletin of the Chemical Society of Japan*, 42, 127–131.
- Palache, C., Berman, H., and Frondel, C. (1951) Dana's system of mineralogy, vol. 2, p. 97–99. Wiley, New York.
- Pascal, P. (1961) *Nouveau traité de chimie minérale*, vol. VI, p. 89–92. Masson, Paris.
- Sicardi, L. (1973) The thermal oscillations of the fumaroles of the Island of Vulcano from 1913 to 1970. *Stromboli*, 13, 65–68.
- Stolba, F. (1870) *Zeitschrift für analytische Chemie*, 9, 95 (not seen; extracted from Mellor, J.W.: A comprehensive treatise on inorganic and theoretical chemistry, vol. 5, Longman, New York, 127, 1924).
- Zambonini, F. (1926) Sulla presenza tra i prodotti dell'attuale attività del Vesuvio di una varietà cesifera del fluoroborato di potassio. *Rendiconti della Reale Accademia Nazionale dei Lincei*, 3, 644–649.

MANUSCRIPT RECEIVED JULY 26, 1993

MANUSCRIPT ACCEPTED NOVEMBER 19, 1993